

Accurate Soiling Ratio Determination with Incident Angle Modifier for PV Modules

Nepal, Pramod; Korevaar, Marc; Ziar, Hesan; Isabella, Olindo; Zeman, Miro

DOI

[10.1109/JPHOTOV.2018.2882468](https://doi.org/10.1109/JPHOTOV.2018.2882468)

Publication date

2019

Document Version

Accepted author manuscript

Published in

IEEE Journal of Photovoltaics

Citation (APA)

Nepal, P., Korevaar, M., Ziar, H., Isabella, O., & Zeman, M. (2019). Accurate Soiling Ratio Determination with Incident Angle Modifier for PV Modules. *IEEE Journal of Photovoltaics*, 9(1), 295-301. Article 8556021. <https://doi.org/10.1109/JPHOTOV.2018.2882468>

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

Accurate Soiling Ratio Determination with Incident Angle Modifier for PV Modules

Pramod Nepal, Marc Korevaar, Hesam Ziar, Olindo Isabella, and Miro Zeman

Abstract— The deposition of dust, soil, and microfibers resulting from the surroundings as well as the growth of minute pollens like moss and fungi contributes toward photovoltaic (PV) module soiling. Soiling is a widely recognized factor that significantly reduces the power production by acting as a barrier for effective light absorption by the module. The estimated loss in the irradiance and power can be determined with the help of soiling ratio (SR) parameter, which is the ratio of short-circuit current (I_{sc}) or maximum power produced (P_{max}) by a soiled module to a clean one. The measured SR is normally not constant throughout a day but changes with the position of the Sun and the amount of dust on the module. This paper proposes an empirical equation to determine the SR at any instant of time of the day based on the Sun's angle of incidence (AOI) on the module and a single SR value measured at the mid of the day. First, an indoor experiment was done to examine the angular loss dependency of two totally different dust colors for the same SR at normal light incidence. Next, in an outdoor experiment, the SR of an artificially soiled module was measured over the course of the day for three conditions of high, medium, and low daily average irradiance due to variation in cloudiness. Then, an empirical equation is introduced based on incident angle modifier (IAM) for soiled and cleaned PV modules. The proposed equation was further used to determine the SR. Finally, the average residuals between the measured and the modeled soiling ratios were determined with the help of root mean square deviation (RMSD). The results showed that the modeled SR was determined with a deviation of $\pm 0.21\%$ and $\pm 0.28\%$ respectively for a high and medium irradiance day, whereas the deviation increased to $\pm 1.04\%$ in case of low irradiance due to clouds.

Index Terms— Photovoltaic (PV) module, module soiling, soiling ratio (SR), incident angle modifier (IAM), angle of incidence (AOI), angular loss (AL), transmission loss (t_{loss}), solar power generation.

I. INTRODUCTION

The technological advancement in the field has resulted in PV technology becoming one of the leading renewable energy sources currently available. The annual growth of PV installations was reported to be 40% from 2010 to 2016 [1]. Despite this outstanding growth, the performance ratio (PR) of PV systems has been greatly influenced due to various environmental factors like non-uniform irradiance, wind, rain, module temperature, and soiling.

P. Nepal is an M.Sc. graduate from Sustainable Energy Technology (SET) at Delft University of Technology, 2628CD Delft, The Netherlands (e-mail: nepalpramod91@gmail.com).

M. Korevaar is with the Kipp & Zonen, Delftechpark 36, 2628 XH, Delft, The Netherlands (email: marc.korevaar@kippzonen.com).

H. Ziar, O. Isabella, and M. Zeman are with the Photovoltaic Materials and Devices Group, Delft University of Technology, 2628CD Delft, The Netherlands (e-mail: h.ziar@tudelft.nl; o.isabella@tudelft.nl; m.zeman@tudelft.nl).

The accumulation of dust, sand, and biological deposits like the growth of algae, moss or bird droppings, and air pollution are categorized as PV module soiling [2]. It directly obstructs the irradiation falling on the module by forming a thin layer of dust usually less than 10 μm [3]. The module soiling is considered to be the third major environmental factor after irradiation and temperature, which directly accounts for lower performance statistics of a PV system [4]. The soiling of PV modules majorly depends on two factors: (i) Installation design of the PV plant such as tracking mechanisms, tilt, and orientation (ii) Local environmental conditions such as atmospheric dust intensity, relative humidity (RH), wind, and rainfall [5]. Therefore, dust accumulation is a result of the rate of deposition and rate of removal by the wind and rain event [6]. Thus, based on the location and dust type the soiling losses might vary. Experiments carried out at different parts of the world suggests, the daily may vary anywhere between 0.1% per day to 20% per day based on the location and rain events [7][8]. Several experiments also suggested that the average soiling loss in the Middle East regions were more severe compared to other parts of the world [3]. In Egypt, an experiment was performed on 100 different glass samples installed at different tilt angles and azimuth orientations for 8 months, the cell at an angle of 45° facing south resulted in a reduction of output power by 17.4% per month [9]. Rainfall event acts as a natural cleaning for the soiled modules. Around 5 mm of rainfall was noticed to completely clean the module in Arizona region [10].

Beside the location and environmental conditions, module's properties also possess a significant influence on soil deposition. Depending on a PV module's glazing surface and orientation, it is subjected to two types of the angle of incidence (AOI) influences, namely mechanical and optical [11]. The mechanical response is associated with its tilt and orientation and the light source. Based on the angle of incidence, solar radiation is de-rated by a cosine of the angle between the surface normal and the Sun's angle commonly known as "cosine effect" [12]. On the other hand, the optical effect is due to the surface properties of the module. A module with an anti-reflective surface coating (ARC) is more resilient towards the effect of AOI than without [11]. Higher AOI increases reflectance losses and thus reducing the amount of solar beam that can be utilized by the module [13]. Several incident angle modifier (IAM) methods like; Physical, ASHRAE, Sandia, Martin & Ruiz have been developed to calculate the optical losses of irradiation due to reflection at the module surface. In 1983, Wilson and Ross found that the cell surface are highly influenced by the surface texture and soiling level because of both Fresnel reflection and soil shadowing [14]. A study carried out in Malaga, Spain has

resulted that the relative irradiance loss of a solar cell increased AOI of the Sun [7], whereas [15] found that the density of soil significantly lowers its critical AOI of the module suggesting higher reflection losses compared to clean. Similarly, Martin & Ruiz have gone one step further and characterized the angular losses in different module technologies with the help of an outdoor experiment. The experimental and modelled data were used to define a dimensionless parameter called “Angular loss coefficient” (a_r) [16]. The optical response of PV module is a surface characteristic, therefore solar irradiance is highly influenced due to the presence of the soiling.

In this paper, a mini PV module was tested indoor for two soil colors at same SR to compare their angular loss (AL) at different AOI. Next, a commercial scale module was tested outdoor at two soiling conditions to estimate (a_r) and subsequently AL. The artificial soiling technique were carried out with the help of soiling chamber and a spray gun also demonstrated in the work of [17] [18]. Then, after introducing the soiling ratio model, the soiling ratio curves were constructed with the help of calculated angular losses (AL) and a single SR measurement done at solar noon for three different scenarios of high, medium, and low irradiance conditions due to different levels of cloudiness. Finally, the measured soiling ratio (SR) curve was compared with modeled soiling ratio (SR^{model}) by calculating the root mean square deviation (RMSD).

II. METHODOLOGY

A. Indoor measurement setup

An incandescent light of 2000 Watts (Arrilite 2000) was used as a constant light source. A mini-monocrystalline silicon module of $2 W_p$ was vertically kept at 1.5 meters from the light source, where the irradiance intensity was $1000 W/m^2$. The module was supported on a flexible arrangement to allow for movement along two axes, i.e. $0-360^\circ$ on horizontal axis and $0-60^\circ$ for vertical angle. The experiments were carried out in a dark room to avoid the influence of other lights in the proximity. For each experiment, the module was rotated carefully from -90° to 90° with 10° interval measured with a 360° circular scale at the bottom of the module. The entire experimental setup is shown in Figure 1.

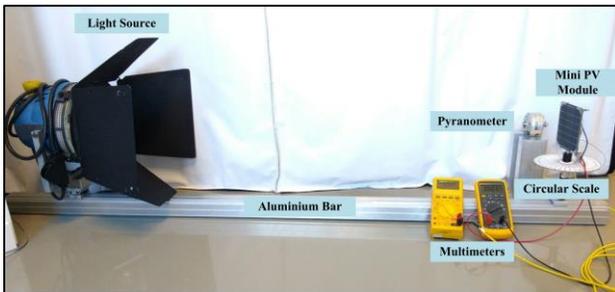


Fig. 1. Indoor experimental setup consisting of a light source, two multimeters, a mini PV module, and a circular scale supported by an aluminium bar. Instantaneous module temperature of soiled and clean module was measured by a $10 K\Omega$ temperature measuring sensor (thermistor, negative temperature coefficient (NTC)), applied at the back of the module. Two multimeters were used to measure the short-circuit current (I_{sc}) and thermistor resistance at each AOI interval.

Two dust samples (produced by KSL Staubtechnik GmbH) mainly characterized by their color were taken for the experiment. Arizona Test Dust (ARIZ-TD (Quartz (SiO_2))) has light-brown color, whereas Prüf-staub (P-030KS16) is black. Two soiling mixture were prepared by suspending 1.5 grams of each dust with 20 ml of deionized water. An equal amount of $8 ml$ ($\sim 0.0029 g/cm^2$) of each soiling mixture was applied on the module with the help of an air gun at 1 bar of air pressure from a distance of 25 cm (pointing horizontally on a flat lying module). I_{sc} and module temperature was measured again to examine the differences in SR at each AOI of the light.

B. Outdoor measurement setup

The experiment was carried out using a rooftop PV setup installed at the height of 16 meters from the ground at Kipp & Zonen BV, Delft, The Netherlands. Two polycrystalline silicon modules (CS6K-270P produced by Canadian solar) installed at a tilt angle of 30° facing south (182°) with an identical mounting mechanism were chosen. One of the modules was uniformly soiled while the other one was kept clean to make a comparison. A soiling mixture was prepared by suspending the Grand Canyon test dust (Eisenoxid- Fe_2O_3 , KSL-312) produced by KSL Staubtechnik GmbH with deionized water in 1:10 ratio. To facilitate a homogeneous soiling process by reducing the wind effects, a wooden-aluminium chamber was also built, which can be seen in Figure 2. The chamber was placed carefully on top of the PV module to be soiled. Finally, module soiling was carried out in two folds, first light soiling, $SR=93.2\%$ ($t_{loss}=6.8\%$) and then after additional soiling, $SR=86.9\%$ ($t_{loss}=13.1\%$) with the help of a paint gun at 1.5 bars of air pressure from 1-meter distance (pointed vertically).

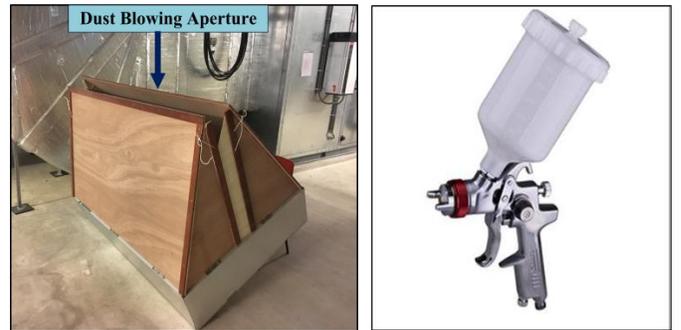


Fig. 2. A wooden-aluminium chamber ($1660 \times 1000 \times 900 mm^3$) (left) and the paint gun (600 cc) used for soiling (right). The chamber has a small opening at the top (pointed by a blue arrow) that provides a space for the gun filled with the soiling mixture. A pressure hose was connected at the bottom of the paint gun at 1.5 bars to provide enough pressure for soiling.

An instantaneous short circuit current (I_{sc}) from both the modules was recorded by measuring its voltage drop (V_D) over a 10-meter long TUV solar cable with a resistance (R_{sc}) of $63m\Omega$ (the accuracy of the multimeter to measure cable resistance is $(0.2\% \text{ of reading} \pm 1 \text{ reading}) \pm 0.126m\Omega$ [19]). The minute average voltage drop from both modules was logged into a Campbell Scientific CR6 data logger with an

average sampling time of 5 seconds. A schematic diagram for module short-circuiting and SR calculation is represented in Figure 3.

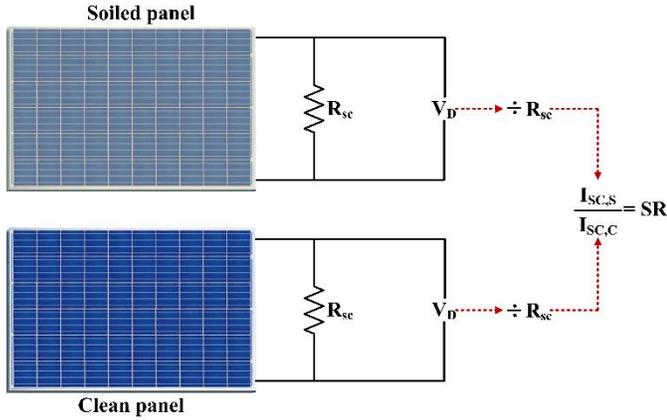


Fig. 3. Circuit diagram representing short-circuiting technique of clean and soiled modules. In the figure, R_{sc} is a low shunt resistor ($63m\Omega$) identical for both modules. Voltage drop (V_D) was converted into the I_{sc} by dividing it with the value of the shunt resistor (R_{sc}), then the SR was calculated using the obtained I_{sc} values.

Instantaneous irradiance was recorded every minute with the help of CMP-21 pyranometer by Kipp & Zonen installed at the plane of array (POA). Minutely average temperatures of soiled and cleaned modules were also measured using two temperatures sensors (negative temperature coefficient (NTC) Thermistor of $10k\Omega$) applied at the backside of each module. The experimental setup consisting of cleaned and artificially soiled module is presented in Figure 4.

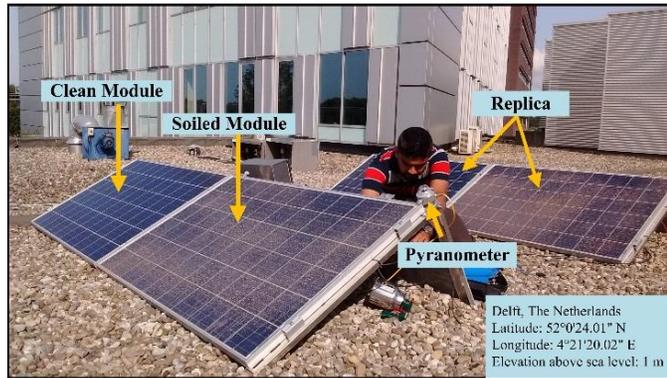


Fig. 4. Experimental setup for soiling ratio (SR) measurement represented by two co-planar modules in the front row, whereas the rear row represents duplicate set of modules to later validate the measured data. The experiment was conducted on 27th of August 2017 from 10:57 to 17:07. The voltage drop from the modules was recorded with the help of a CR6 data logger placed inside a metal box (at the back of the modules).

C. Soiling ratio (SR) calculation

Soiling ratio (SR) is defined as the ratio of irradiance utilized by a soiled (G_s) to cleaned module (G_c) to produce corresponding short-circuit current ($I_{sc,s}$ and $I_{sc,c}$) or power [20]. Using the translation method explained in IEC-60891, the measured short-circuit currents ($I_{sc,s'}$ and $I_{sc,c'}$) were subjected to temperature correction to account for net

irradiance loss only due to soiling (equation (1)). A temperature coefficient ($0.053 \text{ } \%/^{\circ}\text{C}$) mentioned in the datasheet of the PV module was considered for temperature correction [21]. The short circuit current of the two co-planar modules were normalized with the help of calibration factors when both modules were clean and at the reference temperature (25°C) condition. The duplicated modules were used for calibration to account for manufacturing defects, differences in cable resistance or any other abnormal behavior that might lead to varying current and power production at an identical condition. The expanded SR equation with calibration values and the translation method for temperature correction can be written as [20] [22].

$$SR = \frac{G_s}{G_c} = \frac{I_{sc,s}}{I_{sc,c}} = \frac{I_{sc,s'} (1 - \alpha (T_{m,s} - T_{ref}))}{I_{sc,c'} (1 - \alpha (T_{m,c} - T_{ref}))} \times \frac{C_c}{C_s} \quad (1)$$

$$t_{loss} = 1 - SR \quad (2)$$

In (1), $I_{sc,s'}$ and $I_{sc,c'}$ are measured short-circuit currents from soiled and cleaned module respectively, whereas $I_{sc,s}$ and $I_{sc,c}$ are short-circuit currents after temperature corrected. Similarly, α is the temperature coefficient, while C_c and C_s are calibration constants for cleaned and soiled module respectively, which were computed by comparing the short-circuit currents of both the modules. Similarly, $T_{m,s}$ and $T_{m,c}$ are the measured temperature of soiled and cleaned PV modules respectively, whereas T_{ref} is the temperature of the module when the ambient temperature is 25°C . t_{loss} in (2) is the transmission loss due to the presence of soiling. The following SR calculation was performed for three days characterized by their average irradiances (due to different levels of cloudiness) throughout that day; high irradiance (758 W/m^2), medium irradiance (559 W/m^2), and low irradiance (276 W/m^2). In this experiment, SR was calculated from short-circuit method however, it should be noted that SR could also be estimated by maximum power point method, which might give a slightly different result.

D. PV module angular losses

Angular losses (AL) for PV modules are generally calculated referencing a normal incidence of radiation at either cleaned or soiled condition [23]. The complement to the unity of angular losses (AL) is known as angular factor ($f_{I\alpha}$) [24]. Angular factor at any angle of incident (AOI) represents the relative optical response of a module for that angle. The experimental value of angular factor ($f_{I\alpha}$) (for an arbitrary AOI of θ) can be obtained as the ratio of cosine corrected short-circuit current at the angle θ ($I_{sc|\theta}$) to the short-circuit current at normal incidence ($I_{sc|\theta=0^{\circ}}$) represented as [24],

$$f_{I\alpha} = \frac{I_{sc}(\theta)}{I_{sc} |_{\theta=0^{\circ}} \cos \theta} \quad (3)$$

The optical response of any module with or without anti-reflective coatings can be determined with the help of an analytical equation presented below [24],

$$AL(\theta) = 1 - \frac{1 - \exp\left(\frac{-\cos\theta}{a_r}\right)}{1 - \exp\left(\frac{-1}{a_r}\right)} \quad (4)$$

$$IAM(\theta) = 1 - AL(\theta) \quad (5)$$

where a_r is a dimensionless parameter known as angular loss coefficient, which depends on a particular PV module technology or the front cover [24]. For every AOI of the Sun (θ) and a fixed a_r value, angular loss (AL) in a PV module is determined by equation (4). In [23], the analytical model (equation (4)) was found to accurately describe the angular losses of all analysed PV configurations with a high value of determination coefficients (R^2). Equation (5) represents the incident angle modifier (IAM), which is the complement for angular losses (AL) with a maximum of 1 and minimum of 0. It signifies the degree of module performance for any angle of incidence (AOI) of light with a maximum value when lowest AOI is 0 (Perpendicular light incidence). For our calculations, the generated short-circuit currents from each module were first scaled up by linear translation after module temperature correction to the same reference irradiance as it was during solar noon. Then, the angular factor (f_{ia}) in (3) was determined for different angles of incidence of the Sun and different levels of soiling. The calculated angular factors at each soiling level were further plugged into (4) to determine the angular loss factor (a_r) at an AOI of 5° , 10° , 15° , 20° , 25° and 30° . Finally, an average a_r value was again substituted in equation (4) and (5) to calculate the incident angle modifier of the module at every angle of incidence (AOI) from 0° to 90° .

III. RESULTS AND DISCUSSION

In this section, the results of the indoor and outdoor experiments have been discussed. First, the measured soiling ratio (SR) for two dust colors at different AOI of the artificial light source were plotted together. Next, the SR measured from outdoor setup was plotted for a course of a day. Then, the angular losses (AL) as a function of SR and AOI were calculated. Finally, using the empirical equation proposed in this paper, SR over the day has been determined and compared at three irradiance conditions.

A. Indoor soiling ratio (SR)

The measured short-circuit current at different AOI was temperature corrected to calculate the SR using equation (1). The soiling ratio (SR) measured at normal incidence ($\theta=0^\circ$) for the soil type of Prüf-staub (black) was 76.9%, whereas for Arizona Test Dust (light-brown) it was 87%. The higher light absorption nature of the black dust might be the reason behind larger transmission loss. Next, the attenuation of SR values at different AOI were compared. To do this, Arizona Test Dust

was deposited 1.72 times than previous ($\sim 0.005 \text{ g/cm}^2$) to reach the same SR value at normal incidence as it was given by Prüf-staub dust ($\sim 76.9\%$). The SR of Arizona Test Dust and Prüf-staub dust at each AOI is presented in Figure 5.

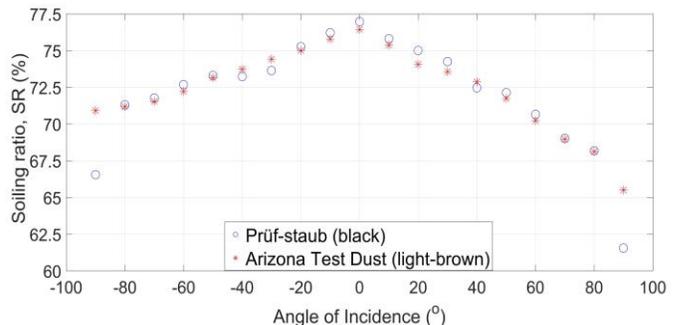


Fig. 5. The measured SR values for Prüf-staub dust and Arizona Test Dust for -90° to $+90^\circ$ AOI. At normal incidence ($\theta=0^\circ$), SR value for Prüf-staub represented by blue circles is 76.9%, whereas for Arizona Test Dust represented as red star was around 76.5%. This value for Arizona Test Dust was achieved by depositing additional amount of the dust and measuring the I_{sc} till the value was reached.

Apart from few outliers at larger AOI, no significant difference in SR value was noticed between Prüf-staub (black) and 1.72 times deposited Arizona Test Dust (light-brown) dust. The angular losses, and consequently SR, for two types of dusts were almost the same for every AOI. The results also suggest that, any dust color with the same SR for AOI=0 possess similar SR at all AOI. Therefore, angular losses and hence SR do not depend on the dust color but only on the amount of the dust (g/cm^2) deposited on the module. This result can be further validated from the work of [13], where the soiling loss pattern in two different modules at the same soil density or SR was found to be similar at every AOI of the light source.

B. Outdoor soiling ratio (SR)

The soiling ratios were measured for a shade free window of around 5.5 hours from 10:57 to 16:30 on each day to avoid partial shading on the PV modules caused by nearby objects. Figure 6 represents a high irradiance day, which showed that soiling ratio (SR) was not constant throughout the day but changed with the position of the Sun. SR was seen to be highest during mid of the day (± 1 hour from 13:45 (solar noon)) fluctuating between 86.5% and 87%. Therefore, the overall transmission loss in the soiled module was estimated to be around 13-13.5% using equation (2). During morning and the evening time, it reached the lowest value due to larger AOI of the Sun. At larger AOI, the dust on the module is believed to cast larger shadow resulting in higher losses compared to midday. SR was also seen to be varying by around $\pm 1\%$ even during the midday. This was probably because of the dynamic shading on the modules caused by passing clouds. Figure 6, 7 and 8 shows the result of SR measurements for high, medium and low irradiance conditions respectively.

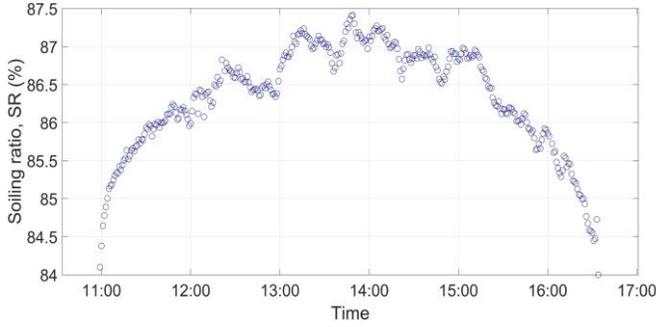


Fig. 6. The measured SR on 27th of August 2017 represents for a high irradiance day (758 W/m^2). SR during morning and evening period is significantly lower compared to the mid of the day. Solar noon on this day was noticed at 13:45 PM, which represents SR value of 86.9%.

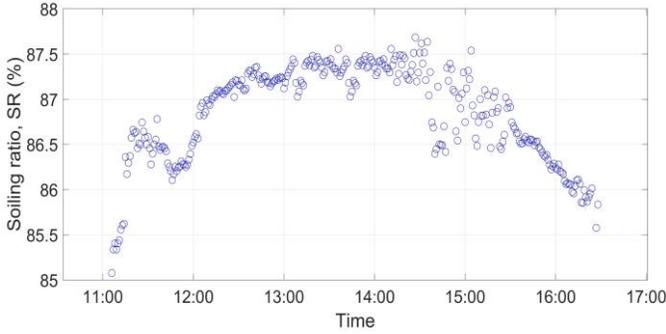


Fig. 7. The measured SR on 23rd of August 2017 represents for a medium irradiance day (559 W/m^2). The SR pattern is similar as in Figure 6 with some additional SR fluctuations. The value of SR at the solar noon was 87.5%, which is higher than for high irradiance day. This is probably due to additional deposition of the atmospheric dust in-between those four days (23rd to 24th August 2017), resulting into lower SR (higher losses).

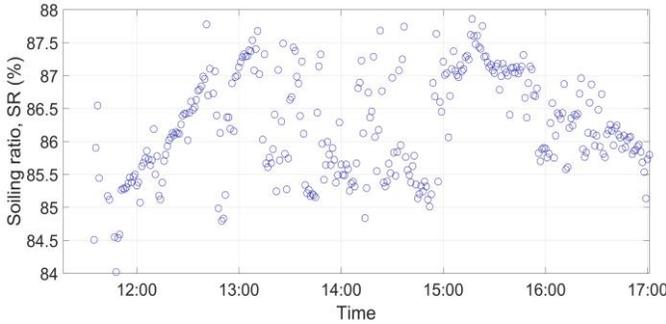


Fig. 8. The measured SR on 24th of August 2017 represents for a low irradiance day (276 W/m^2). The SR pattern cannot be clearly observed due to higher amount of SR fluctuations at cloudy condition. The value of SR at the solar noon was 86%.

This characteristics nature of a soiled module's dependency on AOI of the light can also be noticed from indoor soiling ratio experiment in Figure 5. For the larger AOI, SR values were smaller while it increased and reached the maximum as the light source was perpendicular to the module's surface. The result from both experiments confirm the presence of angular dependency of a soiled module over a day.

C. Angular losses (AL) on the module

The measured short-circuit currents of the clean and soiled module in the outdoor measurement setup were also used to determine the angular losses on the PV modules. To do so, every minute Sun's altitude was calculated with respect to the module's azimuth (182°) for each day. On the solar noon of 11th of July, the solar zenith angle (SZA) was observed to be 60° and the Sun's rays were exactly perpendicular with respect to the modules. The SZA on 27th of August was 68° , therefore modules were already suffering from angular losses even at mid of that day due to its fixed tilt. For our range of interest between 10:57 to 16:30, the light on the module was mainly due to the direct component of the solar irradiance with little influence of shading and diffuse solar irradiance. The angular factor (f_{α}) was calculated for three different soiling levels, clean (SR=100%), medium soiled (SR=93.2%) and heavy soiled (SR=86.9%). It was then used to calculate angular loss factor (a_r) at each case using equation (4). The graph shown in Figure 9 represents incident angle modifier (IAM) for the three soiling ratios.

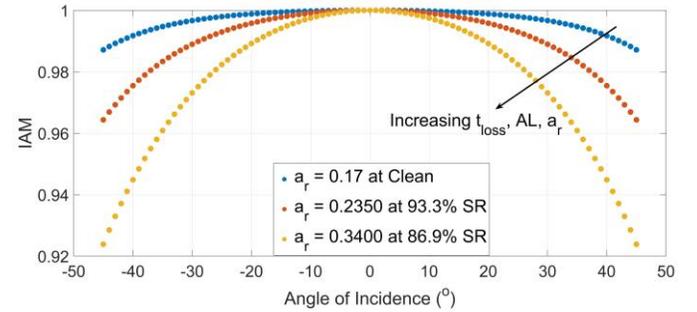


Fig. 9. Incident angle modifier (IAM) calculated for three module conditions namely, clean represented by blue curve, SR of 93.2% represented by red curve and SR of 86.9% represented by yellow curve. IAM was calculated from -45° to $+45^\circ$ at an interval of 1° based on the Sun's position on 27th of August 2017. The arrow points out the increasing pattern of the angular loss (AL) and angular loss coefficient (a_r) as a function of SR due to soiling. AOI in the graph represents different in Sun's altitude when maximum and at any time t on 27th August 2017.

Here, x-axis represents AOI of the Sun on the module, which is the difference between Sun's altitude at the mid of the day (when maximum) at any time. The angular loss coefficient (a_r) was found to be lowest for the cleaned module at 0.17 represented by the top-most blue curve while it increased and reached 0.34 at SR of 86.9%. The pattern of increasing a_r associates with the increase in angular losses with decreasing SR (increasing t_{loss}). A thorough comparison of a_r at increasing soiling loss (decreasing SR) has been presented in the Figure 10.

Comparing the IAM for the cleaned and the soiled modules at the same AOI helps to understand the detrimental effect of soiling on PV modules. The angular loss of a cleaned module for 30° was 0.0018 while for soiled module, the losses increased to 0.0164, i.e. 9.12 times larger. The IAM curve for the soiled and the cleaned modules was used to model SR pattern throughout the day in the next section.

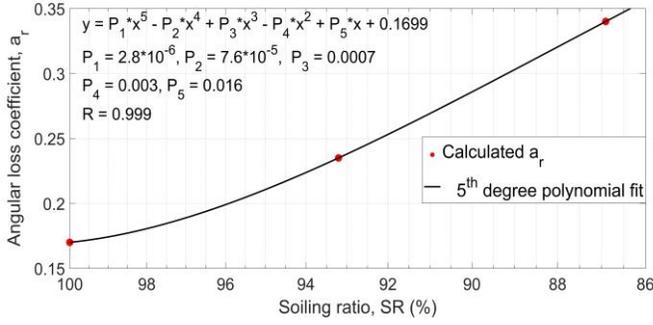


Fig. 10. The increasing trend of angular loss coefficient, a_r , with increasing soiling loss (decreasing SR) on the module. Three different soiling conditions were SR=100% representing clean condition, SR=93.2% and SR=86.9%. The data points are fitted to 5th order polynomial equation on MATLAB. The R coefficient represents the goodness of the fit. The coefficient for clean module is 0.17, which agrees from the experiment carried out by Martin and Ruiz [16].

D. Soiling ratio modeling based on angular losses

The soiling ratio (SR) over the course of the day as described in section III.B will be now modeled with the help of the calculated angular losses and the single midday SR value (SR_{midday}) of 86.9%. The ratio of IAM for the soiled and cleaned module at each AOI from figure 9 was multiplied by midday SR (86.9%) value using the following empirical equation (6).

$$SR^{model} = \frac{IAM_s(\theta)}{IAM_c(\theta)} \times SR_{midday} = IAM_{ratio}(\theta) \times SR_{midday} \quad (6)$$

where $IAM_s(\theta)$ and $IAM_c(\theta)$ are the incident angle modifier of the soiled (SR=86.9%) and the cleaned module. In equation (1), it can be seen that the soiling ratio (SR) is the ratio of the soiled and the cleaned module thus; the IAM_{ratio} in equation (6) has been presented as the ratio of IAM associated with the soiled module (IAM_s) to that of cleaned (IAM_c). After modeling SR (SR^{model}) for each AOI for 27th of August, the red curve shown in Figure 11 was resulted and plotted along with the measured SR values for comparison.

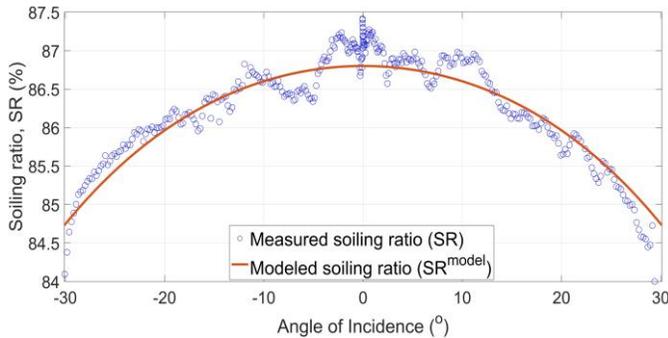


Fig . 11. A comparison of the measured SR values with the modeled values. The blue circles represent the measured SR values in figure 6, whereas the smooth red line is the modeled SR values obtained from empirical equation (6). Here, the x-axis represents the position of the Sun on 27th of August 2017. The two ends of the graph (-30° and +30°), signifies morning and evening times, respectively. AOI in the graph represents different in Sun's altitude when maximum and at any time t on 27th August 2017.

From a visual inspection, the modeled curve (blue) closely seems to follow the pattern of the measured curve (red). The modeled soiling ratio represented by the red curve is much smoother compared to the measured SR because the irradiance fluctuations were not considered in SR modeling. Again, for modeled values at larger solar angle, the module angular losses were also high. Both curves show the AOI dependency of a soiled module.

E. Deviation between measured and modeled SR

An error or residual calculation represents the average deviation of modeled value compared to an actual or observed value [25]. This estimation facilitates the quantification of the difference between experiment and model. To measure the accuracy of the proposed model (equation (6)), root mean square deviation (RMSD) will be calculated for each point of the modeled and the measured SR data [26]. For the high irradiance day, there were 334 data events representing each minute resulting in a mean squared error of 0.0458%. Thus, RMSD between the measured and the modelled data set was then found to be $\pm 0.21\%$. This means the proposed model predicted the measured with a variance of $\pm 0.21\%$. The error associated with medium and low irradiance situation were also estimated in the same way. A comparison for each irradiance conditions have been summarized in Table I.

TABLE I
RMSD DEVIATION AT THREE IRRADIANCES CONDITION

Date	Day type	Daily Avg. Irradiance (W/m ²)	RMSD (%)
27-08-2017	High irradiance	758	± 0.21
23-08-2017	Medium irradiance	559	± 0.28
24-082017	Low irradiance	276	± 1.04

The results indicate that for the low irradiance condition, the degree of deviation is higher, at around $\pm 1\%$. This was most likely due to a constant AOI of the diffuse irradiance from the clouds resulting in a larger amplitude of the deviation. However, during the day with an adequate amount of light, the residual errors were quite low at around $\pm 0.2\%$ and $\pm 0.28\%$. These results suggest that the model predicts the SR very well during sufficient irradiance condition while it is less accurate on cloudy days.

IV. CONCLUSION

The soiling ratio (SR) from the short circuit current method was chosen to determine the SR over the course of a day. The SR was found to be influenced by the AOI of the Sun. Morning and evening time corresponded to a higher degree of module angular losses than around solar noon. The angular dependency of SR of a soiled module was found to be independent of the dust color used for identical SR. An analytical model developed by Martin & Ruiz was followed to characterize the angular loss coefficient (a_r) at different SR

conditions and it was found to increase with the soiling level. The soiled and cleaned PV modules had angular loss coefficient (a_s) values of 0.34 and 0.17 respectively for a high irradiance day (average irradiance of 758 W/m²). It was also noticed that the presence of the dust on the module attenuated the IAM, therefore decreasing the transmittance of irradiance compared with the cleaned PV module. The proposed empirical equation based on the incident angle modifier (IAM) and a single midday SR measurement was found to have accurate prediction of $\pm 0.21\%$ for a sunny day, whereas the deviation was higher for cloudy conditions. The SR was found to be influenced due to the presence of the clouds, thus increasing the RMSD. The cloudy conditions result in light coming from a diffuse sky, resulting in a constant AOI over the day. This results in a less good fit of the model with the measured. No significant difference in the angular dependence of SR measured for two different dust colors shows the possible validity of the proposed empirical equation for any location irrespective of the local dust. This can be further investigated in the future researches.

ACKNOWLEDGEMENT

The authors gratefully acknowledge the helpful support of Kipp & Zonen Company and its staff. They would also like to thank Mr. Gijs Snijders and Mr. Sandeep Mishra for their effort in preparing the experimental test setup.

DISCLAIMER

Results presented in this work strictly concern the type of dust used and the testing condition. The results might differ based on the system's location and local environmental conditions.

REFERENCES

- [1] Fraunhofer Institute for Solar Energy Systems, "Photovoltaics report," *www.ise.fraunhofer.de*, pp. 1–44, 2018.
- [2] J. Sips-Williem, C. Lee, and R. Ringoir, "6 Key influences that determine PV performance ratios," *www.kippzonen.com*, pp. 1–11, 2017.
- [3] M. R. Maghami, H. Hizam, C. Gomes, M. A. Radzi, M. I. Rezadad, and S. Hajighorbani, "Power loss due to soiling on solar panel: A review," *Renew. Sustain. Energy Rev.*, vol. 59, pp. 1307–1316, 2016.
- [4] M. Gostein, J. R. Caron, and B. Littmann, "Measuring soiling losses at utility-scale PV power plants," *2014 IEEE 40th Photovolt. Spec. Conf. PVSC 2014*, pp. 885–890.
- [5] M. Mani and R. Pillai, "Impact of dust on solar photovoltaic (PV) performance: Research status, challenges and recommendations," *Renew. Sustain. Energy Rev.*, vol. 14, no. 9, pp. 3124–3131, 2010.
- [6] A. Sayyah, M. N. Horenstein, and M. K. Mazumder, "Energy yield loss caused by dust deposition on photovoltaic panels," *Sol. Energy*, vol. 107, no. March, pp. 576–604, 2014.
- [7] J. Zorrilla-Casanova *et al.*, "Analysis of dust losses in photovoltaic modules," *World Renew. Energy Congr. 2011 -- Sweden*, pp. 2985–2992, 2011.
- [8] A. Kimber, L. Mitchell, S. Nogradi, and H. Wenger, "The Effect of Soiling on Large Grid - Connected Photovoltaic Systems in California and the Southwest Region of the United States," *IEEE J. Photovoltaics*, pp. 2391–2395, 2006.
- [9] H. K. Elminir, A. E. Ghitass, R. H. Hamid, F. El-Hussainy, M. M. Beheary, and K. M. Abdel-Moneim, "Effect of dust on the transparent cover of solar collectors," *Energy Convers. Manag.*, vol. 47, no. 18–19, pp. 3192–3203, 2006.
- [10] R. Hammond, D. Srinivasan, A. Harris, K. Whitfield, and J. Wohlgenuth, "Effects of soiling on PV module and radiometer

- performance," *Conf. Rec. Twenty Sixth IEEE Photovolt. Spec. Conf. - 1997*, pp. 1121–1124, 1997.
- [11] J. J. John, "Characterization of Soiling Loss on Photovoltaic Modules , and Development of a Novel Cleaning System," *Indian Inst. Technol. Bombay*, p. 146, 2015.
- [12] H. Zhang, Y. Sun, L. Wu, X. Zhang, and Y. Xiang, "Tracking mechanism and cosine effect study of Module-Heliostat Solar Collector," *Proc. 2016 4th Int. Conf. Mach. Mater. Inf. Technol. Appl.*, vol. 71, no. January, pp. 469–474, 2016.
- [13] V. Rajasekar, S. Boppana, and G. Tamizhmani, "Angle of incidence effect on five soiled modules from five different PV technologies," *2015 IEEE 42nd Photovolt. Spec. Conf. PVSC 2015*, 2015.
- [14] A. Wilson and R. Ross, "ANGLE-OF-INCIDENCE EFFECTS ON MODULE POWER AND ENERGY PERFORMANCE iM," pp. 423–426.
- [15] J. John, V. Rajasekar, S. Boppana, and S. Tatapudi, "Angle of incidence effects on soiled PV modules," no. October 2014, 2018.
- [16] N. Martín, F. Chenlo, E. Mejuto, F. Soriano, S. Temprano, and M. C. Alonso-García, "Validating an angular of incidence losses model with different pv technologies and soiling conditions," *27th Eur. Photovolt. Sol. Energy Conf. Exhib.*, no. May 2014, pp. 3436–3438, 2012.
- [17] P. D. Burton and B. H. King, "Artificial soiling of photovoltaic module surfaces using traceable soil components," *Conf. Rec. IEEE Photovolt. Spec. Conf.*, pp. 1542–1545, 2013.
- [18] S. Bhaduri, S. Warade, J. J. John, and B. Kavaipatti, "Artificial Dust Deposition Using Water as Carrier Solvent for Investigation of Soiling Losses in Photovoltaic Modules," pp. 2076–2079, 2016.
- [19] Transcat, "Fluke 80 Series V Multimeters Users Manual," 2017.
- [20] International Electrotechnical commission (IEC):61724-1, "Photovoltaic system performance: Part 1- Monitoring," 2017.
- [21] Canadian Solar Inc., "Canadian Solar datasheet-CS6K-P-v5.531," *CS6K-260/265/270/275P datasheet*, 2017.
- [22] M. Gostein, B. Littmann, J. R. Caron, and L. Dunn, "Comparing PV power plant soiling measurements extracted from PV module irradiance and power measurements," *Conf. Rec. IEEE Photovolt. Spec. Conf.*, no. November, pp. 3004–3009, 2013.
- [23] N. Martín and J. M. Ruiz, "Annual angular reflection losses in PV modules," *Prog. Photovoltaics Res. Appl.*, vol. 13, no. 1, pp. 75–84, 2005.
- [24] N. Martín and J. M. Ruiz, "Calculation of the PV modules angular losses under field conditions by means of an analytical model," *Sol. Energy Mater. Sol. Cells*, vol. 70, no. 1, pp. 25–38, 2001.
- [25] Willmott, C.J., "Some comments on the evaluation of model performance", *Bulletin of the American Meteorological Society* vol. 63, no. 11, p. 1309-1313, 1982.
- [26] G. Piñeiro, S. Perelman, J. P. Guerschman, and J. M. Paruelo, "How to evaluate models: Observed vs. predicted or predicted vs. observed?," *Ecol. Modell.*, vol. 216, no. 3–4, pp. 316–322, 2008.



Pramod Nepal received the B.Tech degree from National Institute of Technology Warangal, Warangal, India in 2014 and M.Sc. degree in sustainable energy technology from Delft University of Technology, Delft, The Netherlands in 2018.

He is currently working as a Solar Designer including complete end to end system design, energy prediction, and performance analysis. During his MSc thesis, he majorly worked towards energy losses in PV module due to module soiling. This involved analyzing the physical and chemical nature of the dust samples, artificial soiling procedure, behavior of soiled module with time, and quantification of transmission and energy loss in PV modules.



Marc Korevaar works as a scientist in the research department at Kipp & Zonen. He attained his PhD in physics working with scintillation detectors at the Technical University Delft, and has 10 years of experience in (optical) detector physics. Since 2013, he has been working with Kipp & Zonen in Research & Development, Delft, where he is involved in

development of new detectors, their calibration, and radiometry. Kipp & Zonen is a leading manufacturer of measurement instruments for meteorology and solar energy.



Miro Zeman received the Ph.D. degree (cum laude) from the Slovak University of Technology, Bratislava, Slovakia, in 1989 for research on amorphous silicon. In 2009, he was appointed as a Full Professor with the Delft University of Technology, Delft, The Netherlands, where he leads the Photovoltaic Materials and Devices Group and is the Head of the Electrical Sustainable Energy Department. He is a leading expert

in light management, modeling, and development and application of novel materials and nanostructures in silicon-based solar cells.



Hesam Ziar received the Ph.D. degree in electrical engineering from University of Tehran, Tehran, Iran, in 2017 for probability-based research on PV modules and systems. Since then he has been a researcher in the Photovoltaic Materials and Devices Group, Delft University of Technology, Delft, The Netherlands. He has collaborated with several companies and research institutes within

consortiums and research projects in Europe and Middle-East. His research interest include photovoltaic systems and applications, renewable energy systems, power electronic converters, probability, and optical studies.



Olindo Isabella received the Ph.D. degree (cum laude) from the Delft University of Technology, Delft, The Netherlands, in 2013 for his research on light management in thin-film silicon solar cells. Between 2013 and 2017, he was an Assistant Professor with the Delft University of Technology in the Photovoltaic Materials and Devices Group. In October 2017, he was appointed as an Associate Professor in the same group, where he

supervises optoelectrical device modeling activities, novel concepts of light management, development of high-efficiency solar cells based on crystalline silicon and thin-film silicon technologies, and advanced power modeling for custom PV systems.