

Enhancing the ROS Sensitivity of a Responsive Supramolecular Hydrogel Using Peroxizyme Catalysis

Piergentili, Irene; Hilberath, Thomas; Klemm, Benjamin; Hollmann, Frank; Eelkema, Rienk

DOI

[10.1021/acs.biomac.3c00262](https://doi.org/10.1021/acs.biomac.3c00262)

Publication date

2023

Document Version

Final published version

Published in

Biomacromolecules

Citation (APA)

Piergentili, I., Hilberath, T., Klemm, B., Hollmann, F., & Eelkema, R. (2023). Enhancing the ROS Sensitivity of a Responsive Supramolecular Hydrogel Using Peroxizyme Catalysis. *Biomacromolecules*, 24(7), 3184-3192. <https://doi.org/10.1021/acs.biomac.3c00262>

Important note

To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.

Enhancing the ROS Sensitivity of a Responsive Supramolecular Hydrogel Using Peroxizyme Catalysis

Irene Piergentili, Thomas Hilberath, Benjamin Klemm, Frank Hollmann, and Rienk Eelkema*



Cite This: *Biomacromolecules* 2023, 24, 3184–3192



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: Hydrogels that can disintegrate upon exposure to reactive oxygen species (ROS) have the potential for targeted drug delivery to tumor cells. In this study, we developed a diphenylalanine (FF) derivative with a thioether phenyl moiety attached to the N-terminus that can form supramolecular hydrogels at neutral and mildly acidic pH. The thioether can be oxidized by ROS to the corresponding sulfoxide, which makes the gelator hydrolytically labile. The resulting oxidation and hydrolysis products alter the polarity of the gelator, leading to disassembly of the gel fibers. To enhance ROS sensitivity, we incorporated peroxizymes in the gels, namely, chloroperoxidase CVCPO and the unspecific peroxygenase rAaeUPO. Both enzymes accelerated the oxidation process, enabling the hydrogels to collapse with 10 times lower H_2O_2 concentrations than those required for enzyme-free hydrogel collapse. These ROS-responsive hydrogels could pave the way toward optimized platforms for targeted drug delivery in the tumor microenvironment.

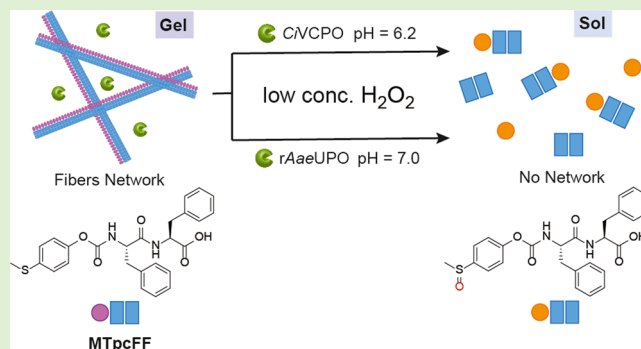

INTRODUCTION


Hydrogels made by self-assembly of small molecules have been drawing attention for over two decades due to the perspective of using these soft materials for applications ranging from drug delivery to tissue engineering.^{1,2} The initial fascination over serendipitously discovered gels was soon replaced by the need to understand the forces that drive gel formation in a way to design a priori molecules that are able to gelate.^{3,4} Considering the pool of self-assembled structures in biological systems,⁵ nature was once again where researchers found inspiration. The first example of peptide-based low-molecular-weight gelator (LMWG), reported in 1995, was used to realize a thermoreversible gel as a carrier for antigen delivery and presentation.⁶ Then, the recognition of diphenylalanine (FF) as a basic structure able to form ordered nanostructures⁷ led to the derivatization of this sequence to obtain a large variety of novel hydrogelators.^{8–11} The biocompatibility, the possibility of bottom-up fabrication, and easy chemical modification made diphenylalanine the natural choice as a short peptide sequence for biomedical materials.^{12–14} Subsequently, this versatile building block was functionalized with groups sensitive to various stimuli such as pH,^{15,16} enzymes,^{17,18} ultraviolet (UV) light,^{19,20} and redox change²¹ to realize responsive hydrogels. Reactive oxygen species (ROS) overproduction is typical in many tumor and diseased cells, causing a redox imbalance in the microenvironment. Ikeda and co-workers prepared FF-type peptides with a boronoaryl group, which fragments in the presence of hydrogen peroxide (H_2O_2), one of the most used ROS.²²

Besides the boronates, sulfides are commonly used oxidation-sensitive groups for stimuli-triggered nanomedicine.^{23,24} In the aqueous medium, the oxidation of a sulfide into sulfoxide or sulfone produces a switch in solubility that can be used to destabilize self-assembled structures bearing these moieties.²⁵ The solubility switch from thioether to sulfoxide to trigger the gel–sol transition of hydrogels is not unprecedented,^{26–28} but to the best of our knowledge, it has not been used for short peptide-based gelators.^{29,30} Recently, we developed a thioether phenyl ester-based cascade mechanism in which the oxidation to sulfoxide induces the hydrolysis of the ester.³¹ We functionalized diphenylalanine with the thioether phenyl moiety, aiming to realize a hydrogelator able to respond to H_2O_2 through a logic gate mechanism that enables the gel to disrupt. Thus, we synthesized MTpcFF (Figure 1), an aromatic amphiphile able to form a self-assembled network in an aqueous environment at both pH values 6.2 and 7.0, which are favorable conditions for biological applications. Moreover, once demonstrated the responsiveness toward H_2O_2 , we included two different H_2O_2 -dependent enzymes, namely, the vanadium-dependent chloroperoxidase

Received: March 14, 2023

Revised: May 1, 2023

Published: June 23, 2023



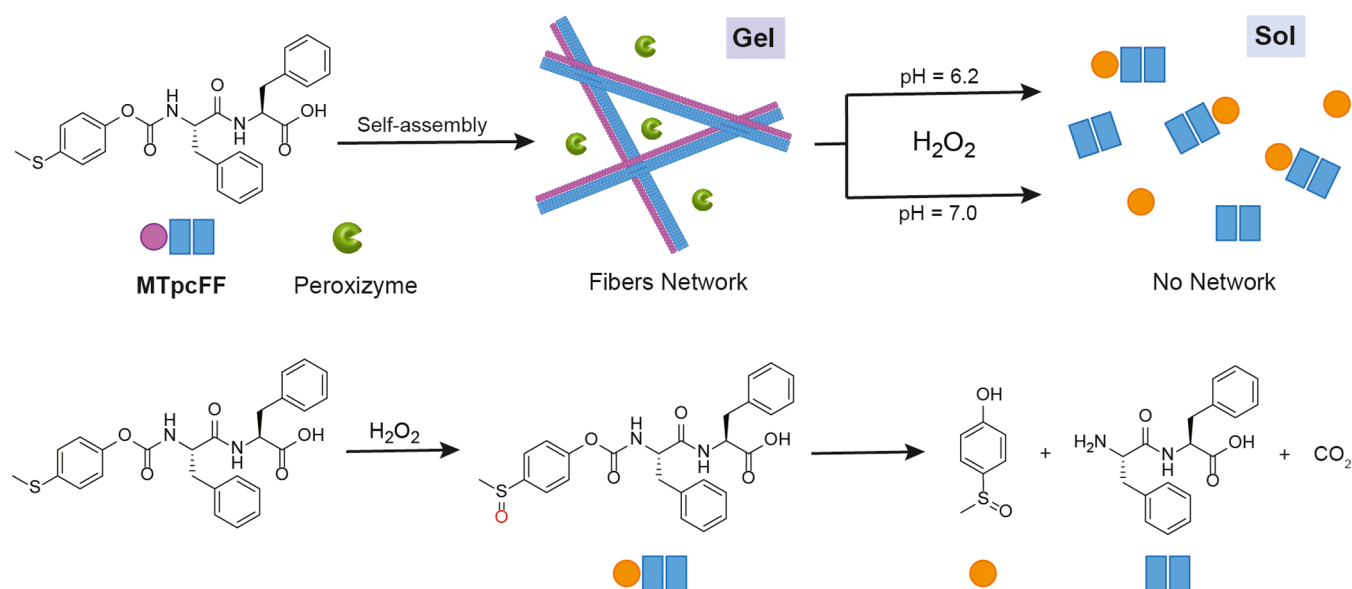


Figure 1. Schematic representation of the MTpcFF self-assembly with peroxizymes showing the formation of a nanofiber network (gel) and H₂O₂-triggered gel–sol transition. Peroxizymes: gels with CiVCPO are prepared in citrate buffer at pH = 6.2, and gels with rAaeUPO are prepared in phosphate buffer at pH = 7.0.

from *Curvularia inaequalis* (CiVCPO) and the unspecific peroxygenase from *Agrocybe aegerita* (rAaeUPO, PaDaI mutant) in the hydrogel. Chloroperoxidases are enzymes that catalyze the formation of hypohalites from H₂O₂ and halides. Despite their lower oxidation potential compared to H₂O₂ (1.78 V), hypohalites such as HOCl (1.49 V) and HOBr (1.34 V) are known to increase the rate of sulfide oxidation.^{32–34} Among the chloroperoxidases used for oxidation of thioanisole-type moieties, we chose CiVCPO for its robustness and high catalytic activity even in the presence of an organic solvent.^{35–38} The production of HOCl is optimal at pH below 7;³⁹ therefore, this system is suitable for mildly acidic conditions, which are often present in tumor tissues.⁴⁰ In the MTpcFF gel, we also incorporated rAaeUPO, which can catalyze the oxidation of aromatic sulfides with H₂O₂ at neutral pH^{41,42} and it is known to have an enzymatic activity in water with a cosolvent and even in a pure organic solvent.^{43,44}

Despite the different mechanisms of the two peroxizymes, we found that their influence over the gel–sol transition of MTpcFF hydrogels upon the addition of H₂O₂ is comparable. This establishes a versatile strategy that allows us to obtain ROS-responsive hydrogels in both mildly acidic and neutral conditions.

EXPERIMENTAL SECTION

Materials. Diphenylalanine (FF) and triphenyl alanine (FFF) were purchased from Sigma-Aldrich. 4-(Methylthio)phenol and 4-(methylsulfonfyl)phenol were purchased from Sigma-Aldrich and TCI, respectively.

Preparation of CiVCPO. The vanadium-dependent chloroperoxidase from *C. inaequalis* CiVCPO was produced in recombinant *Escherichia coli* TOP10 pBADgIIIIB VCPO following previously described procedures.⁴⁵ CiVCPO was purified via heat treatment according to a recently reported protocol.⁴⁶

Preparation of rAaeUPO. The expression-engineered variant of the recombinant unspecific peroxygenase from *A. aegerita* (rAaeUPO, PaDaI mutant) was used as a concentrated supernatant derived from a 2500 L pilot-scale cultivation of recombinant *Pichia pastoris* X-33.^{47,48}

Synthesis of 4-(Methylthio)phenyl 4-Nitrophenyl Carbamate. 4-Nitrophenyl chloroformate (0.97 g, 4.80 mmol) and 4-

(methylthio)phenol (0.56 g, 4.00 mmol) were dissolved in 30 mL of dichloromethane, and the solution was cooled to 0 °C in an ice bath. Triethylamine (0.67 mL, 4.80 mmol) was added dropwise; the mixture was allowed to warm to room temperature and stirred for 4 h. TLC analysis (silica; eluant: dichloromethane) indicated that no 4-(methylthio)phenol remained. The reaction mixture was washed with water (2 × 25 mL) and brine (25 mL). The organic layer was dried over Na₂SO₄, filtered, and the solvent was removed by rotatory evaporation. Recrystallization from toluene (160 mL) gave the pure product (0.92 g, yield 77%) as a yellow solid. ¹H NMR (400 MHz, CDCl₃) δ = 8.32 (d, *J* = 9.2 Hz, 2H), 7.48 (d, *J* = 9.2 Hz, 2H), 7.31 (d, *J* = 8.8 Hz, 2H), 7.21 (d, *J* = 8.8 Hz, 2H), 2.50 (s, 3H). ¹³C NMR (101 MHz, CDCl₃) δ = 155.39, 151.18, 148.42, 145.78, 137.24, 127.98, 125.56, 121.86, 121.32, 16.38. Spectroscopic data aligned with those reported in the literature.⁴⁹

Synthesis of 2-(((4-(Methylthio)phenoxy)carbonyl)amino)ethane-1-sulfonic Acid (1). To a solution of 4-(methylthio)phenyl 4-nitrophenyl carbonate (0.15 g, 0.50 mmol) in THF (2.0 mL) was added dropwise taurine (0.09 g, 0.75 mmol) and DIPEA (0.13 mL, 0.75 mmol) in distilled water (2.0 mL) at 0 °C. The reaction mixture was allowed to warm at room temperature and stirred overnight.^{50,51} After the removal of THF by rotatory evaporation, the mixture was extracted with ethyl acetate to remove the excess of *p*-nitrophenol. The aqueous layer was freeze-dried overnight. The crude was dissolved in acetonitrile, allowing the precipitation of the free taurine as a white solid. After filtration through syringe filters (45 μm), the acetonitrile was evaporated in vacuo. The mixture was dissolved in BuOH and further purified by flash chromatography over silica gel (CH₃COOH/H₂O/BuOH 5:5:90) to remove the excess of DIPEA. Compound 1 was obtained (0.07 g, yield 48%) as a slightly yellow solid. ¹H NMR (400 MHz, CD₃OD) δ = 7.29 (d, *J* = 8.6 Hz, 2H), 7.07 (d, *J* = 8.6 Hz, 2H), 3.62 (t, *J* = 6.9 Hz, 2H), 3.06 (t, *J* = 6.9 Hz, 2H), 2.48 (s, 3H). ¹³C NMR (101 MHz, CD₃OD) δ = 156.8, 150.4, 136.6, 129.0, 123.4, 51.7, 38.3, 16.5. Liquid chromatography-mass spectrometry (LC-MS) (electrospray ionisation (ESI)) calcd for C₁₀H₁₂NO₅S[−] [M − H][−]: 290.02, found: 290.04.

Synthesis of MTpcFF. To a solution of 4-(methylthio)phenyl 4-nitrophenyl carbonate (0.26 g, 0.85 mmol) in THF (16.0 mL) were added dropwise FF (0.40 g, 1.28 mmol) and DIPEA (0.22 mL, 1.28 mmol) in distilled water (4.0 mL) at 0 °C. The reaction mixture was allowed to warm at room temperature and stirred overnight.^{22,50} TLC analysis confirmed that no 4-(methylthio)phenyl 4-nitrophenyl carbonate remained. After the removal of THF through rotatory

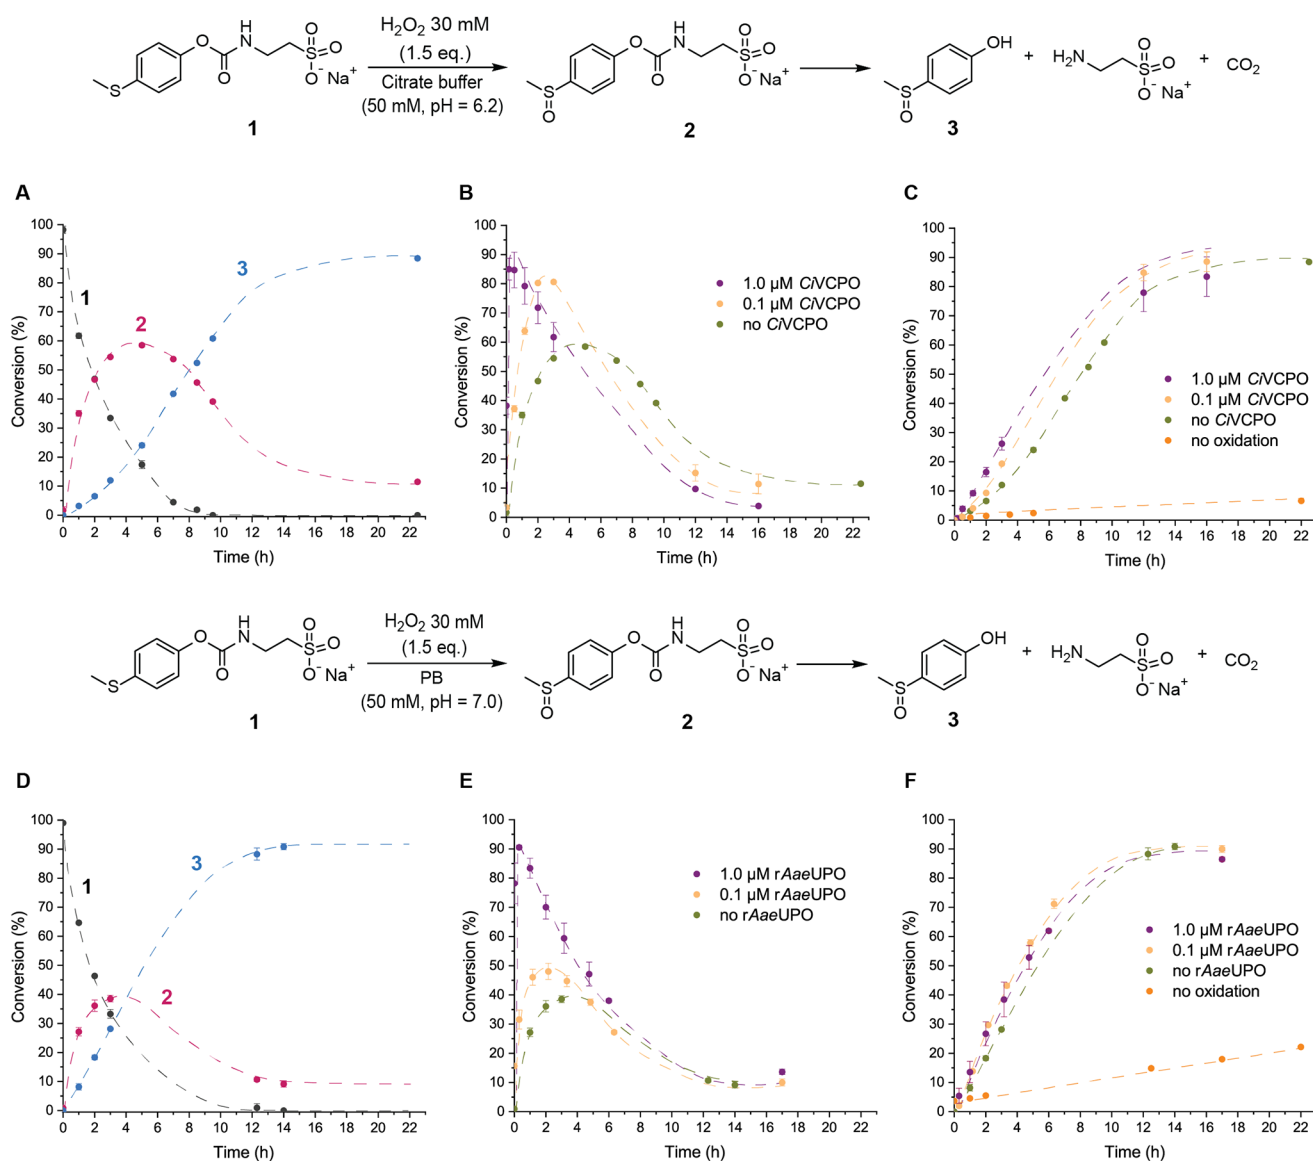


Figure 2. Scheme illustrating the species formed from compound **1** after the addition of H_2O_2 at 37°C . (A) Conversion profile without enzyme in citrate buffer. (B) Conversion profile of **2** after the addition of H_2O_2 in the presence of 0.0, 0.1, and $1.0\ \mu\text{M}$ CiVCPO. (C) Conversion profile of **3** without H_2O_2 in citrate buffer (orange line, the conversion refers to 4-(methylthio)phenol) and after the addition of H_2O_2 in the presence of 0.0, 0.1, and $1.0\ \mu\text{M}$ CiVCPO. (D) Conversion profile without enzyme in phosphate buffer. (E) Conversion profile of **2** after the addition of H_2O_2 in the presence of 0.0, 0.1, and $1.0\ \mu\text{M}$ rAaeUPO. (F) Conversion profile of **3** in the absence of H_2O_2 in phosphate buffer (orange line, the conversion refers to 4-(methylthio)phenol) and after the addition of H_2O_2 in the presence of 0.0, 0.1, and $1.0\ \mu\text{M}$ rAaeUPO. The dashed lines are drawn as a guide for the eye.

evaporation, the aqueous mixture was acidified ($\text{pH} = 2\text{--}3$) with a 5% citric acid solution. The reaction mixture was extracted with ethyl acetate ($3 \times 40\ \text{mL}$), and the combined organic layer was washed with water. The organic layer was dried over Na_2SO_4 and filtered. The filtrate was concentrated and precipitated in hexane twice to provide **MTpcFF** (0.34 g, yield 84%) as a slightly yellow solid. ^1H NMR (400 MHz, CD_3CN) $\delta = 7.32\text{--}7.22$ (m, 12H), 7.01 (d, $J = 7.8\ \text{Hz}$, 1H), 6.89 (d, $J = 8.5\ \text{Hz}$, 2H), 6.20 (d, $J = 8.4\ \text{Hz}$, 1H), 4.70–4.60 (m, 1H), 4.38–4.29 (m, 1H), 3.23–3.10 (m, 2H), 3.06–2.95 (m, 1H), 2.89–2.77 (m, 1H), 2.46 (s, 3H). ^{13}C NMR (101 MHz, CD_3CN) $\delta = 172.7, 171.8, 155.2, 149.7, 138.2, 137.8, 130.3, 129.4, 129.3, 128.3, 127.8, 127.7, 123.2, 57.2, 54.4, 38.5, 37.8, 16.3$. LC-MS (ESI) calcd for $\text{C}_{26}\text{H}_{26}\text{N}_2\text{O}_5\text{S}$ [$\text{M} + \text{H}$] $^+$: 479.16, found 479.13.

MTpcFF Hydrogel Preparation. The CiVCPO/MTpcFF gels were prepared by dissolving 0.75 mg of **MTpcFF** in $5.0\ \mu\text{L}$ of DMSO in a 1.5 mL screwed vial; then $93.5\ \mu\text{L}$ of citrate buffer (CB, 50 mM,

$\text{pH} = 6.2$) and $1.5\ \mu\text{L}$ of the $65.0\ \mu\text{M}$ CiVCPO stock solution in tris/ H_2SO_4 buffer (50 mM, $\text{pH} 8.2$) were added. For enzyme-free gels, $1.5\ \mu\text{L}$ of citrate buffer was added instead of the enzyme stock solution. The rAaeUPO/MTpcFF gels were prepared by dissolving 1.0 mg of **MTpcFF** in $5.0\ \mu\text{L}$ of DMSO in a 1.5 mL screwed vial; then, $93.8\ \mu\text{L}$ of phosphate buffer (PB, 50 mM, $\text{pH} = 7.0$) and $1.2\ \mu\text{L}$ of the $83.9\ \mu\text{M}$ rAaeUPO stock solution were added to the potassium phosphate buffer (20 mM, $\text{pH} 7.0$). For enzyme-free gels, $1.2\ \mu\text{L}$ of phosphate buffer was added instead of the enzyme stock solution. Each vial was stirred by vortexing for 3 s, capped, placed on a stable surface, and left undisturbed overnight. The gelation was evaluated by turning the vial upside down.

Rheology of MTpcFF Hydrogels. Oscillatory experiments were performed using a rheometer AR G2 from TA Instruments in a strain-controlled mode. The rheometer was equipped with a steel plate and plate geometry of diameter 25 mm and a water trap. The temperature

of the plates was controlled at 25 ± 0.2 °C. The gel mixtures were prepared as reported above, obtaining a total volume for each gelation experiment of 0.1 mL. After stirring the vial by vortexing for 3 s, the gel was pipetted on the bottom plate of the rheometer and the upper plate was slowly rotated to equally spread the gel. The storage and loss moduli G' and G'' were followed over time with the rheometer during the formation of the gel, setting up the instrument with a frequency of 1.0 Hz and under 1.0% strain. The measurements were stopped when no further increase of G' was observed. A frequency sweep was measured in the range of 0.01–100 rad/s, confirming that the moduli are constant in the frequency range chosen and the strain sweep revealed that the applied strain percentage is in the linear strain regime. G' was greater than G'' , and both G' and G'' were frequency-independent, which indicated the typical viscoelastic behavior of a hydrogel consisting of fiber networks. The rheological properties of MTpcFF gels were not significantly influenced by the presence of the enzymes CiVCPO and rAaeUPO.

H₂O₂ Response of MTpcFF Hydrogels with and without Peroxizymes (Tube Inversion). To the MTpcFF gels prepared in CB as described above, 5.0 μ L of NaCl 3.00 M was placed on top of the gels. Then, 5.0 μ L of 312, 156, 78.0, or 31.0 mM H₂O₂ stock solution was added to provide, respectively, 1.0, 0.5, 0.25, or 0.1 equiv of H₂O₂ to the gels. To the MTpcFF gels prepared in PB as described above, 10.0 μ L of 200, 100, 50.0, or 20.0 mM H₂O₂ stock solution was added on top of the gels to provide, respectively, 1.0, 0.5, 0.25, or 0.1 equiv of H₂O₂. Control experiments were performed by adding 10.0 μ L of the corresponding buffer instead of H₂O₂ stock solution. All of the experiments were performed at 37 °C. The gel–sol transition was then visually evaluated according to the tube-inversion method over time. Photographs were acquired at different stages of the gel–sol transition. The hydrogels resulted in being stable in the absence of H₂O₂ over 24 h but suffered water loss due to the prolonged time at 37 °C. To maintain the concentrations of the gels constant, control experiments were stopped at 8 h.

RESULTS AND DISCUSSION

Oxidation and Hydrolysis Study on a Soluble Model Compound. In the previous work, we demonstrated the hydrolytic lability of the 4-(methylthio)phenyl ester when the thioether moiety is oxidized to the corresponding sulfoxide.³¹ Here, we synthesized the taurine derivative **1** to study the oxidation process of the thioanisole moiety and whether sulfoxidation triggers carbamate hydrolysis. This model compound was also used to determine the ideal concentration of enzymes to accelerate the oxidation of the thioether unit. To avoid the inactivation of CiVCPO in the presence of inorganic phosphate, we performed all experiments with this chloroperoxidase in citrate buffer (CB, 50 mM, pH = 6.2, 140 mM NaCl). First, we followed product formation from 20 mM **1** in CB upon the addition of 1.5 equiv of H₂O₂ in the absence of enzyme (Figure 2A) at 37 °C.

After the first hour, the appearance of low field peaks in ¹H NMR revealed the formation of sulfoxide **2** and the 4-(methylsulfinyl)phenol **3** (Figure S1). At 3 h, the conversion to **2** and **3** was 55 and 12%, respectively, and 33% of **1** was still present. Compound **1** was completely consumed after 8 h, but the amount of **2** dropped to 45%, while **3** increased to 52%. Sulfoxide **2** is an intermediate that hydrolyzes over time to form **3** and free taurine, demonstrating the hydrolysis of the carbamate moiety in these conditions. It took 16 h to reach more than 80% conversion to phenol **3**, indicating that the hydrolysis rate from **2** to **3** is lower than the rate of oxidation of **1** to **2**. Considering the difficulties in enhancing the rate of hydrolysis, we focused on the catalysis of the oxidation step. Therefore, we tested CiVCPO in concentrations of 0.1 and 1.0 μ M to seek for the optimal oxidation conditions of **1**. In the

presence of 0.1 μ M of CiVCPO, compound **1** converted into 80% of **2** in 2 h after the addition of H₂O₂ (Figure 2B, yellow line). With 1.0 μ M of CiVCPO, 85% of **2** was produced in 10 min (Figure 2B, purple line). This result demonstrates that the chloroperoxidase accelerates the oxidation of **1** more than two times for 0.1 μ M and about 30 times for 1.0 μ M enzyme. In addition, at 3 h, the conversion of **3** was 19% for 0.1 μ M of CiVCPO and 26% for 1.0 μ M of CiVCPO against 12% for the enzyme-free sample (Figure 2C). However, for the samples with the chloroperoxidases, the formation of **3** was about 80% after 12 h. This indicates that the hydrolysis rate is influenced by the concentration of **2**, but this effect fades with the consumption of the sulfoxide and the oxidant, translating into a minor difference in the kinetic profile toward the end of the reaction.

Aiming to investigate the reaction in neutral conditions, we decided to follow the oxidation and hydrolysis of **1** with 1.5 equiv of H₂O₂ in phosphate buffer (PB, 50 mM) at pH = 7.0. In Figure 2D, we show the conversion of **1** and its products in PB in the absence of enzyme. At 3 h, the production of **2** and **3** was, respectively, 39 and 28%, with 33% of **1** remaining. At the same time point, **1** was consumed equally whether in phosphate or in citrate buffer, but the higher concentration of **3** in PB indicates that the hydrolysis is indeed faster than in CB. Due to the incompatibility of CiVCPO and phosphate buffer, we employed rAaeUPO as a peroxizyme to catalyze the oxidation of **1** for these conditions. Similar to CiVCPO, we used 0.1 and 1.0 μ M of rAaeUPO to accelerate the oxidation of **1** with H₂O₂. Compound **2** reached 90% in only 10 min with 1.0 μ M of rAaeUPO and 48% in 2 h with 0.1 μ M of rAaeUPO (Figure 2E). The hydrolysis profile of **2** to **3** (Figure 2F) was similar in all cases, reaching about 90% in 12 h. The use of 0.1 μ M of rAaeUPO barely accelerated the oxidation of **1** compared to the uncatalyzed case. In the presence of 1.0 μ M of rAaeUPO, we have an almost immediate full conversion to **2**, similar to the use of the same concentration of CiVCPO. Finally, at 12 h, the hydrolysis rate reached 90% in PB against 80% in CB. Additionally, after 12 h in the absence of oxidant, 14% of 4-(methylthio)phenol had formed in PB (orange line, Figure 2F) against about 5% in CB (orange line, Figure 2C), confirming the former condition as more advantageous for hydrolytic degradation. Considering the comparable efficiency of both CiVCPO and rAaeUPO at a concentration of 1.0 μ M in the H₂O₂-driven oxidation of the thioether moiety and the balance between responsiveness and stability of the non-oxidized substrate, we chose to explore these conditions at the material level in both PB and CB with the corresponding 1.0 μ M enzyme.

Properties of MTpcFF Hydrogels. Short peptide-based amphiphiles have great potential to form gels encapsulating large amounts of water.^{52,53} Considering its promising gelation properties,⁵⁴ we chose FF as a peptide building block and functionalized its N-terminus with the 4-(methylthio)phenyl moiety to obtain MTpcFF. Using the tube-inversion method, we found that this dipeptide derivative has a critical gel concentration (CGC) of 0.70 wt % in CB (Figure S5) and 0.95 wt % in PB (Figure S6).

Knowing that tripeptide-based hydrogelators have generally lower CGC, we also synthesized MTpcFFF. However, in the tube-inversion tests, the gelation of this derived tripeptide was often difficult to achieve and replicate. We indeed noticed poor solubility in aqueous solution even at a concentration of 0.1 wt %, and without the possibility of heating to avoid the

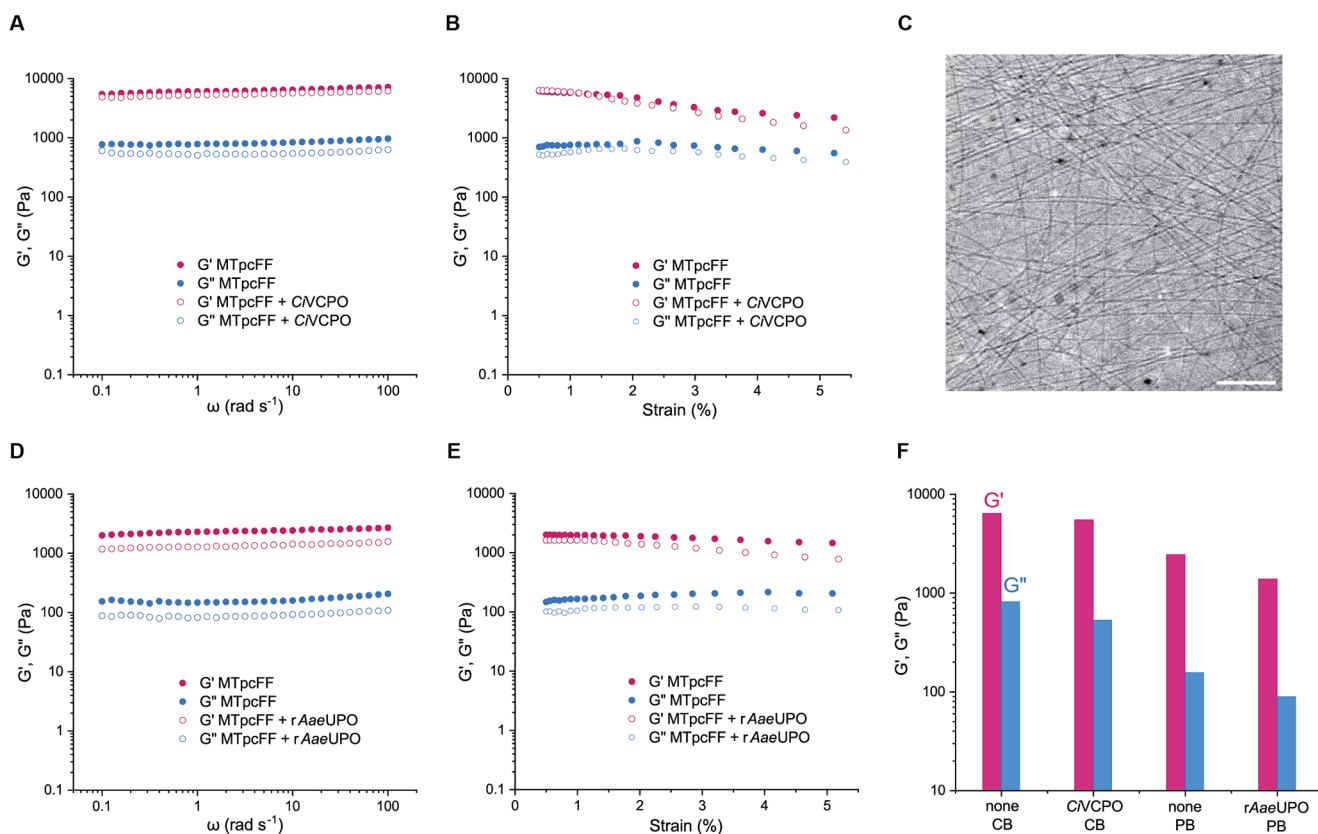


Figure 3. Properties of MTpcFF gels. (A) Frequency sweep and (B) strain sweep rheological properties of MTpcFF with (open circles) and without (filled circles) CiVCPO in citrate buffer. (C) Cryo-EM image of MTpcFF (1.0 wt %) hydrogel in PB (scale bar = 200 nm). (D) Frequency sweep and (E) strain sweep rheological properties of MTpcFF with (open circles) and without (filled circles) rAaeUPO in phosphate buffer. (F) Rheological properties of MTpcFF gels at an angular frequency of 1.0 Hz.

premature hydrolysis of the carbamate motif, we decided to continue our studies exclusively on MTpcFF.

First, we investigated the rheological properties of MTpcFF at 0.75 wt % in CB and at 1.0 wt % in PB. Interestingly, despite the higher concentration of the hydrogelator in PB, the storage modulus (G') is 2.5 kPa and the loss modulus (G'') is 0.2 kPa for MTpcFF in PB against 6.4 (G') and 0.8 (G'') kPa for MTpcFF in CB (Figure 3).

This result is not surprising if we consider the influence that pH and Hofmeister effect have over the gelation of other phenylalanine-based LMWG.^{55–60} Lower pH leads to a higher degree of protonation of the terminal carboxylic acid of the dipeptide amphiphile, making the functionalized FF more hydrophobic and therefore favoring the gelation in aqueous solution. Nevertheless, obtaining G' values always higher than the G'' means that both conditions produced gels with viscoelastic properties typical of fiber networks.⁶¹ Observation of the hydrogels with optical microscopy (Figure S3) and cryo-EM images (Figures 3C and S4) confirmed the presence of nanofibers that can aggregate in bundles with microscopic diameters. Analysis of cryo-EM images showed average fiber diameters of 7.9 ± 2.0 (citrate buffer, Figure S4C) and 4.0 ± 0.7 nm (phosphate buffer, Figure S4F) for the MTpcFF hydrogels.

Additives and impurities can affect the gelation of LMWG. Thus, to exclude that the encapsulation of CiVCPO and rAaeUPO influences the mechanical properties of MTpcFF gels, we performed additional rheological analysis on the enzyme-loaded hydrogels. The resulting data confirmed that

adding 1.0 μM of CiVCPO to 0.75 wt % of MTpcFF in CB and 1.0 μM of rAaeUPO to 1.0 wt % of MTpcFF in PB produced G' and G'' values that are only slightly lower than the corresponding gels without peroxizymes (Figure 3F). We also performed strain amplitude measurements within the linear viscoelastic region for all four different conditions. MTpcFF gels in CB both with and without CiVCPO showed a slight drop in G' and G'' values at 3% strain. In contrast, despite their lower storage and loss moduli, MTpcFF gels in PB demonstrated good stability even at 5% strain. Knowing these minor differences in the mechanical properties of MTpcFF hydrogel in different conditions, we pursued to investigate their response to H_2O_2 .

H_2O_2 -Responsive Gel–Sol Transition of MTpcFF Hydrogels. To test the sensitivity of MTpcFF gels toward oxidation, we followed the gel–sol transition in time after the addition of H_2O_2 via the tube-inversion method. MTpcFF hydrogels (0.75 wt %, 16 mM) were prepared in CB with and without CiVCPO (1.0 μM) and visually followed after the addition of varying equivalents of H_2O_2 (Figure 4A).

The peroxizyme-free gels turned into solution 5 h after the addition of 1.0 equiv of H_2O_2 , while CiVCPO-loaded MTpcFF hydrogels became solutions within 30 min in the presence of an equimolar amount of hydrogen peroxide (Figure 4A). The hydrogels with CiVCPO fully disrupted in 1 and 3 h with 0.5 and 0.25 equiv of H_2O_2 , respectively. Meanwhile, the CiVCPO-loaded control gels, where the oxidant was not added, remained intact for over 8 h.

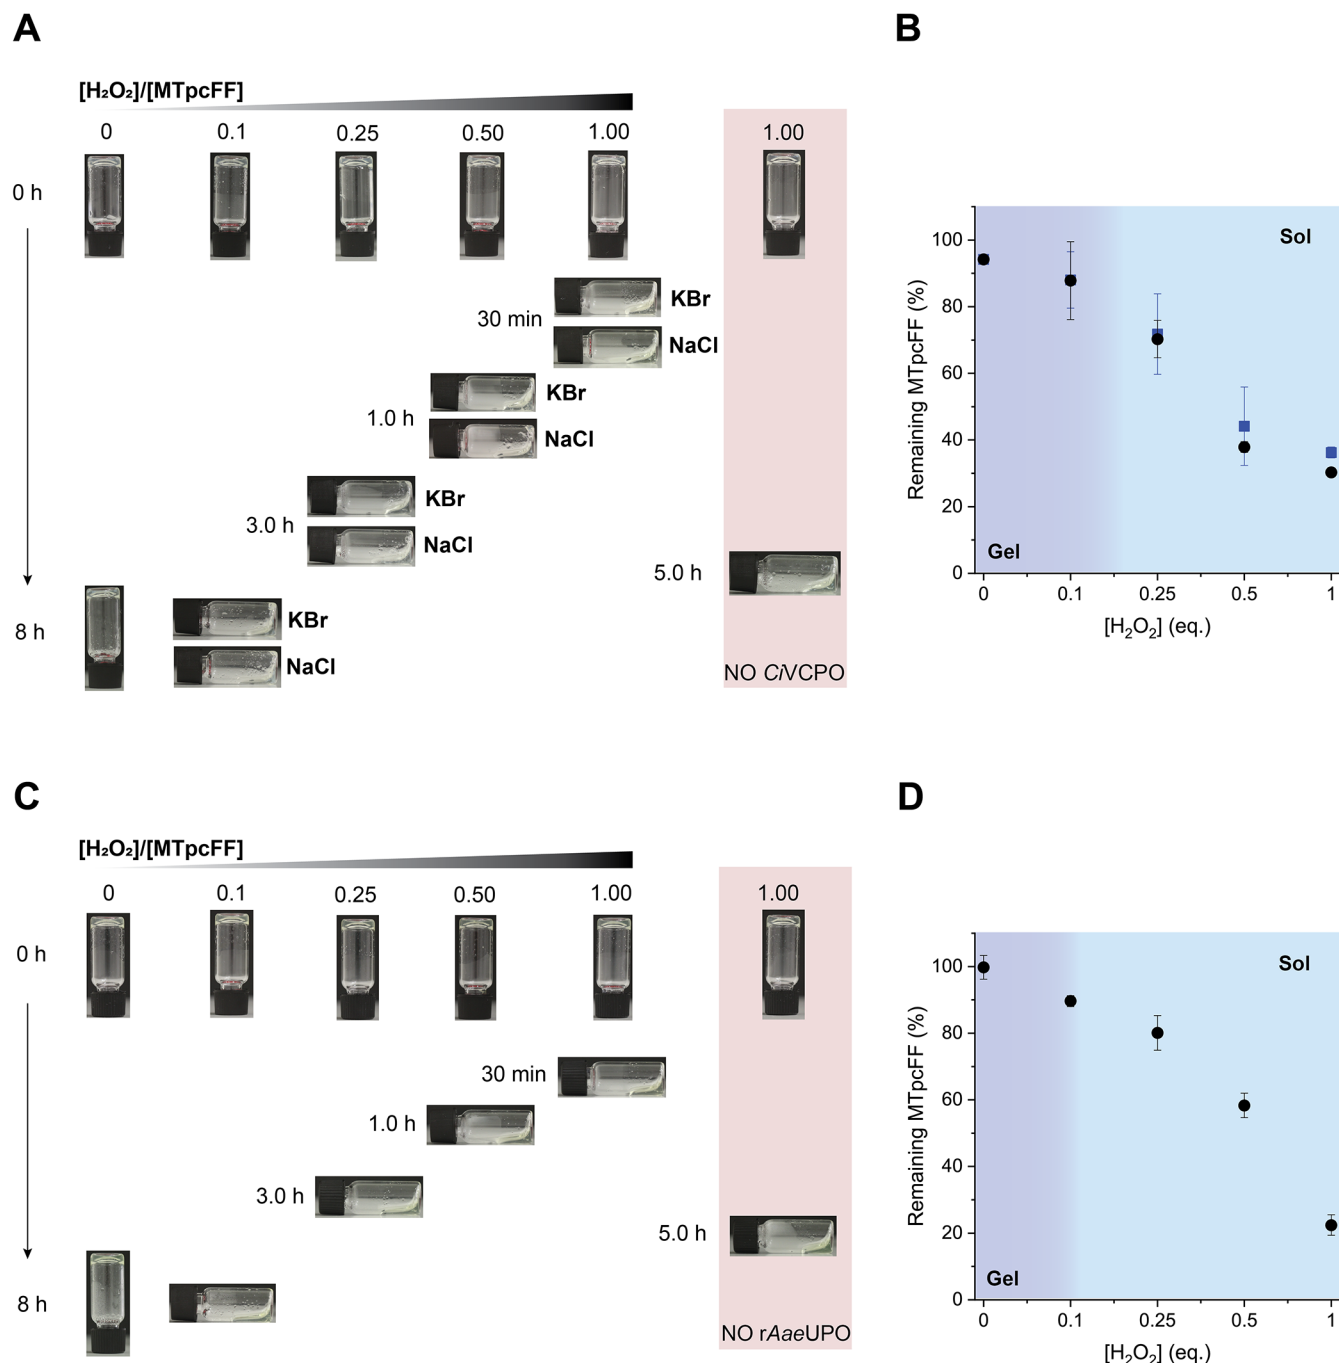


Figure 4. (A) Photographs of CVCPO (1.0 μM)-loaded MTpcFF hydrogels in CB after the addition of various amounts of H_2O_2 . (B) HPLC analysis of the remaining MTpcFF after the addition of various amounts of H_2O_2 in the presence of CVCPO (1.0 μM) in CB with NaCl (filled circles) or KBr (filled squares). The experiments were performed in duplicate to obtain the mean and standard deviation values (shown as error bars). (C) Photographs of rAaeUPO (1.0 μM)-loaded MTpcFF hydrogels in PB after the addition of various amounts of H_2O_2 . (D) HPLC analysis of the remaining MTpcFF after the addition of various amounts of H_2O_2 in the presence of rAaeUPO (1.0 μM) in PB. The experiments were performed in duplicate to obtain the mean and standard deviation values (shown as error bars).

To investigate the molecular mechanism behind the material change, we analyzed MTpcFF hydrogels as soon as they had disintegrated after the addition of 1.0 equiv. of H_2O_2 with the high-performance liquid chromatography (HPLC). In the chromatogram, we found that after this time the peak of MTpcFF has decreased, while an unidentified peak appeared at $t_R = 18.7$ min. LC-MS analysis revealed that we obtained the corresponding sulfoxide of the gelator (Figure S9). Despite the

presence in the HPLC analysis of about 15% FF 5 h after the addition of H_2O_2 , we concluded that the main cause of the disassembly of the hydrogel is the oxidation of MTpcFF into the more hydrophilic sulfoxide. This result comes unexpected since the sulfoxidation-related change in hydrophilicity was previously considered to be too small to lead to the disassembly of block copolymers based on this motif.³¹ On the other hand, the observed gel disruption at the oxidation

step accelerates the material response and removes the slow hydrolysis as the rate-determining step. In addition, the slow hydrolysis rate explains the considerable stability of the hydrogels in the absence of the oxidant.

The 10-fold acceleration of gel–sol transition encouraged us to explore $[\text{H}_2\text{O}_2]/[\text{MTpcFF}]$ ratios as low as 0.1. Interestingly, **MTpcFF** hydrogels were responsive to such low concentrations of H_2O_2 , even if the gel solubilization was not complete at 8 h (Figure 4A, bottom left). The HPLC analysis was performed on the solutions obtained after 5 h for the hydrogels exposed to high oxidant concentration, while the partially disrupted gels exposed to 0.1 equiv of H_2O_2 and the control experiments were analyzed after 8 h. The HPLC data in Figure 4B show that the presence of 0.1 equiv of H_2O_2 caused the consumption of about 10% gelator. Considering the corresponding gel picture, we can conclude that this variation in the **MTpcFF** concentration, and therefore the addition of 0.1 equiv of H_2O_2 , is not sufficient to completely degrade the gel. In contrast, upon the addition of 0.25 equiv of H_2O_2 we obtained full collapse of the gels in 3 h, with about 75% of the remaining gelator according to HPLC analysis. This suggests that the threshold for full solubilization of an **MTpcFF** gel (0.75 wt %) in CB is in the range of 0.1–0.2 equiv of H_2O_2 . All of these experiments were carried out either with hydrogen peroxide and either NaCl or KBr, needed for the production of hypohalites by *CiVCPO*. The chloroperoxidase is able to convert H_2O_2 and NaCl into HOCl, while in the presence of KBr, HOBr is formed. In principle, HOCl has a higher oxidation potential than HOBr, while the latter is more electrophilic and can react faster with the thioether.⁶² In the tube-inversion tests, the use of NaCl together with H_2O_2 led to solutions that appeared slightly less viscous than when KBr was used. In the correlating HPLC analysis, for additions of 1.0 and 0.5 equiv of H_2O_2 , about 6% less **MTpcFF** was measured when NaCl was added instead of KBr. However, the difference is not significant, making it difficult to assess what species has more impact on the system. On a second note, considering the abundant presence of chlorine in the cellular environment and the tendency of HOBr to react with a broad range of substrates other than the thioether,^{63,64} the conditions with NaCl should be favorable for biological applications.

Subsequently, we proceeded to test the gel disruption upon the addition of H_2O_2 between 0.1 and 1.0 equiv on 1.0 wt % of **MTpcFF** hydrogels (20 mM) in PB with and without *rAaeUPO* (1.0 μM). The photographs of these inverted vial tests are shown in Figure 4C. *rAaeUPO*-free hydrogels take 5 h to turn into a viscous solution in the presence of 1.0 equiv of the oxidant, while when *rAaeUPO* was encapsulated in the gel formulation, this time reduced to 30 min. The time to gel degradation was 1 and 3 h when, respectively, 0.5 and 0.25 equiv of H_2O_2 were added. We found that 0.1 equiv of hydrogen peroxide is enough to achieve the gel–sol transition even if the time scale is extended to 8 h in this case. The corresponding HPLC results (Figure 4D) showed that for 0.1 equiv of H_2O_2 , the expected 90% of **MTpcFF** was detected, which appeared to be below the CGC of the gels when compared with the tube-inversion tests. Such a low threshold is in line with the need for increasing the gelator concentration when performing gelation in PB compared to that achieved in CB. Additionally, we tested the stability of previously formed **MTpcFF** hydrogels in both PB and CB solutions, showing that **MTpcFF** hydrogels are stable in 500 μL of citrate buffer for 20 h and in 200 μL of phosphate buffer for more than 8 h (Figure

S7). These results demonstrate good stability of **MTpcFF** hydrogels compared to their responsiveness toward H_2O_2 .

Despite the different concentrations and conditions of **MTpcFF** hydrogels with *rAaeUPO* and with *CiVCPO*, the response times in gel collapse upon the addition of H_2O_2 were remarkably similar. The close catalytic effect of 1.0 μM of *rAaeUPO* and of 1.0 μM of *CiVCPO* (in the presence of halides) to oxidize the thioether with H_2O_2 was already anticipated from the ^1H NMR study on **1** (Figure 2). The translation of this effect to the hydrogels with different formulations enables these materials to have comparable sensitivity toward H_2O_2 (~ 2.0 mM), in both mildly acidic and neutral settings.

CONCLUSIONS

This study presents a thioether carbamate-based dipeptide that can form stable hydrogels in the pH range of 6.0–7.0. The addition of H_2O_2 leads to oxidation of the thioether to sulfoxide, triggering a solubility switch and disruption of the gel. We encapsulated two different peroxidases in the hydrogel: the vanadium-dependent chloroperoxidase *CiVCPO* in citrate buffer at pH 6.2 and the heme-dependent peroxidase *rAaeUPO* in phosphate buffer at pH 7.0. Enzymatic hydrogen peroxide activation in both cases resulted in the gel collapsing 10 times faster than peroxidase-free samples. The encapsulation of peroxidases in the gel matrix proved essential to achieve a gel–sol transition at hydrogen peroxide concentrations below 2.0 mM. Moreover, we believe that the similar responsiveness of the hydrogel in two different conditions is a key feature for application of this system in neutral and mildly acidic environments with elevated ROS concentrations.

This simple dipeptide-based gelator could be used to create a library of thioanisole carbamate-based LMWGs with different mechanical properties and response thresholds, making it a promising material for devices sensitive to redox imbalance in biological settings. Additionally, although not essential in this study, the hydrolytic instability of the carbamate after oxidation makes the thioether phenyl group a potential ROS-labile protecting group for amines in pharmaceutically active compounds.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.biomac.3c00262>.

Methods description; additional synthetic and characterization procedures; ^1H NMR and ^{13}C NMR spectra of the synthesized molecular models and hydrogelators; hydrogel characterization procedures; photographs of the inverted tube tests; optical microscopy and cryo-EM images of the hydrogels, and frequency distribution of the gel fiber diameters and HPLC analysis (PDF)

AUTHOR INFORMATION

Corresponding Author

Rienk Eelkema – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-2626-6371; Email: r.eelkema@tudelft.nl

Authors

Irene Piergentili – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-2220-4157

Thomas Hilberath – Department of Biotechnology, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-9778-2509

Benjamin Klemm – Department of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0002-8758-5771

Frank Hollmann – Department of Biotechnology, Delft University of Technology, 2629 HZ Delft, The Netherlands; orcid.org/0000-0003-4821-756X

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acs.biomac.3c00262>

Funding

This work was supported by an NWO-NSFC joint project.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

The authors acknowledge financial support from the Netherlands Organisation for Scientific Research and the National Natural Science Foundation of China (NWO-NSFC joint project). The authors thank Lloyd Mallee for the help with preparative HPLC and TU Delft Catalysis Engineering group and Liliana Baron for providing access and assistance to the Waters Acquity UPLC instrument. The authors are grateful to Dr. Wiel H. Evers for the cryo-EM images and to Sarah Schyck for the help with the optical microscope.

REFERENCES

- (1) Ni, M.; Zhuo, S. Applications of self-assembling ultrashort peptides in bionanotechnology. *RSC Adv.* **2019**, *9*, 844–852.
- (2) Yadav, N.; Chauhan, M. K.; Chauhan, V. S. Short to ultrashort peptide-based hydrogels as a platform for biomedical applications. *Biomater. Sci.* **2020**, *8*, 84–100.
- (3) Weiss, R. G. The Past, Present, and Future of Molecular Gels. What Is the Status of the Field, and Where Is It Going? *J. Am. Chem. Soc.* **2014**, *136*, 7519–7530.
- (4) Gupta, J. K.; Adams, D. J.; Berry, N. G. Will it gel? Successful computational prediction of peptide gelators using physicochemical properties and molecular fingerprints. *Chem. Sci.* **2016**, *7*, 4713–4719.
- (5) Mendes, A. C.; Baran, E. T.; Reis, R. L.; Azevedo, H. S. Self-assembly in nature: using the principles of nature to create complex nanobiomaterials. *Wiley Interdiscip. Rev.: Nanomed. Nanobiotechnol.* **2013**, *5*, 582–612.
- (6) Vegners, R.; Shestakova, I.; Kalvinsh, I.; Ezzell, R. M.; Janmey, P. A. Use of a gel-forming dipeptide derivative as a carrier for antigen presentation. *J. Pept. Sci.* **1995**, *1*, 371–378.
- (7) Reches, M.; Gazit, E. Casting Metal Nanowires Within Discrete Self-Assembled Peptide Nanotubes. *Science* **2003**, *300*, 625–627.
- (8) Roytman, R.; Adler-Abramovich, L.; Kumar, K. S. A.; Kuan, T.-C.; Lin, C.-C.; Gazit, E.; Brik, A. Exploring the self-assembly of glycopeptides using a diphenylalanine scaffold. *Org. Biomol. Chem.* **2011**, *9*, 5755–5761.
- (9) Krysmann, M. J.; Castelletto, V.; Kelarakis, A.; Hamley, I. W.; Hule, R. A.; Pochan, D. J. Self-Assembly and Hydrogelation of an Amyloid Peptide Fragment. *Biochemistry* **2008**, *47*, 4597–4605.
- (10) Kim, J.; Han, T. H.; Kim, Y.-I.; Park, J. S.; Choi, J.; Churchill, D. G.; Kim, S. O.; Ihee, H. Role of Water in Directing Diphenylalanine Assembly into Nanotubes and Nanowires. *Adv. Mater.* **2010**, *22*, 583–587.
- (11) Görbitz, C. H. The structure of nanotubes formed by diphenylalanine, the core recognition motif of Alzheimer's β -amyloid polypeptide. *Chem. Commun.* **2006**, *22*, 2332–2334.
- (12) Kuang, Y.; Du, X.; Zhou, J.; Xu, B. Supramolecular Nanofibrils Inhibit Cancer Progression In Vitro and In Vivo. *Adv. Healthcare Mater.* **2014**, *3*, 1217–1221.
- (13) Ischakov, R.; Adler-Abramovich, L.; Buzhansky, L.; Shekhter, T.; Gazit, E. Peptide-based hydrogel nanoparticles as effective drug delivery agents. *Biorg. Med. Chem.* **2013**, *21*, 3517–3522.
- (14) Diaferia, C.; Morelli, G.; Accardo, A. Fmoc-diphenylalanine as a suitable building block for the preparation of hybrid materials and their potential applications. *J. Mater. Chem. B* **2019**, *7*, 5142–5155.
- (15) Cardoso, A. Z.; Alvarez, A. E. A.; Cattoz, B. N.; Griffiths, P. C.; King, S. M.; Frith, W. J.; Adams, D. J. The influence of the kinetics of self-assembly on the properties of dipeptide hydrogels. *Faraday Discuss.* **2013**, *166*, 101–116.
- (16) Tang, C.; Ulijn, R. V.; Saiani, A. Effect of Glycine Substitution on Fmoc-Diphenylalanine Self-Assembly and Gelation Properties. *Langmuir* **2011**, *27*, 14438–14449.
- (17) Yang, Z.; Liang, G.; Wang, L.; Xu, B. Using a Kinase/Phosphatase Switch to Regulate a Supramolecular Hydrogel and Forming the Supramolecular Hydrogel in Vivo. *J. Am. Chem. Soc.* **2006**, *128*, 3038–3043.
- (18) Yi, M.; Guo, J.; He, H.; Tan, W.; Harmon, N.; Ghebreyess, K.; Xu, B. Phosphobisaromatic motifs enable rapid enzymatic self-assembly and hydrogelation of short peptides. *Soft Matter* **2021**, *17*, 8590–8594.
- (19) Huang, Y.; Qiu, Z.; Xu, Y.; Shi, J.; Lin, H.; Zhang, Y. Supramolecular hydrogels based on short peptides linked with conformational switch. *Org. Biomol. Chem.* **2011**, *9*, 2149–2155.
- (20) Sahoo, J. K.; Nalluri, S. K. M.; Javid, N.; Webb, H.; Ulijn, R. V. Biocatalytic amide condensation and gelation controlled by light. *Chem. Commun.* **2014**, *50*, 5462–5464.
- (21) Ikeda, M.; Tanida, T.; Yoshii, T.; Hamachi, I. Rational Molecular Design of Stimulus-Responsive Supramolecular Hydrogels Based on Dipeptides. *Adv. Mater.* **2011**, *23*, 2819–2822.
- (22) Ikeda, M.; Tanida, T.; Yoshii, T.; Kurotani, K.; Onogi, S.; Urayama, K.; Hamachi, I. Installing logic-gate responses to a variety of biological substances in supramolecular hydrogel–enzyme hybrids. *Nat. Chem.* **2014**, *6*, 511–518.
- (23) Napoli, A.; Valentini, M.; Tirelli, N.; Müller, M.; Hubbell, J. A. Oxidation-responsive polymeric vesicles. *Nat. Mater.* **2004**, *3*, 183–189.
- (24) El Mohtadi, F.; d'Arcy, R.; Burke, J.; De La Rosa, J. M. R.; Gennari, A.; Marotta, R.; Francini, N.; Donno, R.; Tirelli, N. “Tandem” Nanomedicine Approach against Osteoclastogenesis: Polysulfide Micelles Synergically Scavenge ROS and Release Rapamycin. *Biomacromolecules* **2020**, *21*, 305–318.
- (25) Geven, M.; d'Arcy, R.; Turhan, Z. Y.; El-Mohtadi, F.; Alshamsan, A.; Tirelli, N. Sulfur-based oxidation-responsive polymers. Chemistry, (chemically selective) responsiveness and biomedical applications. *Eur. Polym. J.* **2021**, *149*, No. 110387.
- (26) Yu, S.; Wang, C.; Yu, J.; Wang, J.; Lu, Y.; Zhang, Y.; Zhang, X.; Hu, Q.; Sun, W.; He, C.; Chen, X.; Gu, Z. Injectable Bioresponsive Gel Depot for Enhanced Immune Checkpoint Blockade. *Adv. Mater.* **2018**, *30*, No. 1801527.
- (27) Xu, Q.; He, C.; Ren, K.; Xiao, C.; Chen, X. Thermosensitive Polypeptide Hydrogels as a Platform for ROS-Triggered Cargo Release with Innate Cytoprotective Ability under Oxidative Stress. *Adv. Healthcare Mater.* **2016**, *5*, 1979–1990.
- (28) Spitzer, D.; Rodrigues, L. L.; Straßburger, D.; Mezger, M.; Besenius, P. Tuneable Transient Thermogels Mediated by a pH- and Redox-Regulated Supramolecular Polymerization. *Angew. Chem., Int. Ed.* **2017**, *56*, 15461–15465.
- (29) Miao, X.; Cao, W.; Zheng, W.; Wang, J.; Zhang, X.; Gao, J.; Yang, C.; Kong, D.; Xu, H.; Wang, L.; Yang, Z. Switchable Catalytic Activity: Selenium-Containing Peptides with Redox-Controllable Self-Assembly Properties. *Angew. Chem., Int. Ed.* **2013**, *52*, 7781–7785.

- (30) Criado-Gonzalez, M.; Mecerreyes, D. Thioether-based ROS responsive polymers for biomedical applications. *J. Mater. Chem. B* **2022**, *10*, 7206–7221.
- (31) Piergentili, I.; Bouwmans, P. R.; Reinalda, L.; Lewis, R. W.; Klemm, B.; Liu, H.; de Kruijff, R. M.; Denkova, A. G.; Eelkema, R. Thioanisole ester based logic gate cascade to control ROS-triggered micellar degradation. *Polym. Chem.* **2022**, *13*, 2383–2390.
- (32) Allen, B. L.; Johnson, J. D.; Walker, J. P. Encapsulation and Enzyme-Mediated Release of Molecular Cargo in Polysulfide Nanoparticles. *ACS Nano* **2011**, *5*, 5263–5272.
- (33) Tóth, Z.; Fábrián, I. Oxidation of Chlorine(III) by Hypobromous Acid: Kinetics and Mechanism. *Inorg. Chem.* **2004**, *43*, 2717–2723.
- (34) Hu, Y.; Xie, G.; Stanbury, D. M. Oxidations at Sulfur Centers by Aqueous Hypochlorous Acid and Hypochlorite: Cl⁺ Versus O Atom Transfer. *Inorg. Chem.* **2017**, *56*, 4047–4056.
- (35) Höfler, G. T.; But, A.; Hollmann, F. Haloperoxidases as catalysts in organic synthesis. *Org. Biomol. Chem.* **2019**, *17*, 9267–9274.
- (36) Fernández-Fueyo, E.; van Wingerden, M.; Renirie, R.; Wever, R.; Ni, Y.; Holtmann, D.; Hollmann, F. Chemoenzymatic Halogenation of Phenols by using the Haloperoxidase from *Curvularia inaequalis*. *ChemCatChem* **2015**, *7*, 4035–4038.
- (37) Fernández-Fueyo, E.; Younes, S. H. H.; van Rootselaar, S.; Aben, R. W. M.; Renirie, R.; Wever, R.; Holtmann, D.; Rutjes, F. P. J. T.; Hollmann, F. A Biocatalytic Aza-Achmatowicz Reaction. *ACS Catal.* **2016**, *6*, 5904–5907.
- (38) Dong, J. J.; Fernández-Fueyo, E.; Li, J.; Guo, Z.; Renirie, R.; Wever, R.; Hollmann, F. Halofunctionalization of alkenes by vanadium chloroperoxidase from *Curvularia inaequalis*. *Chem. Commun.* **2017**, *53*, 6207–6210.
- (39) Wever, R.; Renirie, R.; Hollmann, F. Vanadium Chloroperoxidases as Versatile Biocatalysts. In *Vanadium Catalysis*; Sutradhar, M.; Pombeiro, A. J. L.; da Silva, J. A. L., Eds.; The Royal Society of Chemistry, 2021; pp 548–563.
- (40) Lin, B.; Chen, H.; Liang, D.; Lin, W.; Qi, X.; Liu, H.; Deng, X. Acidic pH and High-H₂O₂ Dual Tumor Microenvironment-Responsive Nanocatalytic Graphene Oxide for Cancer Selective Therapy and Recognition. *ACS Appl. Mater. Interfaces* **2019**, *11*, 11157–11166.
- (41) Ozaki, S.-i.; Yang, H.-J.; Matsui, T.; Goto, Y.; Watanabe, Y. Asymmetric oxidation catalyzed by myoglobin mutants. *Tetrahedron: Asymmetry* **1999**, *10*, 183–192.
- (42) Baciocchi, E.; Gerini, M. F.; Harvey, P. J.; Lanzalunga, O.; Mancinelli, S. Oxidation of aromatic sulfides by lignin peroxidase from *Phanerochaete chrysosporium*. *Eur. J. Biochem.* **2000**, *267*, 2705–2710.
- (43) Peter, S.; Kinne, M.; Wang, X.; Ullrich, R.; Kayser, G.; Groves, J. T.; Hofrichter, M. Selective hydroxylation of alkanes by an extracellular fungal peroxygenase. *FEBS J.* **2011**, *278*, 3667–3675.
- (44) Kluge, M.; Ullrich, R.; Dolge, C.; Scheibner, K.; Hofrichter, M. Hydroxylation of naphthalene by aromatic peroxygenase from *Agrocybe aegerita* proceeds via oxygen transfer from H₂O₂ and intermediary epoxidation. *Appl. Microbiol. Biotechnol.* **2009**, *81*, 1071–1076.
- (45) Höfler, G. T.; But, A.; Younes, S. H. H.; Wever, R.; Paul, C. E.; Arends, I. W. C. E.; Hollmann, F. Chemoenzymatic Halocyclization of 4-Pentenoic Acid at Preparative Scale. *ACS Sustainable Chem. Eng.* **2020**, *8*, 2602–2607.
- (46) Zippilli, C.; Bartolome, M. J.; Hilberath, T.; Botta, L.; Hollmann, F.; Saladino, R. A Photochemoenzymatic Hunsdiecker-Borodin-Type Halodecarboxylation of Ferulic Acid. *ChemBioChem* **2022**, *23*, No. e202200367.
- (47) Tonin, F.; Tieves, F.; Willot, S.; van Troost, A.; van Oosten, R.; Breestraat, S.; van Pelt, S.; Alcalde, M.; Hollmann, F. Pilot-Scale Production of Peroxygenase from *Agrocybe aegerita*. *Org. Process Res. Dev.* **2021**, *25*, 1414–1418.
- (48) Molina-Espeja, P.; Garcia-Ruiz, E.; Gonzalez-Perez, D.; Ullrich, R.; Hofrichter, M.; Alcalde, M. Directed Evolution of Unspecific Peroxygenase from *Agrocybe aegerita*. *Appl. Environ. Microbiol.* **2014**, *80*, 3496–3507.
- (49) Freer, R.; McKillop, A. Synthesis of Symmetrical and Unsymmetrical Ureas Using Unsymmetrical Diaryl Carbonates. *Synth. Commun.* **1996**, *26*, 331–349.
- (50) Dadhwal, S.; Fairhall, J. M.; Goswami, S. K.; Hook, S.; Gamble, A. B. Alkene–Azide 1,3-Dipolar Cycloaddition as a Trigger for Ultrashort Peptide Hydrogel Dissolution. *Chem. - Asian J.* **2019**, *14*, 1143–1150.
- (51) Tanwar, D. K.; Ratan, A.; Gill, M. S. A facile synthesis of sulfonylureas via water assisted preparation of carbamates. *Org. Biomol. Chem.* **2017**, *15*, 4992–4999.
- (52) de Loos, M.; Feringa, B. L.; van Esch, J. H. Design and Application of Self-Assembled Low Molecular Weight Hydrogels. *Eur. J. Org. Chem.* **2005**, *2005*, 3615–3631.
- (53) Estroff, L. A.; Hamilton, A. D. Water Gelation by Small Organic Molecules. *Chem. Rev.* **2004**, *104*, 1201–1218.
- (54) Adler-Abramovich, L.; Vaks, L.; Carny, O.; Trudler, D.; Magno, A.; Cafisch, A.; Frenkel, D.; Gazit, E. Phenylalanine assembly into toxic fibrils suggests amyloid etiology in phenylketonuria. *Nat. Chem. Biol.* **2012**, *8*, 701–706.
- (55) Raeburn, J.; Pont, G.; Chen, L.; Cesbron, Y.; Lévy, R.; Adams, D. J. Fmoc-diphenylalanine hydrogels: understanding the variability in reported mechanical properties. *Soft Matter* **2012**, *8*, 1168–1174.
- (56) Fleming, S.; Ulijn, R. V. Design of nanostructures based on aromatic peptide amphiphiles. *Chem. Soc. Rev.* **2014**, *43*, 8150–8177.
- (57) Hofmeister, F. Zur Lehre von der Wirkung der Salze. *Arch. Exp. Pathol. Pharmacol.* **1888**, *24*, 247–260.
- (58) Roy, S.; Javid, N.; Frederix, P. W. J. M.; Lamprou, D. A.; Urquhart, A. J.; Hunt, N. T.; Halling, P. J.; Ulijn, R. V. Dramatic Specific-Ion Effect in Supramolecular Hydrogels. *Chem. - Eur. J.* **2012**, *18*, 11723–11731.
- (59) Gregory, K. P.; Elliott, G. R.; Robertson, H.; Kumar, A.; Wanless, E. J.; Webber, G. B.; Craig, V. S. J.; Andersson, G. G.; Page, A. J. Understanding specific ion effects and the Hofmeister series. *Phys. Chem. Chem. Phys.* **2022**, *24*, 12682–12718.
- (60) Abraham, B. L.; Agredo, P.; Mensah, S. G.; Nilsson, B. L. Anion Effects on the Supramolecular Self-Assembly of Cationic Phenylalanine Derivatives. *Langmuir* **2022**, *38*, 15494–15505.
- (61) Aggeli, A.; Bell, M.; Boden, N.; Keen, J. N.; Knowles, P. F.; McLeish, T. C. B.; Pitkeathly, M.; Radford, S. E. Responsive gels formed by the spontaneous self-assembly of peptides into polymeric β -sheet tapes. *Nature* **1997**, *386*, 259–262.
- (62) Ximenes, V. F.; Morgon, N. H.; de Souza, A. R. Hypobromous acid, a powerful endogenous electrophile: Experimental and theoretical studies. *J. Inorg. Biochem.* **2015**, *146*, 61–68.
- (63) Hawkins, C. L.; Davies, M. J. Role of myeloperoxidase and oxidant formation in the extracellular environment in inflammation-induced tissue damage. *Free Radical Biol. Med.* **2021**, *172*, 633–651.
- (64) Davies, M. J. Myeloperoxidase-derived oxidation: mechanisms of biological damage and its prevention. *J. Clin. Biochem. Nutr.* **2010**, *48*, 8–19.