

## **Durability of European Asphalt Mixtures Containing Reclaimed Asphalt and Warm-Mix Additives**

Varveri, Katerina; Avgerinopoulos, Stavros; Scarpas, Tom

**Publication date**

2016

**Document Version**

Accepted author manuscript

**Published in**

Transportation Research Board 95th annual meeting

**Citation (APA)**

Varveri, K., Avgerinopoulos, S., & Scarpas, T. (2016). Durability of European Asphalt Mixtures Containing Reclaimed Asphalt and Warm-Mix Additives. In *Transportation Research Board 95th annual meeting: Washington DC, United States* (pp. 1-13)

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

1                   **Durability of European Asphalt Mixtures Containing Reclaimed**  
 2                   **Asphalt and Warm Mix Additives**

3  
4  
5   **Aikaterini (Katerina) Varveri**

6 Pavement Engineering

7 Faculty of Civil Engineering & Geosciences

8 Delft University of Technology

9 Address: Stevinweg 1, 2628 CN, Delft, The Netherlands.

10 Tel: +31 15 27 84665, Fax: +31 15 27 85767, Email: [a.varveri@tudelft.nl](mailto:a.varveri@tudelft.nl)

11  
12   **Stavros Avgerinopoulos**

13 Faculty of Technology

14 De Montfort University

15 Address: The Gateway, LE1 9BH, Leicester, United Kingdom

16 Tel: +44 116 257 7092, Fax: +44 116 250 6092, Email: [savgerinopoulos@dmu.ac.uk](mailto:savgerinopoulos@dmu.ac.uk)

17  
18   **Athanasios (Tom) Scarpas**

19 Pavement Engineering

20 Faculty of Civil Engineering & Geosciences

21 Delft University of Technology

22 Address: Stevinweg 1, 2628 CN, Delft, The Netherlands.

23 Tel: +31 15 27 84665, Fax: +31 15 27 85767, Email: [a.scarpas@tudelft.nl](mailto:a.scarpas@tudelft.nl)

24  
25  
26  
27  
28   Word count

29			
30	Number of words in the abstract:	=	223 words
31	Number of words in text:	=	4607 words
32	Number of words in references:	=	634 words
33	Number of tables: (2 x 250)	=	500 words equivalent
34	Number of figures: (5 x 250)	=	1250 words equivalent
35	-----		-----
36	Total number of words	=	7214 words equivalent

37  
38  
39   Date of first paper submission: 8 July 2015

40   Date of revised paper submission: 11 November 2015

41  
42  
43   *Corresponding author:*

44   Aikaterini Varveri

45   Pavement Engineering

46   Faculty of Civil Engineering & Geosciences

47   Delft University of Technology

48   Address: Stevinweg 1, 2628 CN, Delft, the Netherlands.

49   Tel: +31 15 27 84665, Fax: +31 15 27 85767, Email: [a.varveri@tudelft.nl](mailto:a.varveri@tudelft.nl)

50  
51

**ABSTRACT**

This paper investigates the moisture susceptibility of European asphalt mixtures containing reclaimed asphalt (RA) and warm mix (WMA) additives. Test sections of a typical SMA mixture have been laid, from which cylindrical samples were cored and utilised for laboratory testing. Four variants of the SMA mixture were prepared; a control HMA mixture with 0% RA, a mixture with 30% RA and no WMA additive, a mixture with 30% RA in which a WMA additive was added and a mixture with 40% RA and a WMA additive. The coring procedure and testing were carried out in two phases; first field cores were taken 24 hrs after the construction of the test section was completed and then once again 12 months later. In this way, the influence of field ageing on the mechanical performance of the mixtures was considered. The samples were moisture conditioned at various combinations of water bath immersion and cyclic pore pressures by means of the Moisture Induced Sensitivity Tester (MiST). The degradation in strength due to moisture was quantified through indirect tensile strength tests. The results indicated that the use of RA in combination with WMA additives resulted to mixtures with improved durability characteristics, with respect to moisture damage, compared to the control HMA mixture. Based on the results, recommendations were made for characterizing and limiting moisture damage of asphalt pavements.

*Keywords:* Durability, Moisture damage, Ageing, Reclaimed asphalt, Warm mix additive

## 1 INTRODUCTION

2 Traditional technologies for asphalt mixture production are gradually being replaced by warm  
3 mix asphalt (WMA) and reclaimed asphalt (RA) technologies due to the associated environmental  
4 benefits. These benefits are usually listed as a combination of lower fuel consumption and  
5 greenhouse gases emissions, along with a reduction in virgin materials consumption and the  
6 amount of waste sent to landfills, all potentially contributing to the overall development of  
7 sustainable road infrastructure. The challenge for engineers is to develop environmental friendly  
8 pavement materials with similar mechanical performance to those of the conventional ones and,  
9 at the same time, to consider ways to make the most of such technologies by further increasing  
10 the RA content or lowering the temperatures in pavement mixture design and construction.  
11 Obviously, the benefits that arise from the use of RA and WMA can be compromised if the  
12 mixture performance is poor in the long-term. For this reason, further research is still needed to  
13 evaluate the performance and durability of WMA and RA mixtures.

14 Traffic loading and environment affect substantially the long-term performance and  
15 durability of asphalt pavements. Several environmental factors such as temperature variations,  
16 humidity, precipitation, oxygen, freeze-thaw cycles and ultraviolet radiation can degrade the  
17 mixture properties, thus decreasing its ability to sustain traffic loads. As a result, an increase in  
18 the operational and maintenance costs is needed in order to fulfil the expected service life of the  
19 pavement system. Of all possible damages, moisture and oxidative ageing have been identified as  
20 important contributors to various forms of damage such as ravelling, rutting and cracking.

21 Moisture damage is a result of various processes that occur when liquid water or moisture  
22 vapour interacts with asphalt mixtures. Moisture diffusion, binder erosion due to the scouring  
23 action of water and pressure development in the macro pores of the pavements due to repeated  
24 traffic loading are the most important moisture-induced damage processes found in literature (1,  
25 2). Moisture damage phenomena are particularly complex as they depend, among others, on  
26 mixture morphology (air voids percentage, size and interconnectivity and hence permeability) and  
27 on the physico-chemical properties of bituminous binders and aggregates (diffusivity and  
28 chemical affinity with water). Similarly, oxidative ageing of the binder is another cause of  
29 mixture degradation. It appears to be a complex phenomenon that alters the viscoelastic  
30 behaviour of the binder through chemical and/or physical processes in time and typically leads to  
31 embrittlement of the binder, making the pavements more prone to damage under the same loads  
32 and strains. Depending on the availability of oxygen for diffusion in a pavement, asphalt binders  
33 will harden in time and become brittle; consequently the propensity of asphalt pavements to  
34 cracking increases (3).

35 The use of RA and WMA technologies can influence the aforementioned degradation  
36 mechanisms and hence, can further complicate an already complex situation. At the time of  
37 construction, it may be that the initial properties of these mixtures are comparable to those of  
38 traditional hot mix asphalt (HMA) mixtures; however, the changes in material properties with  
39 time may be greater (or lesser) for those mixtures than for HMA mixtures and consequently this  
40 will have an influence on their durability. WMA is a type of asphalt mixture that is produced, laid  
41 and compacted at temperatures lower than those for HMA. Typically, the mixing temperature for  
42 WMA ranges from 100°C to 140°C compared with 150°C to 180°C for HMA (4). It is quite  
43 frequently noted, however, that the reduction in mixing temperatures for WMA could adversely  
44 affect the moisture resistance of asphalt mixtures (5), because the reduced mixing temperature  
45 might lead to inadequate drying and/or coating of the aggregates. Additionally, the introduction  
46 of water into the production of the mixtures (for example when using foaming techniques) could  
47 also give unintended moisture damage issues.

48 In the recent past, several studies have been undertaken to evaluate moisture  
49 susceptibility of WMA mixtures. Kanitpong et al. (5) performed dynamic creep tests under water  
50 on HMA and WMA specimens produced by using a 60/70 asphalt binder combined with two  
51 aggregate types. For the WMA mixtures 3% Sasobit was used as an additive to allow production

1 at a lower temperature of 110°C. The results indicated that WMA mixtures had a greater  
2 resistance to permanent deformation than HMA mixtures, probably due to the fact that Sasobit  
3 results in higher mixture stiffness. However, in terms of moisture susceptibility, WMA was more  
4 sensitive to moisture compared to HMA. Differences, between the WMA and HMA mixtures,  
5 were also found in relation to the gradation and aggregate type. Slag aggregates performed better  
6 against moisture for the HMA mixtures, while the WMA slag mixtures exhibited high sensitivity  
7 to moisture damage. This can be attributed to the fact that moisture entrapped within the slag  
8 aggregates, due to their high porosity, could not be thoroughly dried in WMA due to the lower  
9 production temperature. Therefore, to improve moisture susceptibility of WMA mixtures,  
10 aggregate types with desirable properties should be considered.

11 In another study, Xiao et al. (6) performed indirect tensile tests on WMA and HMA  
12 mixtures after moisture conditioning. They reported that HMA had a better performance  
13 compared to WMA mixtures regardless of the aggregate, storage duration and antistripping agent  
14 type. However, there exists also evidence that does not support the abovementioned results.  
15 Kavussi and Hashemian (7) reported that the addition of 2% hydrated lime improved significantly  
16 the performance of WMA mixtures in terms of their tensile strength and rutting potential under  
17 wet conditions. Nevertheless, a further reduction in mixing temperature resulted to a increase in  
18 moisture sensitivity. Moreover, Hurley and Prowell (8) reported that, depending on the aggregate  
19 and binder type, different WMA additives showed variability compared to the control mixture  
20 with respect to moisture susceptibility. From the above it is clear that more investigation is still  
21 required to achieve a better understanding of moisture-induced damage in WMA mixtures.

22 Apart from the low temperature mixtures, reclaimed asphalt technology, namely the use  
23 of old asphalt pavements that are milled up or ripped off the road (9), is a useful alternative to  
24 virgin materials that can reduce the use of virgin aggregates and asphalt binders for HMA, WMA  
25 or cold mix asphalt mixtures (10). To investigate the durability characteristics of RA mixtures,  
26 with respect to their moisture sensitivity, several research projects were undertaken. Aurangzeb et  
27 al. (11) performed the Illinois DOT's moisture susceptibility test on four mixtures with 0%, 30%,  
28 40%, and 50% RA content produced with two aggregate types. The results showed that the tensile  
29 strength and tensile strength ratio (TSR) of all mixtures increased with increasing RA content,  
30 with the exception of the 40% RA mixture that failed to pass the minimum TSR criterion (TSR ≥  
31 85%). Moreover, Hajj et al. (12) reported that overall the addition of RA to a mixture resulted in  
32 acceptable moisture resistance; however a reduction in the unconditioned and conditioned tensile  
33 strength was observed.

34 Another study by He and Wong (13) concluded that the bitumen type and ageing level of  
35 RA materials significantly affects moisture susceptibility. Also, they reported that the indirect  
36 tensile strength of fine aggregate mixtures decreased with increasing RA content under dry and  
37 wet conditions and that hard bitumen types were found to improve moisture susceptibility. West  
38 et al. (14) conducted performance related tests to determine the susceptibility of asphalt mixtures  
39 containing RA to various distresses. Thirty mixtures were designed and produced with different  
40 RA contents and virgin binders, using materials from contractors in New Hampshire, Utah,  
41 Minnesota, and Florida. The assessment of the mixtures for their susceptibility to moisture was  
42 performed using AASHTO T283. The results showed that mixtures with high RA content  
43 generally had higher tensile strength than virgin mixtures before and after moisture conditioning.  
44 In several cases, however, the high RA content mixtures did not initially meet the standard 0.80  
45 TSR criterion and the addition of an antistripping additive was needed to improve their TSR  
46 values.

47 Other researchers investigated the moisture sensitivity of mixtures prepared with both  
48 WMA and RA technologies. A study by Zhao et al. (15) used laboratory performance tests to  
49 evaluate the effect of high RA percentages on WMA mixtures. The performance against rutting,  
50 fatigue and moisture damage was investigated for four WMA mixtures with 0%, 30%, 40%, and  
51 50% RA. In addition, two HMA control mixtures were designed with 0% and 30% RA. Moisture

1 susceptibility was evaluated using the Hamburg wheel tracking test and AASHTO T283 with one  
 2 freeze-thaw cycle. It was found that the TSR values of WMA containing high percentages of  
 3 RAP (30%, 40% and 50%) were higher compared to that of virgin WMA, which indicates that the  
 4 addition of RA can potentially reduce significantly moisture susceptibility of WMAs. Similar  
 5 observations were made for the HMA mixtures containing RA.

6 Moreover, Shu et al. (16) evaluated the moisture susceptibility of plant-produced foamed  
 7 WMA containing high percentages of RA using multiple moisture conditioning procedures and  
 8 laboratory performance tests. Testing involved the Superpave indirect test, the Hamburg wheel  
 9 tracking test, and the dynamic modulus test on dry and moisture conditioned samples using two  
 10 conditioning procedures i.e. the AASHTO T283 freeze–thaw procedure and the moisture induced  
 11 stress tester (MIST). The findings showed that increasing the RA content in the mixtures  
 12 generally led to the increase in the ratios of conditioned to dry samples for the various properties.  
 13 Overall, it was observed that moisture susceptibility decreased with increasing RA content and  
 14 that plant-produced foamed WMA showed similar moisture susceptibility to that of HMA. It was  
 15 concluded that foamed WMA combined with RA could perform as well as HMA in terms of  
 16 moisture damage.


17 From the above, it can be concluded that there is a need for further research regarding the  
 18 moisture damage susceptibility of asphalt mixtures that use WMA and RA technologies. A better  
 19 understanding of the moisture damage mechanisms themselves, but also in relation with the new  
 20 mixture production technologies is essential.

21  
 22 **OBJECTIVES**

23 The main objective of this study was to evaluate the differences in moisture sensitivity  
 24 that arise from the use of WMA and RA technologies in comparison to hot mix asphalt (HMA)  
 25 mixtures. Moreover, an attempt was made to study the effect of ageing on the moisture sensitivity  
 26 of HMA and WMA-RA mixtures. To this end, in this study, a moisture conditioning protocol that  
 27 combines bath conditioning and pore pressure application by means of MiST was used to  
 28 characterize moisture damage of WMA asphalt mixtures containing RA. The combined protocol  
 29 takes into account the key moisture damage processes and allows the quantification of their  
 30 contributions to moisture damage. For this, asphalt cores obtained from site trials at two distinct  
 31 time intervals, namely after pavement construction and after one year of service. The evaluation  
 32 of the moisture susceptibility characteristics of the various mixtures was made on the basis of  
 33 their tensile strength and tensile strength ratio (TSR).

34  
 35 **MIXTURE DESIGN AND SAMPLE COLLECTION**

36 In this study, the effect of using reclaimed asphalt and WMA additives on the durability of  
 37 asphalt pavements was studied on the basis of site trials. Four variants of a typical SMA surface  
 38 course were produced according to the Irish and European standards and laid on the test sections,  
 39 as shown in Figure 1.

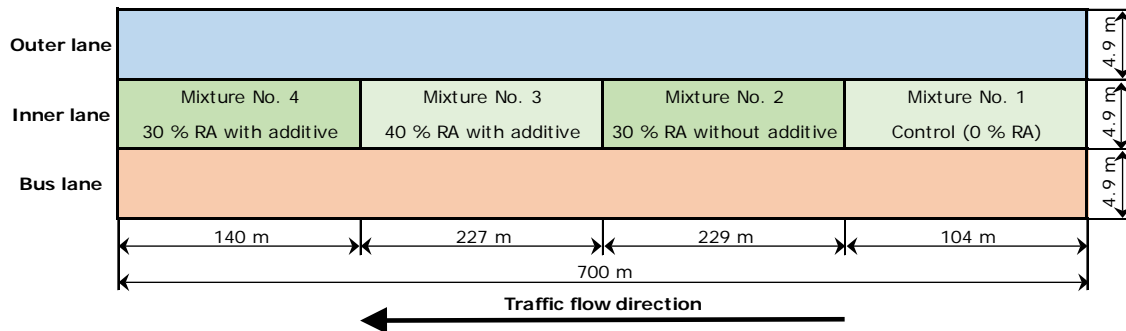

40  
 41 **FIGURE 1 Schematic representation of the test sections. After Tabaković et al. (17).**

The selected test section is a dual carriage road with three traffic lanes on each direction (bus lane and two traffic lanes). The middle lane was chosen as the test lane because it will be subjected to the most trafficking, particularly from heavy goods vehicles (18). The mixture had a maximum aggregate size of 10 mm. The mix design target air voids content for all mixtures was 10% whereas the achieved air voids content ranged from 6.8% to 7.5 %. Four variants of the SMA mixture were prepared. Specifically, a control mixture with 0% RA, a mixture with 30% RA and no WMA additive and two more mixtures with Cecabase RT 945 warm mix additive and 30% and 40% of reclaimed asphalt. Table 1 shows the mix design of the four different mixtures. More information on the mixture design and construction of the site trials can be found in Tabaković et al. (17).

**TABLE 1 Mixture design. After Tabaković et al. (17).**

Mixture	Proportional content (%)					
	RA content (%)	Aggregates (10 mm)	CRF*	Filler	Fresh binder	WMA additive**
A	0	65.9	22.8	5.7	5.6	0
B	28.6	43.8	17	5.7	4.9	0
C	38.1	34.4	17.1	5.7	4.7	0.3
D	28.6	43.8	17	5.7	4.9	0.3

\*Crushed rock fines  
\*\*WMA additive added at 0.5% of the total binder content

Overall, a total of 216 cores were collected and tested for their sensitivity to moisture damage. First, a total of 108 cores (27 from each trial section) were collected 24 hours after the construction of the site trial section was completed, while in order to consider the effect of ageing another 108 cores were taken nearly one year after the construction of the trial section. The asphalt field cores were 100 mm in diameter and approximately 60 mm in height. The cores consisted of two different layers, namely the SMA surface course and the underneath binder course. Therefore, prior to testing, the binder course was removed by sawing the asphalt cores using a diamond saw. Then the height of the samples was measured in accordance with the European standard EN 12697-29.

### MOISTURE CONDITIONING AND TESTING PROTOCOL

Earlier, moisture diffusion and pumping action were identified as the dominant moisture-induced damage mechanisms. However, the time frame over which each mechanism occurs in the field differs significantly. Moisture diffusion occurs over a longer timeframe, while excess pore pressure development takes place in very short times. In order to address the individual mechanisms associated with these two damage processes, the field cores were subjected to a combination of two different conditioning methods: (a) immersion in water bath and (b) cyclic pore pressure application.


Bath conditioning was performed at elevated temperatures so as to facilitate moisture diffusion into the mixture, accelerating thus the long-term degradation of the material properties. Cyclic pore pressure was applied on the samples by means of the moisture induced sensitivity tester (MiST). MiST is a self-contained unit which includes a hydraulic pump and a piston mechanism that is designed to cyclically apply pressure inside a sample chamber. Moisture conditioning is performed by placing a compacted asphalt sample in the chamber and filling it with water. Then the water is pumped through the sample, thus creating pressure cycles between zero and the chosen pressure. One can choose the pressure, temperature and the number of conditioning cycles to replicate different combinations of traffic and environmental conditions (19).

1 After delivery, the samples were subjected to the above mentioned combinations of bath  
 2 and MiST conditioning. First the samples were immersed in a bath with distilled water at an  
 3 elevated temperature of 60°C, in order to facilitate the diffusion of water into the asphalt samples.  
 4 At specified time intervals of 3 and 6 weeks three samples per mixture were removed from the  
 5 bath, placed in water at 20°C for 2 hours and then maintained in a climate chamber at 20°C until  
 6 tested. An additional three samples per mixture were removed from the bath and further  
 7 conditioned in MiST; 4000 cycles of pressure were applied at a temperature of 60°C and a  
 8 pressure of 70 psi (0.48 MPa). After MiST conditioning, the samples were placed in a water bath  
 9 at 20°C for 2 hours and then in a climate chamber until testing. More details on the moisture  
 10 conditioning protocol and the selection of the various parameters are given in a previous study  
 11 (20).

12 The additional step of placing the samples in a water bath at room temperature (20°C)  
 13 was found to be essential, considering that the samples were conditioned at high temperature and  
 14 therefore, they became soft after bath or MiST application. This extra step allowed the  
 15 stabilization and further handling of the samples. The degradation of the mechanical properties  
 16 due to moisture conditioning was evaluated through indirect tensile tests (ITT), which were  
 17 performed in accordance with the EN 12697-23 standard. The indirect tensile strength tests were  
 18 performed at 20°C at a loading rate of 50 mm/min.

19  
 20 **TEST RESULTS AND DISCUSSION**

21 The susceptibility of the asphalt cores to moisture was evaluated on the basis of their indirect  
 22 tensile strength (ITS) and indirect tensile strength ratio (ITSR). The mean ITSR values (out of  
 23 three replicate samples), after bath and bath-MiST conditioning, for the unaged (fresh) and field  
 24 aged samples are shown in Figures 2 and 3, respectively. Also, the coefficient of variation was  
 25 calculated and presented on the top of the columns. The dashed line represents the threshold value  
 26 below which an asphalt mixture is considered to be susceptible to moisture damage, according to  
 27 Dutch and Irish standards.

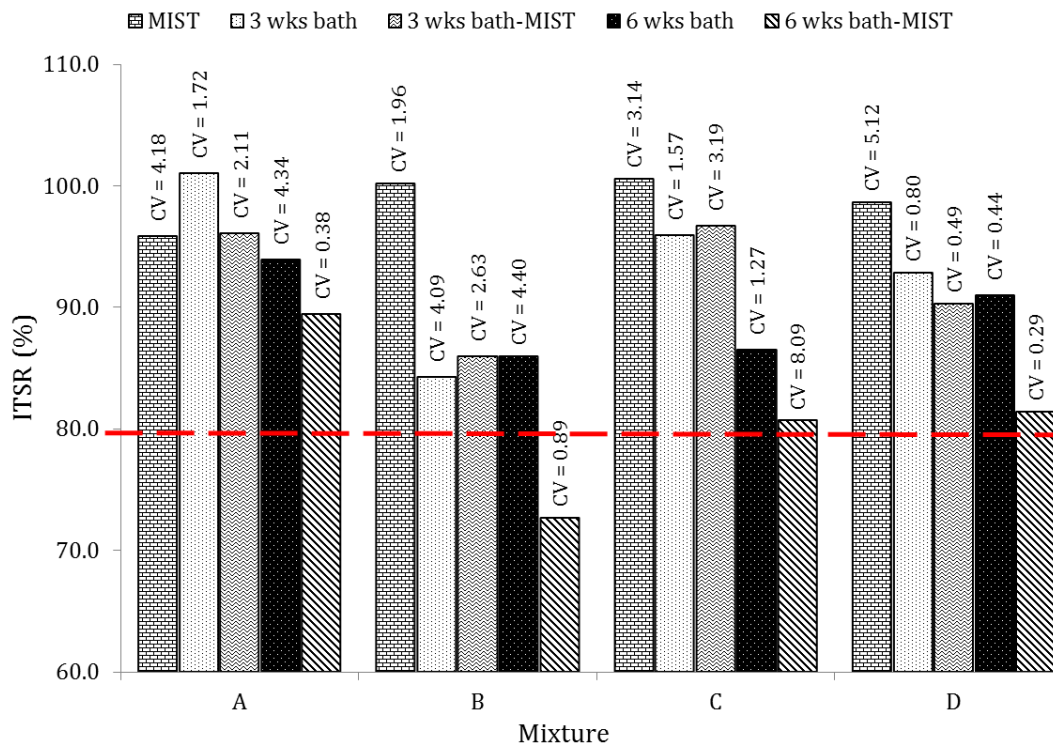


28  
 29 **FIGURE 2 Mean ITSR values for unaged (fresh) samples.**



Figure 2 shows that the tensile strength ratios of the RA mixtures, regardless of the addition of WMA, were found to be lower than the conventional HMA mixtures for the unaged samples. The addition of WMA additive appeared to improve the resistance of the RA mixtures against moisture as follows from the comparison between mixture B and D, which had the same amount of RA content but differed in terms of the addition of the WMA additive.

After field ageing, however, a different trend was observed as the ITSR values of the RA mixtures were found to be higher than those of the control HMA mixture (0% RA), as shown in Figure 3. The mechanical performance of the control mixture after moisture conditioning (0% RA) had significantly deteriorated for the samples that were collected after one year of field ageing, thus suggesting mixture A is sensitive to moisture damage. On the other hand, after field ageing, the moisture susceptibility of all RA mixtures improved significantly. Specifically, mixture B (30% RA; no WMA additive) was found to be susceptible to moisture damage both before and after field ageing; nevertheless its performance was slightly improved after ageing. Similarly, mixtures C (40% RA plus WMA additive) and D (30% RA plus WMA additive) had high tensile strength ratios before ageing, which were further improved after field ageing. In general, it was found that mixture D performed better against moisture damage compared to other mixture variants. The improvement of the ITS ratios after field ageing suggests that the RA mixtures (with and without WMA additives) underwent a curing process during field ageing that resulted to an increase in their wet tensile strength, thus exhibiting lower sensitivity to moisture damage.

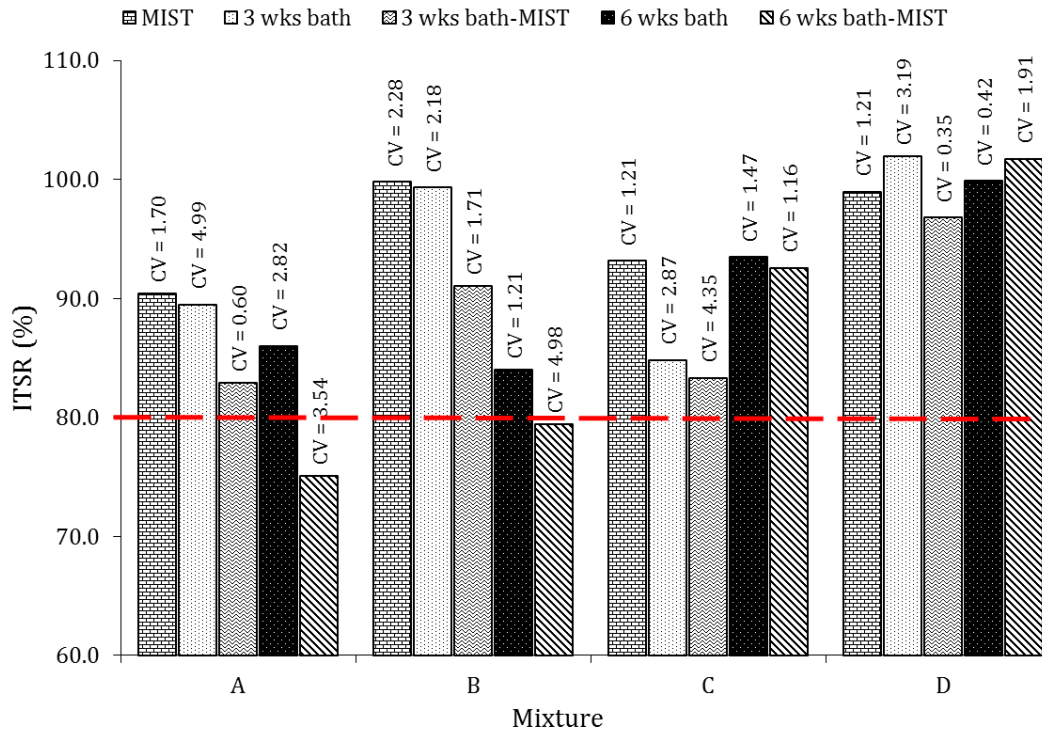

**FIGURE 3 Mean ITSR values for the field aged samples.**

Table 3 shows the reduction in strength for all mixtures after the application of the various conditioning regimes. From the results, the contributions of the short- and long-term moisture damage on the strength of the samples were quantified. The results for the samples obtained right after the construction of the test sections, show that the HMA control mixture was found to be less sensitive to both long- and short-term moisture conditioning. After three weeks

of bath conditioning a slight increase in tensile strength was observed for the unaged samples, while six weeks of bath conditioning resulted to a minor reduction in strength of about 6%. On the other hand, the RA mixtures had higher reduction in strength after bath conditioning that ranged from 4% to 16%. Among the RA mixtures, the 30% RA mixture with a WMA additive showed the best performance, while mixture B that had no WMA additive (but the same RA content of 30%) was extremely sensitive to moisture. Furthermore, it was observed that an increase in the amount of RA content, from 30 % to 40 %, did not result to great differences in the moisture susceptibility of the mixtures, as follows from the comparison between mixture C and D. With respect to the short-term moisture damage, it was observed that MiST application, without any prior bath conditioning and after three weeks in the bath, had a greater effect on the HMA mixture than on the RA mixtures regardless of the addition of WMA additive. However, after six weeks of bath conditioning the samples containing RA weakened considerably and the application of pressure cycles resulted to a high decrease in strength compared to the control mixture.


**TABLE 3 Average reduction in strength for the unaged (fresh) and aged samples**

Conditioning method	Time (wks)	Strength reduction (%)							
		Mixture A		Mixture B		Mixture C		Mixture D	
		Fresh (unaged)	Aged	Fresh (unaged)	Aged	Fresh (unaged)	Aged	Fresh (unaged)	Aged
Long-term bath conditioning	0	na	na	na	na	na	na	na	na
	3	-1.01	10.50	15.75	0.70	4.05	15.20	7.12	-1.90
	6	6.08	14.00	14.00	16.00	13.51	6.50	9.01	0.10
Long-term bath conditioning & MiST	0	4.17	9.60	-0.21	0.20	-0.58	6.80	1.32	1.00
	3	3.92	17.10	14.03	9.00	3.31	16.70	9.68	3.20
	6	10.54	24.90	27.29	20.60	19.32	7.40	18.58	-1.70
MiST application*	0	4.17	9.60	-0.21	0.20	-0.58	6.80	1.32	1.00
	3	4.93	6.60	-1.72	8.30	-0.74	1.50	2.56	5.10
	6	4.46	10.9	13.29	4.60	5.81	0.90	9.57	-1.80


\* The effect of MiST is given as the difference between bath and bath-MiST conditioning; na: not applicable

After one year in the field, however, the mixtures containing RA exhibited a lower reduction in strength compared to the control mixture after the application of the different conditioning regimes. Specifically, mixture A (0% RA) had the highest reduction in strength for all conditioning protocols (maximum strength loss was 24.90%), suggesting that the mechanical properties of the HMA mixtures deteriorated significantly during a year of service that resulted to high moisture sensitivity. Moreover, similar levels of strength reduction were observed, after only bath conditioning, for the aged samples of mixture B (30% RA; no WMA additive) compared to the unaged ones. However, the performance of mixture B, subjected to the combined protocol, was slightly improved after field ageing. Furthermore, the results demonstrated the positive effect of using WMA additives on moisture susceptibility of both unaged and field aged mixtures. Mixture C (40% RA plus WMA additive) showed a decreasing strength with increasing bath conditioning time; however it appeared to be insensitive to the application of cyclic pressure, indicating that mixture C is more probable to fail cohesively, due to the weakening of the binder, rather than adhesively. This can be attributed to the antistripping effect of the Cecabase RT 945 WMA additive, which appeared to improve the adhesion properties of the aggregate-binder systems. Mixture D (30% RA plus WMA additive), exhibited the best performance against moisture damage. The rate of strength degradation was very low, particularly after field ageing; comparable strength levels were measured after the various conditioning scenarios.

1 The aforementioned observations are depicted in Figures 4 and 5. The degradation curves  
 2 due to long- and short-term moisture induced damage mechanisms, i.e. moisture diffusion and  
 3 cyclic pore pressures, are shown. The red (or blue) curve demonstrates the effect of moisture  
 4 diffusion on tensile strength due to bath conditioning alone, while the green (or purple) curve  
 5 shows the influence of the combined conditioning protocol (bath and MiST) on tensile strength.  
 6 From the results, it can be observed that the dry strength of the control mixture increases  
 7 significantly after field ageing, in contrast to the RA mixtures that were found to have comparable  
 8 strength levels for both the unaged and aged samples. With respect to moisture damage  
 9 susceptibility, the strength of the control mixture appeared to decrease with increasing bath  
 10 conditioning. Similar observations were also made for mixture B, which did not contain a WMA  
 11 additive.

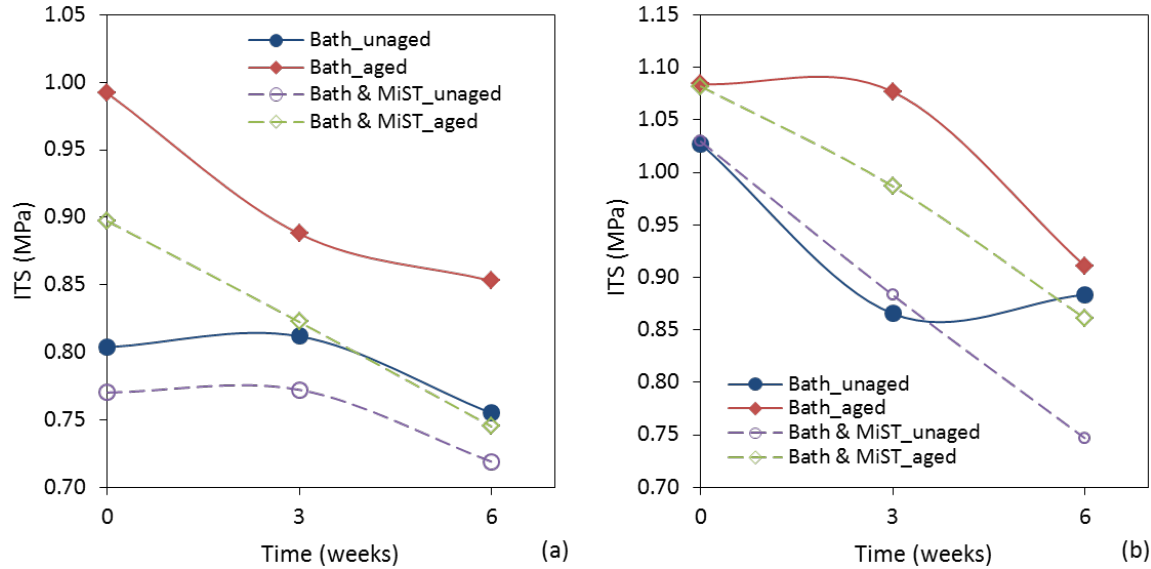

12 **FIGURE 4** Strength degradation curves due to moisture conditioning for (a) mixture A  
 13 (Control; 0% RA) and (b) mixture B (30% RA; no WMA additive).  
 14  
 15

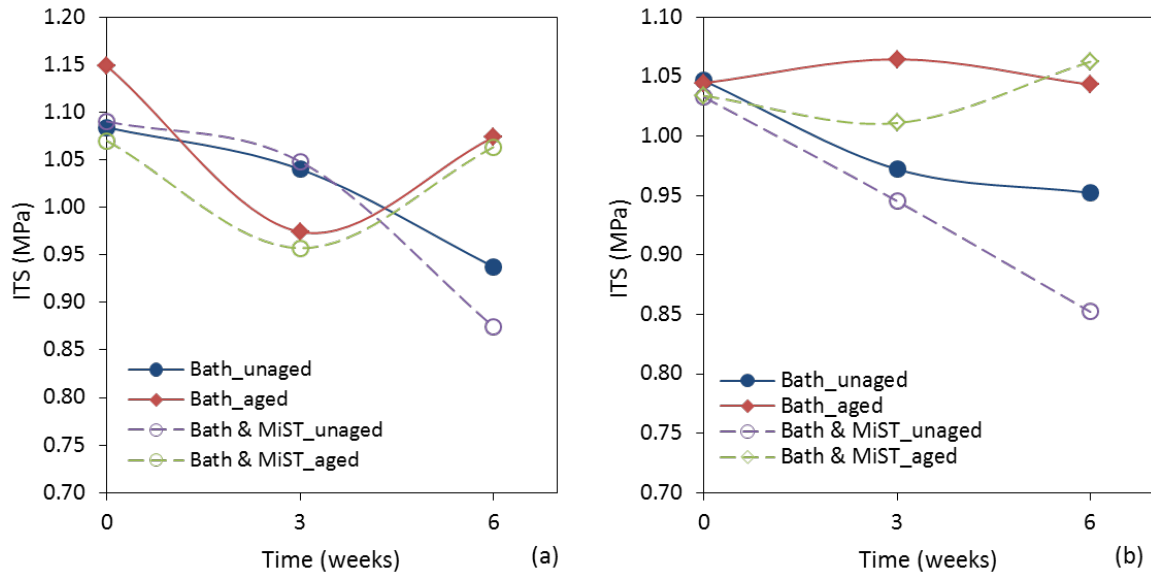

16 **FIGURE 5** Strength degradation curves due to moisture conditioning for (a) mixture C  
 17 (40% RA; WMA additive) and (b) mixture D (30% RA; WMA additive).  
 18

1  
2       Regarding the influence of short-term moisture conditioning, it was found that MiST  
3 application resulted to additional strength loss for both mixtures A and B. The graphs show that  
4 the reduction in strength, which corresponds to the influence of pore pressure cycles, increases  
5 with bath conditioning time, suggesting that moisture diffusion, degraded further the properties of  
6 the mixtures, thus resulting in a greater reduction in strength for the same amount of MIST  
7 conditioning. On the contrary, the tensile strength of the mixtures containing reclaimed asphalt  
8 and a WMA additive were not significantly affected by pore pressure application. In general, the  
9 use of WMA additive resulted to mixtures with superior performance against moisture, especially  
10 with respect to the pressure-induced damage.

## 11 **SUMMARY AND CONCLUSIONS**

12 Overall, the objective of this work was to evaluate the moisture sensitivity of mixtures containing  
13 RA and WMA additives and investigate the effect of field ageing on their moisture damage  
14 susceptibility. Four variants of a typical European SMA mixture were prepared; a control HMA  
15 mixture with 0% RA, a mixture with 30% RA and no WMA additive, a mixture with 30% RA in  
16 which a WMA additive was added, as well as a mixture with 40% RA and a WMA additive. Test  
17 sections were laid using the four mixtures and a total of 216 samples were cored after 24 hours  
18 and one year after the construction of the test sections. The field cores were conditioned in  
19 combinations of water bath immersion and cyclic pore pressures by means of the moisture  
20 induced sensitivity tester (MiST). The degradation in strength was quantified through indirect  
21 tensile strength tests. Based on the results the contributions of long- and short-term moisture  
22 damage were quantified. On the basis of this study the following conclusions can be made:

- 24
- 25       • The inclusion of RA has a great effect on mixture strength. The tensile strength of the
- 26       mixture increased with increasing RA content.
- 27       • A change in the amount of RA content, from 30% to 40%, did not create great differences
- 28       in the dry and wet ITS and ITSR values.
- 29       • The rate of strength degradation due to moisture damage was found to be lower for the
- 30       mixtures containing RA and WMA additive compared to the control mixture. The RA
- 31       mixtures, subjected to the various moisture conditioning regimes, had a lower reduction
- 32       in strength, especially after field ageing.
- 33       • The results showed that mixtures with RA content generally had higher tensile strength
- 34       than the control mixture before and after moisture conditioning. In a number of cases,
- 35       however, the RA mixtures, with and without WMA additive, did not initially meet the
- 36       standard 0.80 TSR criterion, but their TSR values were found to improve for the field
- 37       aged samples. The results suggest that the mixtures underwent a curing process in the
- 38       field that enhanced their response to moisture damage. Therefore it is recommended that
- 39       ageing considerations are made when performance testing is necessary to validate the mix
- 40       design with respect to moisture damage susceptibility.
- 41       • The use of warm mix additive increased the resistance to moisture damage induced both
- 42       by bath and bath-MIST conditioning. A comparison between mixture B and D, which had
- 43       the same amount of RA and only differed with respect to the addition of WMA additive,
- 44       clearly demonstrates the positive effect of WMA additive on the moisture damage
- 45       susceptibility of the mixtures.
- 46       • The results indicate that the two moisture damage inducing mechanisms had diverse
- 47       effects on strength degradation. Mixtures with variable composition, but the same
- 48       morphological characteristics (air void content, aggregate gradation etc.) can be
- 49       susceptible to long- or short-term conditioning to a lesser or greater degree. Therefore

1 considerations of both moisture damage mechanisms should be made when evaluating  
2 asphalt mixtures for their susceptibility to moisture damage.

3

#### 4 **ACKNOWLEDGEMENTS**

5 The research study was carried out in the framework of the CEDR Transnational Road Research  
6 Programme project “Effects on Availability of Road Network (EARN)”. The funding for this  
7 project was provided by the national road administrations of Denmark, Finland, Germany,  
8 Ireland, Netherlands and Norway.

9

#### 10 **REFERENCES**

- 11 1. Hicks, R.G. NCHRP Synthesis of Highway Practice 175: Moisture Damage in Asphalt  
12 Concrete. Washington D.C.: TRB & National Research Council, 1991.
- 13 2. Kringos, N. and A. Scarpas. Raveling of asphaltic mixes due to water damage:  
14 Computational identification of controlling parameters. *Transportation Research Record:  
15 Journal of the Transportation Research Board*, Vol. 1929, 2005, pp. 79–87.
- 16 3. Ruan, Y.R., R. Davison and C.J. Glover. An investigation of asphalt durability:  
17 Relationships between ductility and rheological properties for unmodified asphalts.  
18 *Petroleum Science and Technology*, Vol. 21, No. 1-2, 2003, pp. 231-254.
- 19 4. Xiao, F., J. Jordan and S.N. Amirkhanian. Laboratory investigation of moisture damage  
20 in warm-mix asphalt containing moist aggregate. *Transportation Research Record:  
21 Journal of the Transportation Research Board*, Vol. 2126, No.1, 2009, pp. 115-124.
- 22 5. Kanitpong, K., N. Charoentham and S. Likitlersuang. Investigation on the effects of  
23 gradation and aggregate type to moisture damage of warm mix asphalt modified with  
24 Sasobit. *International Journal of Pavement Engineering*, Vol. 13, No. 5, 2012, pp. 451-  
25 458.
- 26 6. Xiao, F., W. Zhao, T. Gandhi and S.N. Amirkhanian. Laboratory investigation of  
27 moisture susceptibility of long-term saturated warm mix asphalt mixtures. *International  
28 Journal of Pavement Engineering*, Vol. 13, No. 5, 2012, pp. 401-414.
- 29 7. Kavussi, A. and L. Hashemian. Laboratory evaluation of moisture damage and rutting  
30 potential of WMA foam mixes. *International Journal of Pavement Engineering*, Vol. 13,  
31 No. 5, 2012, pp. 415-423.
- 32 8. Hurley, G.C. and B.D. Prowell. *Evaluation of Sasobit for use in warm mix asphalt*.  
33 NCAT report, 05-06, National Center for Asphalt Technology, 2005.
- 34 9. McDaniel, R. and R.M. Anderson. *Recommended use of reclaimed asphalt pavement in  
35 the Superpave mix design method: Technician's manual*. NCHRP Report 452,  
36 Transportation Research Board, National Research Council, 2001.
- 37 10. Copeland, A. *Reclaimed asphalt pavement in asphalt mixtures: state of the practice*,  
38 Report No. FHWA-HRT-11-021, Federal Highway Administration, Washington D.C.,  
39 2011.
- 40 11. Aurangzeb, Q., I.L. Al-Qadi, I.M. Abuawad, W.J. Pine and J.S. Trepanier. Achieving  
41 desired volumetrics and performance for mixtures with high percentage of reclaimed  
42 asphalt pavement. *Transportation Research Record: Journal of the Transportation  
43 Research Board*, Vol. 2294, No. 1, 2012, pp. 34-42.

- 1 12. Hajj, E.Y., P.E. Sebaaly and R. Shrestha. Laboratory evaluation of mixes containing  
2 recycled asphalt pavement (RAP). *Road Materials and Pavement Design*, Vol. 10, No. 3,  
3 2009, pp. 495-517.
- 4 13. He, G.P. and W.G. Wong. Effects of moisture on strength and permanent deformation of  
5 foamed asphalt mix incorporating RAP materials. *Construction and Building Materials*,  
6 Vo. 22, No. 1, 2008, pp. 30-40.
- 7 14. West, R., J.R. Willis and M. Marasteanu. Improved mix design, evaluation and materials  
8 management practices for hot mix asphalt with high reclaimed asphalt pavement content.  
9 NCHRP Report 752, Transportation Research Board, Washington, D.C., 2013.
- 10 15. Zhao, S., B. Huang, X. Shu, X. Jia and M. Woods. Laboratory performance evaluation of  
11 warm-mix asphalt containing high percentages of reclaimed asphalt pavement.  
12 *Transportation Research Record: Journal of the Transportation Research Board*, Vol.  
13 2294, No. 1, 2012, pp. 98-105.
- 14 16. Shu, X., B. Huang, E.D. Shrum and X. Jia. Laboratory evaluation of moisture  
15 susceptibility of foamed warm mix asphalt containing high percentages of RAP.  
16 *Construction and Building Materials*, Vol. 35, 2012, pp. 125-130.
- 17 17. Tabaković, A., C. McNally, A. Gibney, C. Nicholls, K. Mollenhauer, A. Varveri and S.  
18 Avgerinopoulos. *Report of laboratory and site testing for site trials*. EARN deliverable  
19 D8, 2014.
- 20 18. Nicholls, C., M. Wayman, K. Mollenhauer, C. McNally, A. Tabakovic, A. Varveri, S.  
21 Cassidy, R. Shahmohammadi and K. Gilbert. Effect of using of reclaimed asphalt and/or  
22 lower temperature asphalt on the availability of the road network. *Proceedings of the*  
23 *transport research arena (TRA) conference*, 2104, pp. 1-10.
- 24 19. InstroTek Inc. Moisture Induced Sensitivity Test Operators Guide, Version 10. Raleigh  
25 N.C., 2012.
- 26 20. Varveri, A., S. Avgerinopoulos and A. Scarpas. Experimental Evaluation of Long- and  
27 Short-Term Moisture Damage Characteristics of Asphalt Mixtures. *Road Materials and*  
28 *Pavement Design*, 2105, <http://dx.doi.org/10.1080/14680629.2015.1066705>.  
29