

## Fatigue Testing of Transversely Prestressed Concrete Decks

Lantsoght, Eva; van der Veen, Cor; Koekkoek, Rutger; Sliedrecht, Henk

**DOI**

[10.14359/51715569](https://doi.org/10.14359/51715569)

**Publication date**

2019

**Document Version**

Accepted author manuscript

**Published in**

ACI Structural Journal

**Citation (APA)**

Lantsoght, E., van der Veen, C., Koekkoek, R., & Sliedrecht, H. (2019). Fatigue Testing of Transversely Prestressed Concrete Decks. *ACI Structural Journal*, 116(4), 143-153. <https://doi.org/10.14359/51715569>

**Important note**

To cite this publication, please use the final published version (if applicable).  
Please check the document version above.

**Copyright**

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

**Takedown policy**

Please contact us and provide details if you believe this document breaches copyrights.  
We will remove access to the work immediately and investigate your claim.

# FATIGUE TESTING OF TRANSVERSELY PRESTRESSED CONCRETE DECKS

Eva O. L. Lantsoght<sup>1,2,3</sup>, Cor van der Veen<sup>1</sup>, Rutger Koekkoek<sup>4</sup>, and Henk Sliedrecht<sup>5</sup>

<sup>1</sup> Concrete Structures, Delft University of Technology, Delft, The Netherlands

<sup>2</sup> Universidad San Francisco de Quito, Quito, Ecuador

<sup>3</sup> Adstren, Quito, Ecuador

<sup>4</sup> BAM Infraconsult, Gouda, the Netherlands

<sup>5</sup> Rijkswaterstaat, Ministry of Infrastructure and the Environment, Utrecht, the Netherlands

**Biography:** ACI member **Eva Lantsoght** is a full professor at Universidad San Francisco de Quito, a researcher at Delft University of Technology, The Netherlands, and a structural engineer at Adstren, Ecuador. She is a member of ACI 445-0D Shear Databases, ACI-ASCE 421 Design of Reinforced Concrete Slabs, ACI 342 Evaluation of Concrete Bridges and Bridge Elements, and an associate member of ACI 437 Strength Evaluation of Existing Concrete Structures, and ACI-ASCE 445 Shear and Torsion.

**Cor van der Veen** is an associate professor at Delft University of Technology, Delft, The Netherlands. He received his MSc and PhD from Delft University of Technology. He is a member of various National Committees. His research interests include (very) high strength (steel fiber) concrete, concrete bridges and computational mechanics.

**Rutger Koekkoek** is a maritime engineer at BAM Infraconsult. Formerly he was a researcher at Delft University of Technology where he prepared and executed several outdoor load tests and did fatigue tests on transversally precast bridge decks and shear tests on prestressed beams.

**Henk Sliedrecht** is a senior consultant at Rijkswaterstaat, Ministry of Infrastructure and Watermanagement, Utrecht, The Netherlands. He received his MSc from Delft University of Technology. His research interests include the assessment of existing concrete bridges in particular methods of analysis and standards for structural safety.

## ABSTRACT

In the Netherlands, slab-between-girder bridges with prestressed girders and transversely prestressed decks in between the girders require assessment. Static testing showed that compressive membrane action increases the capacity of these structures and that the decks fail in punching shear. The next question is if compressive membrane action also increases the capacity of these decks under repeated loads. Therefore, the same half-scale bridge structure as used for the static tests was subjected to repeated loads at different fractions of the maximum static load, different loading sequences, and for single and double concentrated loads. A relationship between the load level and number of cycles at failure ( $S-N$  curve) for the assessment of these bridges is proposed, but the influence of the loading sequence was not successfully quantified yet. The conclusion of the experiments is that compressive membrane action enhances the punching capacity of transversely prestressed thin decks subjected to repeated loads.

**Keywords:** Bridge evaluation; Compressive membrane action; Concrete bridges; Fatigue; Fatigue testing; Laboratory testing; Prestressed concrete; Punching shear.

## INTRODUCTION

During the decades following the Second World War, the Dutch road network underwent rapid expansion. Many existing bridges in the highway network have now been in service for fifty years or more. These bridges were designed according to the codes of that era. Nowadays, these bridges should be assessed according to the live loads as prescribed by the current code NEN-EN 1991-2:2003 (CEN, 2003). This code reflects current traffic loads and volumes, which have increased over the past decades. On the other hand, the resulting design capacity for shear and punching shear in the Eurocode NEN-EN 1992-1-1:2005 (CEN, 2005) is lower than the design shear and punching shear capacity that was prescribed by the Dutch National codes. For reinforced concrete slab bridges, the shear capacity is often found to be insufficient upon assessment according to the current codes (Lantsoght et al., 2013). For existing slab-between-girder bridges consisting of post-tensioned girders and thin transversely prestressed concrete decks, the punching shear capacity is often found to be insufficient upon assessment according to the current codes. The span to depth ratio of the decks in these bridges is larger than 10, so that the contributions of the shear deformations are negligible, and the deck can be considered as thin.

The subset of slab-between-girder bridges in the Netherlands consists of about seventy bridges (Koekkoek et al., 2018). The punching shear capacity from NEN-EN 1991-2:2003 (CEN, 2003) is an empirical expression, derived from tests on slab-column connections (Mitchell et al., 2005; Regan and Braestrup, 1985). These test elements have a different structural behaviour from the slabs in slab-between-girder bridges. In these structures, additional sources of capacity can increase the capacity; in particular compressive membrane action, which can develop when sufficient lateral restraint exists (Amir, 2014; Hon et al., 2005; Kirkpatrick et al., 1986; Kuang and Morley, 1992; 1993; Taylor et al., 2007; Tong and Batchelor, 1972). The transverse prestressing in these deck slabs further enhances the capacity (Marshe and Green, 1999).

To quantify the effect of compressive membrane action and transverse prestressing for slab-

1 between-girder bridges, Amir (Amir, 2014) carried out static tests on a half-scale model of an  
2 existing slab-between-girder bridge (Amir et al., 2016). A test specimen was built consisting of four  
3 prestressed girders, prestressed concrete transverse beams, and a transversely prestressed concrete  
4 deck (Amir et al., 2016), see **Fig. 1**. The 19 experiments on this specimen quantified the ultimate  
5 capacity of these decks as part of a realistic bridge structure. The variables in the experiments were  
6 the position of the load, the details of the joint between the deck and girders, the difference between  
7 a single and a double wheel load, and the amount of transverse prestressing. The deck failed in  
8 punching shear for all experiments. The test results were compared to the mean punching shear  
9 capacity from prENV 1992-1-1:2002 (Walraven, 2002), which lies at the basis of the design  
10 punching shear capacity in NEN-EN 1992-1-1:2005 (CEN, 2005). This comparison showed an  
11 average tested-to-predicted capacity of 2.32 (Amir, 2014).

12 To consider the beneficial effect of compressive membrane action for the assessment of  
13 existing Dutch slab-between-girder bridges in assessment, it needs to be proven first that this  
14 mechanism also occurs under repeated loading. He (1992) also raised this concern. For this purpose,  
15 fatigue tests are carried out on the same half-scale model of an existing slab-between-girder bridge  
16 as used for the static tests. Practicing engineers have also reported their concerns regarding the  
17 fatigue capacity of bridge slabs (Low, 2011).

18

## 19 **RESEARCH SIGNIFICANCE**

20 Laboratory experiments are typically carried out on structural members and not on structural  
21 systems. For fatigue testing, previous research has focused more on materials subjected to cyclic  
22 loading than structural elements. The presented fatigue experiments on a half-scale model of a  
23 complete bridge structure give insight in the behavior and capacity of slab-between-girder  
24 prestressed concrete bridges, and in particular the effect of fatigue on compressive membrane  
25 action. As such, the presented experiments provide a novel insight in the behavior of bridge systems

under fatigue loading. The results can be used for an improved assessment of existing slab-between-girder bridges.

### FATIGUE STRENGTH OF CONCRETE STRUCTURES

The effect of fatigue on concrete structures is typically first studied based on the effect of cycles of loading on the material properties (CEB Committee GTG 15, 1988; Hordijk, 1991): concrete compressive (Bennett and Muir, 1967; Lantsoght et al., 2016) and tensile strength (Hordijk et al., 1995; Hsu, 1981; Wang and Song, 2011; Yu et al., 2014), and reinforcing and prestressing steel strength (Mander et al., 1994; Tilly, 1979; Tilly, 1984). The reduction of the material strength is expressed as a function of the number of applied cycles, which results in the so-called Wöhler-curve or  $S$ - $N$  curve (with  $S$  the fraction of the static strength and  $N$  the number of cycles). These relations are developed based on experimental results. Some material models for fatigue assume an endurance limit (Arora and Singh, 2016; Lee and Barr, 2004; Saucedo et al., 2013; Yin and Hsu, 1995), which means that no further reduction of  $S$  occurs after a certain number of cycles (for example:  $2 \times 10^6$ ).

Experiments on structural elements under fatigue loading representative of traffic loads on bridges are not very common. The influence of cycles of loads that represent seismic actions has been studied experimentally (El-Bahy et al., 1999; Mander et al., 1994; Manfredi and Pecce, 1997; Marthong et al., 2016; Thomson et al., 1998). Such experiments use loads that result in stress reversals, a situation which is different from what happens in a bridge subjected to repeated traffic loads (Elfgren, 2015; Forrest et al., 2010; Schlafli and Bruhwiler, 1998).

In the literature, fatigue experiments on isolated structural members are reported. Of interest here are the experiments on shear-critical structures. Experiments are reported on the fatigue life of deep beams (Isojeh et al., 2017; Teng et al., 1998), the fatigue life of shear-critical concrete beams (Gallego et al., 2014; Hawkins, 1974; Hegger et al., 2015; Liu et al., 2018; Muller and Dux, 1994; Patrick M. Bachman et al., 1987; Teworte and Hegger, 2011; Teworte et al., 2015; Tien and Clyde,

1958; Ueda, 1983; Yuan et al., 2017), and the fatigue life of shear-critical slabs (Fujiyama et al., 2008). The tests on slabs showed that the fatigue life under a moving load is lower than for a load that is repeatedly applied at the same position (Sonoda and Horikawa, 1982). For partially prestressed concrete beams (Harajli and Naaman, 1985; Naaman and Founas, 1991; Shahawi and Batchelor, 1986; Xin et al., 2015; Xin et al., 2017; Zeng et al., 2014), experiments showed that the failure mode could change from flexural failure to shear failure, which led to thorough research on this topic.

Furthermore, experiments are used to assess the fatigue life of strengthening measures on structural elements (Noël and Soudki, 2015; Oudah and El-Hacha, 2013), of new sections or materials (Larson et al., 2005; Tong et al., 2016; Younes et al., 2017; Zhang et al., 2016a), and of elements with material damage or degradation (Ahmed et al., 1998; Salem, 2013; Zhang et al., 2016b). Probabilistic approaches can address the large scatter on the results from fatigue tests (Al-Zaid and Nowak, 1988; Casas and Crespo-Minguillon, 1998; Juan, 2000; Rodrigues et al., 2013).

## EXPERIMENTAL INVESTIGATION

### Test setup

The fatigue experiments were carried out on the same test setup as the static tests. To be able to carry out additional fatigue tests, the original central deck was removed and a new deck was cast. The overall geometry of the test bridge is shown in **Fig. 1**. All dimensions are modelled after an existing bridge. The overall dimension of the specimen was 6.4 m (21 ft) by 12 m (39 ft). The precast girders have a span length of 10.95 m (36 ft), height of 1.3 m (4.3 ft), and center-to-center distance of 1.8 m (5.9 ft) and were made by a Dutch fabricator of precast prestressed concrete girders. The cast-in-situ deck panels have a thickness of 100 mm (4 in) and width of 1.05 m (3.4 ft). The cast-in-situ transverse beams have a rectangular cross-section of 810 mm × 350 mm (32 in × 14 in). All details of the original setup are discussed in (Amir, 2014; Amir et al., 2016).

The sequence of building the test setup was as follows: the girders were brought from the

fabricator, the formwork for the transverse beams was built, the transverse beams were cast, the formwork for the deck panels was built, the deck panels were cast, the steel frame for testing was positioned over the model bridge, and finally the transverse beams and deck were prestressed. To carry out the additional fatigue tests, slab panel B (see **Fig. 1b**) was removed after applying a saw cut, formwork was built, and a new slab was cast again. **Fig. 2a** shows the setup before casting the new deck and **Fig. 2b** shows the complete setup with the new slab panel B.

## Material properties

High strength concrete is used in the scale model to be representative of the measured compressive strength in an existing slab-between-girder bridge ( $f_{cm,cube} = 98.8 \text{ MPa} = 14,330 \text{ psi}$  in the deck, determined on concrete core samples, see Amir (2014)). The high compressive strength in the existing bridge is the result of ongoing cement hydration. Given the casting sequence in the laboratory of the elements of the setup, and the fact that the prestressed girders were fabricated by a prefabricator, the different values of the compressive strength are discussed here.

The concrete compressive strength of the girders at 273 days (after finishing the static experiments) as measured on 150 mm (6 in) cubes is  $f_{cm,cube} = 90 \text{ MPa}$  (13,050 psi) (Amir, 2014). The average splitting tensile strength of the concrete is  $f_{ctm,cube} = 6.3 \text{ MPa}$  (914 psi) at 273 days.

The concrete compressive strength of the transverse beams is  $f_{cm,cube} = 71 \text{ MPa}$  (10,300 psi) measured at 28 days (Amir, 2014).

Cubes that were cast along with the deck slab are tested at different points in time. At 28 days,  $f_{cm,cube} = 75 \text{ MPa}$  (10,880 psi) for the original decks slab (Amir, 2014), and  $f_{cm,cube} = 68 \text{ MPa}$  (9,863 psi) measured at 28 days for the newly cast slab panel B. The average splitting tensile strength is  $f_{ctm,cube} = 5.4 \text{ MPa}$  (783 psi) for the original deck slab at 28 days, and  $f_{ctm,cube} = 5.5 \text{ MPa}$  (798 psi) for the newly cast slab panel B at 28 days. Details about the strength development of the concrete in the original test setup are given in (Amir, 2014). For the concrete of the newly cast deck panel B, the results of cube tests at 56 days are  $f_{cm,cube} = 77 \text{ MPa}$  (11,170 psi) and  $f_{ctm,cube} = 5.7 \text{ MPa}$



(827 psi), and after 188 days  $f_{cm,cube} = 78$  MPa (11,310 psi) and  $f_{ctm,cube} = 5.9$  MPa (856 psi). The results of the concrete compressive strength for the cubes tested at the day of an experiment are given in **Table 1** for the static tests and in **Table 2** for the fatigue tests.

The reinforcement steel in the girders is B500A for bars with a diameter  $\leq 6$  mm (0.236 in  $\approx$  #2 bars) and B500B for bars with diameter  $\geq 8$  mm (0.315 in  $\approx$  #3 bars), which has a yield strength of  $f_y \geq 500$  MPa (73 ksi). For the reinforcement steel of the elements cast in the laboratory, the yield strength is measured on steel samples in the laboratory as  $f_y = 525$  MPa (76 ksi) and the ultimate tensile strength is  $f_t = 580$  MPa (84 ksi). The prestressing steel in the girders is Y1860S (prestressing strands), which has a characteristic tensile strength  $f_{pk} = 1,860$  MPa (270 ksi) and the prestressing steel in the slab and transverse beam is Y1100H (prestressing bars), which has a characteristic tensile strength  $f_{pk} = 1,100$  MPa (160 ksi).

## Reinforcement

In total, the deck has 30 prestressing ducts with a diameter of 40 mm (1.6 in) and a center-to-center distance of 400 mm (16 in). In the newly cast slab panel B, at two positions over the entire span length, ducts with a diameter of 30 mm (1.2 in) and a spacing of 300 mm (12 in) are used to study the influence of the duct spacing, see **Fig. 3b**. The deck is post-tensioned with unbonded prestressing bars, to vary the level of transverse prestressing, which was a parameter studied in the first series of experiments (Amir et al., 2016). For the fatigue tests, the average compressive stress in the concrete deck from the transverse prestressing is 2.5 MPa (363 psi), which is the same level of transverse prestressing as used in an existing bridge. The prestressing bars in the deck have a diameter of 15 mm (0.6 in). The bars are anchored with steel plates of 100 mm  $\times$  170 mm  $\times$  20 mm (3.9 in  $\times$  6.7 in  $\times$  0.8 in).

For the reinforcing steel, the longitudinal reinforcement in the slab is diameter 6 mm (0.236 in  $\approx$  #2) bars spaced 200 mm (7.9 in) on center top and bottom (5 bars in total per slab panel), and the transverse reinforcement is diameter 6 mm (0.236 in  $\approx$  #2) bars spaced 250 mm (9.8 in) on

center top and bottom (61 bars in total per slab panel). The clear cover to the mild steel is 7 mm (0.28 in). The details of the reinforcement and prestressing of the girders, deck, and transverse beams are given in (Amir, 2014).

#### **Instrumentation**

During the experiments, sensors measured the deflections, crack widths, and movement in the joint of the bridge setup. The specimens were instrumented with 16 LVDTs and 14 laser distance finders. In total, 46 load cells measure the force in the prestressing bars in the deck and the transverse beams. The deflection from the top of the specimen is measured with eight laser distance finders and four LVDTs, whereas the deflection at the bottom of the specimen is measured with four laser distance finders. Two LVDTs monitor crack width after the occurrence of the crack in the length direction. The remaining LVDTs and lasers follow the joint and movement at the supports of the prestressed girders. On the original deck, two experiments were carried out for which acoustic emission sensors were used as part of a research project on acoustic emission measurements.

#### **Loading procedure**

For the tests on the original test setup, the load is applied with a hydraulic jack on a steel plate of 200 mm × 200 mm (7.9 in × 7.9 in). This size is half-scale of the wheel print of the design tandem used in live Load Model 1 of NEN-EN 1991-2:2003 (CEN, 2003). The design tandem has two axles at a distance of 1.2 m (4 ft) with two wheel prints at 2 m (6.6 ft) distance. The load plate is 20 mm (0.8 in) thick. For the fatigue tests on the new deck, a steel plate of 115 mm × 150 mm × 20 mm (4.5 in × 5.9 in × 0.8 in) is used. This size is half-scale of the wheel print used in the fatigue load model in the Netherlands. This load model uses the same geometry of the design tandem as Load Model 1, but uses a smaller wheel print. Between the deck and the load plate, a layer of rubber of 10 mm (0.4 in) thick is placed to avoid stress concentrations. For the static reference tests, the load was applied with a monotonic loading protocol (**Fig. 4a**), and at certain load levels the load was kept constant to inspect the specimen and mark cracks. The static tests were performed in a

displacement-controlled way. For two experiments with a low number of cycles, three cycles for each predetermined load level were carried out, as typical for load tests (Lantsoght et al., 2017), see **Fig. 4b**. For the fatigue tests, the load was cycled between a low load level  $F_{low}$  and an upper load level  $F_{up}$ , with  $F_{low} = 0.1F_{up}$ . The load is applied as a sinus function (see excerpt of 5 seconds in **Fig. 4c**) with a frequency of 1 Hz. The influence of the frequency is not studied in these experiments, and is still a topic of discussion (Lantsoght et al., 2016). The fatigue tests were performed in a force-controlled way. These tests ran almost continuously, and were only paused at predetermined numbers of cycles, so that the researchers could mark the cracks and report the crack development.

## EXPERIMENTAL RESULTS AND DISCUSSION

### Test results and failure modes

In total, 19 static tests (BB1 through BB19) were carried out on the original setup, and these experiments are all reported elsewhere (Amir et al., 2016). Subsequently, two tests with a limited number of cycles were carried out (**Fig. 4b**) (BB17 and BB18), and then two fatigue tests were carried out on the original setup (BB23 and BB24). On the new deck, eight experiments in total were carried out: five dynamic tests (four with a single load and one with a double load; BB26, BB28, BB29, BB30, and BB32) and three static tests (BB25, BB27, and BB31). An overview of the number of the experiments is shown in **Fig. 3a** for the original setup and **Fig. 3b** for the setup with the new slab panel B. For the study of the effect of fatigue loading, four static experiments from the original series (BB1, BB2, BB7, and BB19) with a transverse prestressing of 2.5 MPa (363 psi) are analyzed together with the new experiments. Table 1 gives an overview of the main properties of the static tests. In this table, the failure load is given as  $P_{max}$  and the average cube concrete compressive strength measured on concrete at the day of testing is  $f_{cm,cube}$ . The size of the loading plate is indicated for reference as well.

Table 2 gives an overview of all fatigue tests. BB17 and BB18 were tested under three

cycles per load level as part of the research on the use of acoustic emission measurements. BB24 did not fail after 1,500,000 cycles and was then subjected to a static test of which the result is given in Table 1. For the fatigue tests in which the maximum load  $F$  was varied, the different load levels and their respective number of cycles  $N$  are reported separately in Table 2. The values of  $F/P_{max}$  are the ratio of the applied maximum load in the fatigue test  $F$  to the maximum load in the corresponding static test  $P_{max}$  as reported in **Table 1**. For experiments that lasted more than a day, Table 2 gives the range of ages of the concrete between the start of the test and the end of the test, and the cube concrete compressive strength  $f_{cm,cube}$  tested at the start of the test and at the end of the test. The size of the loading plate is indicated as reference as well.

The failure mode for all experiments is punching shear, either brittle punching (BP) or flexural punching (FP). The brittle punching failure mode is characterized by a sudden failure, whereas the flexural punching is characterized by a plateau in the load-deflection diagram before punching occurs. **Fig. 5** shows photographs of the specimens after failure.

All details of these experiments and the development of the cracks are given in the experimental report (van der Veen and Bosman, 2014). An example of the development of cracks as drawn for each experiment is shown in **Fig. 6** for a selection of the predetermined number of cycles at which cracks were registered. The existing cracks are shown in black, and the newly observed cracks are shown in red.

### **Distance between prestressing strands**

In the existing bridge after which the test setup is modeled, the difference between the transverse prestressing varies between 650 mm (26 in) and 800 mm (31 in). In the laboratory setup for the first series of experiments, the most unfavorable situation of 800 mm (31 in) was selected as a reference, resulting in 400 mm (16 in) on the 1:2 scale model. In the newly cast deck slab panel B, the influence of the distance was studied, and a spacing of 300 mm (12 in) was tested as well.

For the static tests, the results of BB25 with 300 mm (12 in) spacing with  $P_{max} = 329.9$  kN

(74 kip) can be compared to the results of BB27 ( $P_{max} = 364.6 \text{ kN} = 82 \text{ kip}$ ) and BB31 ( $P_{max} = 333.0 \text{ kN} = 75 \text{ kip}$ ), which gives an average of  $P_{max,avg} = 348.8 \text{ kN}$  (78 kip), for a spacing of 400 mm (16 in). In conclusion, for the static tests, the influence of the distance between the transverse prestressing bars on the failure load is limited.

For the fatigue tests, the results of BB26 with 300 mm (12 in) spacing can be analyzed. In this test, failure occurred after 1,405,337 cycles with  $F = 165 \text{ kN}$  (37 kip). A comparable test is BB28 with 400 mm (16 in) spacing between the ducts. In BB28, 1,500,000 cycles with  $F = 165 \text{ kN}$  (37 kip) were followed by 1,000,000 cycles with 200 kN (45 kip), and ultimately 7,144 cycles with 240 kN (54 kip). This result seems to indicate that a shorter distance between the prestressing ducts is less favorable than a larger distance. This observation is contradictory to the original assumptions followed when designing the test setup. However, to come to a conclusion on the effect of duct spacing on fatigue strength of the concrete decks, more experiments are necessary, because the scatter on fatigue tests is large.

#### **Sequence of load levels**

For the fatigue tests, the influence of the sequence of load levels was studied by comparing experiments with high-to-low load levels to experiments with low-to-high load levels. In BB32, the load was first 10,000 cycles at 240 kN (54 kip). Then, the load was reduced to 200 kN (45 kip), and the deck punched after 272,548 cycles. In BB28, on the other hand, the first load level was 165 kN (37 kip) with 1,500,000 cycles, then 200 kN (45 kip) in 1,000,000 cycles, and then 240 kN (54 kip) in 7,144 cycles. This observation seems to indicate that a higher load level followed by a lower load level leads to a lower fatigue resistance than a lower load level followed by a higher load level. Given the large scatter on fatigue tests, however, the currently presented two experiments do not provide sufficient information to draw conclusions on the sequence of load levels. Therefore, it is recommended to investigate this parameter and thus the validity of Miner's rule with additional experiments. This influence is the topic of future research.

2 For the static load tests, the effect of using a single wheel load versus a double wheel load is  
3 discussed in (Amir, 2014). For the tests with a double load, failure occurred by punching of one of  
4 the loads through the slab. The maximum load on the two wheel prints combined is on average 1.48  
5 times the load on a single wheel print.

6 For the fatigue tests, only one experiment with double wheel prints is available: BB30. In  
7 this experiment, the load was applied at load levels of  $F/P_{max} = 0.58, 0.5, 0.58, 0.67$ , and  $0.75$ . The  
8 last load level is higher than any of the load levels used in the experiments with a single load. The  
9 sequence of load levels is also different. Therefore, a direct comparison with a similar experiment  
10 with a single load is not possible. It can only be remarked that the overall trend is similar when one  
11 or two loads are used.

Table 2 shows that for BB24, BB28, B29, BB30, and BB32, different load levels were used if failure did not occur after the first load level, resulting in a variable amplitude loading. For the analysis and development of the  $S-N$  curve, a conservative approach is used to take these results into account. BB28 was subjected to 2,507,144 cycles in total: 1,500,000 at  $F/P_{max} = 0.48$ , 1,000,000 at  $F/P_{max} = 0.58$ , and 7,144 at  $F/P_{max} = 0.7$ . It is conservative to assume that the specimen would have resisted 2,507,144 cycles at  $F/P_{max} = 0.48$ , 1,007,144 cycles at  $F/P_{max} = 0.58$ , and 7,144 cycles at  $F/P_{max} = 0.7$ . For BB30, where  $F/P_{max} = 0.58$  is applied twice, the results for the two applications of the same load ratio are summed. **Fig. 7** shows the resulting  $S-N$  curve. The 16 datapoints on this curve are the 17 entries in Table 2, without the first load level of BB30 as explained previously. The first two experiments in which three cycles of different load levels were used as part of the research on acoustic emission measurements are shown as “AE tests” in **Fig. 7**. The results of runout tests are indicated as such in **Fig. 7**. The results for the load level at which the

slab punched, as well as the results from BB23 and BB26 in which failure occurred for the first load level that was tested, are indicated as “failure” in **Fig. 7**. The results show a clear trend: the number of cycles to failure increases as the ratio  $S = F/P_{max}$  decreases, as expected for fatigue testing.

The average line in the  $S$ - $N$  curve is found using the linear least squares approximation:

$$S = -0.062 \log N + 0.910 \quad (1)$$

The 5% lower bound curve is:

$$S = -0.062 \log N + 0.812 \quad (2)$$

The 95% upper bound curve is:

$$S = -0.062 \log N + 1.008 \quad (3)$$

**Fig. 7** shows the lines of the average, the 5% lower bound, and the 95% upper bound. From the expression of the average, Eq. (1), the fatigue strength at 1 million cycles is 54% of the static strength, 48% at 10 million cycles, and 41% at 100 million cycles. These results are similar to other fatigue tests of structural concrete and the fatigue resistance of concrete under compression. As such, the results show that compressive membrane action which was found to act as an enhancement for the punching shear capacity during static tests is also activated during fatigue loading of concrete slab-between-girder bridges.

## SUMMARY AND CONCLUSIONS

As a result of the introduction of the new Eurocodes, existing slab-between-girder prestressed concrete bridges in the Netherlands that were designed according to national codes require assessment. Previous research found that the maximum load on the transversely prestressed concrete decks in these bridges is larger than predicted by the governing codes as a result of compressive membrane action. To be able to apply this result to the assessment of these bridges, it must be shown that compressive membrane action occurs when transversely prestressed concrete decks are subjected to fatigue loading.

1 To study the effect of fatigue loading on compressive membrane action, a half-scale bridge  
2 was built in the laboratory. In total, four static tests were carried out in addition to the available  
3 static tests from the previous research, as well as two tests with three cycles per load level, and  
4 seven fatigue tests. All tests resulted in a punching shear failure.

5 The influence of the distance between the prestressing ducts was studied, and was found to  
6 be of minor importance. Similar trends for the behavior of slabs under single wheel loads as for  
7 slabs under double wheel loads were observed. The maximum total load for a double wheel print is  
8 about 1.48 times the maximum load for a single wheel print. The sequence of the load levels seems  
9 to indicate that using a higher load level first leads to a lower fatigue life than using a lower load  
10 level first. This topic requires further experimental research.

11 From the experiments, an *S-N* curve is developed. The relation between the load ratio and  
12 the number of cycles to failure is similar as what is observed for concrete under cycles of  
13 compression and concrete members under fatigue loading. As such, it is shown that compressive  
14 membrane action contributes to the increased capacity of transversely prestressed concrete decks  
15 when these are subjected to fatigue loading. The enhancement of compressive membrane action was  
16 determined in static tests as 2.32 as compared to the punching capacity predicted by the Eurocode  
17 with an empirical formula derived from slab-column connection tests.

## 18 19 **ACKNOWLEDGMENTS**

20 The authors wish to express their gratitude and sincere appreciation to the Dutch Ministry of  
21 Infrastructure and the Environment (Rijkswaterstaat) for financing this research work. We are  
22 deeply indebted to our colleague Albert Bosman for his work in the laboratory and the meticulous  
23 reporting of the experiments. We'd also like to thank our former colleagues Sana Amir and Patrick  
24 van Hemert for their contributions to the beginning of this research project.



## NOTATION

1		
2	$f_{cm,cube}$	average measured concrete cube compressive strength
3	$f_{ctm,cube}$	average measured concrete splitting tensile strength measured on cubes
4	$f_t$	tensile strength of the steel
5	$f_y$	yield strength of the steel
6	$F$	applied load
7	$F_{low}$	lower limit of applied load during fatigue tests
8	$F_{up}$	upper limit of applied load during fatigue tests
9	$N$	number of cycles
10	$P_{max}$	maximum load in experiment
11	$S$	fraction of static strength
12		
13		

## REFERENCES

- Ahmed, T., Burley, E. and Rigden, S., 1998, "The static and fatigue strength of reinforced concrete beams affected by alkali-silica reaction," *ACI Materials Journal*, V. 95, No. 4, Jul-Aug, pp. 376-388.
- Al-Zaid, R. Z. and Nowak, A. S., 1988, "Fatigue strength of prestressed concrete girder bridges," *Canadian Journal of Civil Engineering*, V. 15, No. 2, pp. 199-205.
- Amir, S., 2014, "Compressive Membrane Action in Prestressed Concrete Deck Slabs," Ph.D. Thesis, Delft University of Technology, pp. 317.
- Amir, S., Van der Veen, C., Walraven, J. C. and de Boer, A., 2016, "Experiments on Punching Shear Behavior of Prestressed Concrete Bridge Decks," *ACI Structural Journal*, V. 113, No. 3, pp. 627-636.
- Arora, S. and Singh, S. P., 2016, "Analysis of flexural fatigue failure of concrete made with 100% Coarse Recycled Concrete Aggregates," *Construction and Building Materials*, V. 102, 2016/01/15/, pp. 782-791.
- Bachman P.M., Kreger, M.E. and Breen, J. E., 1987, "An exploratory investigation of shear fatigue behavior of prestressed concrete girders," Research Report 465-1, The University of Texas at Austin, 198 pp.
- Bennett, E. W. and Muir, S. E. S. J., 1967, "Some fatigue tests of high-strength concrete in axial compression," *Magazine of Concrete Research*, V. 19, No. 59, pp. 113-117.
- Casas, J. R. and Crespo-Minguillon, C., 1998, "Probabilistic response of prestressed concrete bridges to fatigue," *Engineering Structures*, V. 20, No. 11, pp. 940-947.
- Casas, J.R., 2000, "Safety of Prestressed Concrete Bridges to Fatigue: Application to Serviceability Limit State of Decompression," *ACI Structural Journal*, V. 97.
- CEB Committee GTG 15, 1988, "Fatigue of Concrete Structures," CEB Bulletin d'information No 188.

1 CEN, 2003, "Eurocode 1: Actions on structures - Part 2: Traffic loads on bridges, NEN-EN 1991-  
2 2:2003," Comité Européen de Normalisation, Brussels, Belgium, 168 pp.

3 CEN, 2005, "Eurocode 2: Design of Concrete Structures - Part 1-1 General Rules and Rules for  
4 Buildings. NEN-EN 1992-1-1:2005," Comité Européen de Normalisation, Brussels, Belgium, 229  
5 pp.

6 El-Bahy, A., Kunnath, S. K., Stone, W. C. and Taylor, A. W., 1999, "Cumulative Seismic Damage  
7 of Circular Bridge Columns: Benchmark and Low-Cycle Fatigue Tests," *Structural Journal*, V. 96,  
8 No. 4.

9 Elfgren, L., 2015, "Fatigue Capacity of Concrete Structures: Assessment of Railway Bridges,"  
10 Lulea University of Technology.

11 Forrest, R. W. B., Higgins, C. and Senturk, A. E., 2010, "Experimental and Analytical Evaluation of  
12 Reinforced Concrete Girders under Low-Cycle Shear Fatigue," *ACI Structural Journal*, V. 107, No.  
13 2, March-April 2010, pp. 199-207.

14 Fujiyama, C., Gebreyouhannes, E. and Maekawa, K., 2008, "Present Achievement and Future  
15 Possibility of Fatigue Life Simulation Technology for RC Bridge Deck Slabs," *Society for Social  
16 Management Systems Internet Journal*, V. 4, No. 1.

17 Gallego, J. M., Zanuy, C. and Albajar, L., 2014, "Shear fatigue behaviour of reinforced concrete  
18 elements without shear reinforcement," *Engineering Structures*, V. 79, pp. 45-57.

19 Harajli, M. H. and Naaman, A. E., 1985, "Static and Fatigue Tests on Partially Prestressed Beams,"  
20 *Journal of Structural Engineering*, V. 111, No. 7, pp. 1602-1618.

21 Hawkins, N. M., 1974, "Fatigue Characteristics in Bond and Shear of Reinforced Concrete Beams,"  
22 *ACI Special Publication SP-41 Fatigue of Concrete*.

23 He, W., 1992, "Punching behaviour of composite decks with transverse prestressing," Ph.D Thesis,  
24 Queen's University, Ontario, Canada.

25 Hegger, J., Marzahn, G., Teworte, F. and Herbrand, M., 2015, "Principal tensile stress criterion for

1 the shear assessment of existing concrete bridges," *Beton- und Stahlbetonbau*, V. 110, No. 2, pp.  
2 82-95.

3 Hon, A., Taplin, G. and Al-Mahaidi, R. S., 2005, "Strength of reinforced concrete bridge decks  
4 under compressive membrane action," *ACI Structural Journal*, V. 102, No. 3, May-Jun, pp. 393-  
5 401.

6 Hordijk, D. A., 1991, "Local approach to fatigue of concrete," Ph.D. Thesis, Delft University of  
7 Technology, Delft, the Netherlands, pp.

8 Hordijk, D. A., Wolsink, G. M. and Vries, J. d., 1995, "Fracture and fatigue behaviour of a high  
9 strength limestone concrete as compared to gravel concrete," *Heron*, V. 40, No. 2, pp. 125-146.

10 Hsu, T. T. C., 1981, "Fatigue of plain concrete," *Journal of the American Concrete Institute*, V. 78,  
11 No. 4, pp. 292-305.

12 Isojeh, B., El-Zeghayar, M. and Vecchio, F. J., 2017, "High-cycle fatigue life prediction of  
13 reinforced concrete deep beams," *Engineering Structures*, V. 150, pp. 12-24.

14 Kirkpatrick, J., Rankin, G. I. B. and Long, A. E., 1986, "The influence of compressive membrane  
15 action on the serviceability of beam and slab bridge decks," *The structural engineer*, V. 64B, No. 1,  
16 pp. 6-9.

17 Koekkoek, R. T., van der Veen, C. and de Boer, A., 2018, "Fatigue Tests on Post-tensioned Bridge  
18 Decks," *fib symposium 2017*, Springer International Publishing, Maastricht, pp. 912-920.

19 Kuang, J. S. and Morley, C. T., 1992, "Punching shear behavior of restrained reinforced-concrete  
20 slabs," *ACI Structural Journal*, V. 89, No. 1, pp. 13-19.

21 Kuang, J. S. and Morley, C. T., 1993, "A Plasticity Model for Punching Shear of Laerally  
22 Restrained Slabs with Compressive Membrane Action," *International Journal of Mechanical*  
23 *Sciences*, V. 35, No. 5, pp. 371-385.

24 Lantsoght, E. O. L., van der Veen, C., de Boer, A. and Walraven, J. C., 2013, "Recommendations  
25 for the Shear Assessment of Reinforced Concrete Slab Bridges from Experiments " *Structural*

1    *Engineering International*, V. 23, No. 4, pp. 418-426.

2    Lantsoght, E. O. L., van der Veen, C. and de Boer, A., 2016, "Proposal for the fatigue strength of  
3    concrete under cycles of compression," *Construction and Building Materials*, V. 107, No. 15 March  
4    2016, pp. 138-156.

5    Lantsoght, E. O. L., Yang, Y., van der Veen, C., de Boer, A. and Hordijk, D. A., 2017, "Beam  
6    experiments on acceptance criteria for bridge load tests," *ACI Structural Journal*, V. 114, No. 4, pp.  
7    1031-1041.

8    Larson, K. H., Peterman, R. J. and Rasheed, H. A., 2005, "Strength-Fatigue Behavior of Fiber  
9    Reinforced Polymer Strengthened Prestressed Concrete T-Beams," *Journal of Composites for*  
10    *Construction*, V. 9, No. 4, pp. 313-326.

11    Lee, M. K. and Barr, B. I. G., 2004, "An overview of the fatigue behaviour of plain and fibre  
12    reinforced concrete," *Cement and Concrete Composites*, V. 26, No. 4, 2004/05/01/, pp. 299-305.

13    Liu, F., Zhou, J. and Yan, L., 2018, "Study of stiffness and bearing capacity degradation of  
14    reinforced concrete beams under constant-amplitude fatigue," *PLOS ONE*, V. 13, No. 3.

15    Low, A., 2011, "A Hole in Current Design Standards for Concrete Structures," *IABSE Symposium*,  
16    London, UK.

17    Mander, J. B., Panthaki, F. D. and Kasalanati, A., 1994, "Low-Cycle Fatigue Behavior of  
18    Reinforcing Steel," *Journal of Materials in Civil Engineering*, V. 6, No. 4, pp. 453-468.

19    Manfredi, G. and Pecce, M., 1997, "Low cycle fatigue of RC beams in NSC and HSC,"  
20    *Engineering Structures*, V. 19, No. 3, pp. 217-223.

21    Marshe, S. and Green, M. F., 1999, "Punching behaviour of composite bridge decks transversely  
22    prestressed with carbon fibre reinforced polymer tendons," *Canadian journal of civil engineering*,  
23    V. 26, No. 5, pp. 618-630.

24    Marthong, C., Dutta, A. and Deb, S. K., 2016, "Effect of Cyclic Loading Frequency on the  
25    Behavior of External RC Beam-Column Connections," *Journal of Earthquake Engineering*, V. 20,

1 No. 7, pp. 1126-1147.

2 Mitchell, A. D., Cook, W. D. and Dilger, W. H., 2005, "Effect of Size, Geometry and Material  
3 Properties on Punching Shear Resistance," *ACI SP-232: Punching Shear in Reinforced Concrete*  
4 *Slabs*, pp. 39-56.

5 Muller, J. F. and Dux, P. F., 1994, "Fatigue of Prestressed Concrete Beams with Inclined Strands,"  
6 *Journal of Structural Engineering ASCE*, V. 120, No. 4, pp. 1122-1139.

7 Naaman, A. E. and Founas, M., 1991, "Partially Prestressed Beams under Random-Amplitude  
8 Fatigue Loading," *Journal of Structural Engineering ASCE*, V. 117, No. 12, pp. 3742-3761.

9 Noël, M. and Soudki, K., 2015, "Fatigue Behavior of Full-Scale Slab Bridge Strips with FRP  
10 Reinforcement," *Journal of Composites for Construction*, V. 19, No. 2, pp. 04014047.

11 Oudah, F. and El-Hacha, R., 2013, "Research progress on the fatigue performance of RC beams  
12 strengthened in flexure using Fiber Reinforced Polymers," *Composites Part B: Engineering*, V. 47,  
13 2013/04/01/, pp. 82-95.

14 Regan, P. E. and Braestrup, M. W., 1985, "Punching Shear in Reinforced Concrete," CEB Bulletin  
15 168, 241 pp.

16 Rodrigues, J. F. S., Casas, J. R. and Almeida, P. A. O., 2013, "Fatigue-safety assessment of  
17 reinforced concrete (RC) bridges: application to the Brazilian highway network," *Structure and*  
18 *Infrastructure Engineering*, V. 9, No. 6, pp. 601-616.

19 Salem, A., 2013, "Dynamic analysis and fatigue assessment of bridge decks subjected to traffic and  
20 corrosion effects," M.S. Thesis, Colorado State University, Fort Collins, Colorado, pp. 119.

21 Saucedo, L., Yu, R. C., Medeiros, A., Zhang, X. and Ruiz, G., 2013, "A probabilistic fatigue model  
22 based on the initial distribution to consider frequency effect in plain and fiber reinforced concrete,"  
23 *International Journal of Fatigue*, V. 48, Mar, pp. 308-318.

24 Schlafli, M. and Bruhwiler, E., 1998, "Fatigue of existing reinforced concrete bridge deck slabs,"  
25 *Engineering Structures*, V. 20, No. 11, pp. 991-998.

1 Shahawi, M. E. and Batchelor, B. d., 1986, "Fatigue of Partially Prestressed Concrete," *Journal of*  
2 *Structural Engineering ASCE*, V. 112, No. 3, pp. 524-537.

3 Sonoda, K. and Horikawa, T., 1982, "Fatigue strength of reinforced concrete slabs under moving  
4 loads," V. 37, IABSE Reports.

5 Taylor, S. E., Rankin, B., Cleland, D. J. and Kirkpatrick, J., 2007, "Serviceability of bridge deck  
6 slabs with arching action," *ACI Structural Journal*, V. 104, No. 1, January - February 2010, pp. 39-  
7 48.

8 Teng, S., Ma, W., Tan, K. H. and Kong, F. K., 1998, "Fatigue tests of reinforced concrete deep  
9 beams," *The structural engineer*, V. 76, No. 18, pp. 347-352.

10 Teworte, F. and Hegger, J., 2011, "Shear Fatigue of Prestressed Concrete Beams," *IABSE 2011*, pp.  
11 8.

12 Teworte, F., Herbrand, M. and Hegger, J., 2015, "Structural Assessment of Concrete Bridges in  
13 Germany — Shear Resistance under Static and Fatigue Loading," *Structural Engineering*  
14 *International*, V. 25, No. 3, pp. 266-274.

15 Thomson, E., Bendito, A. and Flórez-López, J., 1998, "Simplified Model of Low Cycle Fatigue for  
16 RC Frames," *Journal of Structural Engineering*, V. 124, No. 9, pp. 1082-1085.

17 Tien, S. C. and Clyde, E. K., 1958, "Static and Fatigue Strength in Shear of Beams with Tensile  
18 Reinforcement," *ACI Journal Proceedings*, V. 54, No. 6.

19 Tilly, G.P., 1979, "Fatigue of steel reinforcement bars in concrete: a review," *Fatigue & Fracture of*  
20 *Engineering Materials & Structures*, V. 2, No. 3, pp. 251-268.

21 Tilly, G. P., 1984, "Fatigue testing and performance of steel reinforcement bars," *Matériaux et*  
22 *Construction*, V. 17, No. 1, January 01, pp. 43-49.

23 Tong, L., Liu, B., Xian, Q. and Zhao, X.-L., 2016, "Experimental study on fatigue behavior of Steel  
24 Reinforced Concrete (SRC) beams," *Engineering Structures*, V. 123, pp. 247-262.

25 Tong, P. Y. and de Batchelor, B. V., 1972, "Compressive membrane enahncement in two-way

1 bridge slabs," *ACI SP 30-12*, pp. 271-286.

2 Ueda, T., 1983, "Behavior in shear of reinforced concrete beams under fatigue loading," PhD  
3 Thesis, University of Tokyo, pp. 124.

4 van der Veen , C. and Bosman, A., 2014, "Fatigue strength of prestressed cast-in-between deck  
5 panels (in Dutch)," Stevin Report nr. 25.5-14-06, 65 pp.

6 Walraven, J. C., 2002, "Background document for EC-2, Chapter 6.4 Punching Shear," Delft  
7 University of Technology, Delft, The Netherlands, 16 pp.

8 Wang, H. L. and Song, Y. P., 2011, "Fatigue capacity of plain concrete under fatigue loading with  
9 constant confined stress," *Materials and Structures*, V. 44, pp. 253-262.

10 Weisu, Y. and Thomas, T. C. H., 1995, "Fatigue Behavior of Steel Fiber Reinforced Concrete in  
11 Uniaxial and Biaxial Compression," *ACI Materials Journal*, V. 92, No. 1, 1/1/1995.

12 Xin, Q., Dou, Y. and Chen, W., 2015, "Load Spectrum and Fatigue Life Computer Analysis of  
13 Prestressed Concrete Bridges," 247-266 pp.

14 Xin, Q., Dou, Y. and Li, S., 2017, "Fatigue Behavior of Prestressed Concrete Beams under  
15 Overload," 124-131 pp.

16 Younes, T., Al-Mayah, A. and Topper, T., 2017, "Fatigue performance of prestressed concrete  
17 beams using BFRP bars," *Construction and Building Materials*, V. 157, 2017/12/30/, pp. 313-321.

18 Yu, R. C., Saucedo, L. and Ruiz, G., 2014, "A probabilistic fatigue model for quasi-brittle  
19 materials," *Advanced Materials Research*, V. 875-877, pp. 1239-1242.

20 Yuan, M., Yan, D., Zhong, H. and Liu, Y., 2017, "Experimental investigation of high-cycle fatigue  
21 behavior for prestressed concrete box-girders," *Construction and Building Materials*, V. 157, pp.  
22 424-437.

23 Zeng, D., Wang, G.-l., Xie, J. and Zheng, X.-h., 2014, "Exploratory Experimental Study on Fatigue  
24 Prestress Loss of Prestressed Concrete Beams," *Journal of Highway and Transportation Research  
25 and Development (English Edition)*, V. 8, No. 2, pp. 37-41.



- 1 Zhang, F., Ding, Y., Xu, J., Zhang, Y., Zhu, W. and Shi, Y., 2016a, "Shear strength prediction for  
2 steel fiber reinforced concrete beams without stirrups," *Engineering Structures*, V. 127, No.  
3 Supplement C, pp. 101-116.
- 4 Zhang, W., Liu, X. and Gu, X., 2016b, "Fatigue behavior of corroded prestressed concrete beams,"  
5 *Construction and Building Materials*, V. 106, pp. 198-208.

6

7

## TABLES AND FIGURES

### List of Tables

Table 1 – Overview of static tests. Conversion: 1 kN = 0.225 kip, 1 MPa = 145 psi

Table 2 – Overview of fatigue tests. Conversion: 1 kN = 0.225 kip, 1 MPa = 145 psi

**Table 1 – Overview of static tests. Conversion: 1 kN = 0.225 kip, 1 MPa = 145 psi**

Test number	Size load (mm × mm)	$P_{max}$ (kN)	Age (days)	$f_{cm,cube}$ (MPa)	Failure mode
BB1	200 × 200	348.7	96	80.0	BP
BB2	200 × 200	321.4	99	79.7	BP
BB5*	200 × 200	490.4	116	79.2	FP
BB7	200 × 200	345.9	127	80.8	BP
BB16*	200 × 200	553.4	186	81.2	FP
BB19	200 × 200	317.8	223	79.9	BP
BB24 <sup>1</sup>	200 × 200	330.0	326	79.9	BP
BB25**	150 × 115	329.9	29	68.7	BP
BB27	150 × 115	364.6	62	76.9	BP
BB31	150 × 115	333.0	179	78.0	BP

\* Experiments with double wheel print

\*\* Ducts of diameter 30 mm (1.2 in) at 300 mm (12 in) on center.

<sup>1</sup> Static test after fatigue test to 1,500,000 cycles in which no failure occurred.

**Table 2 – Overview of fatigue tests. Conversion: 1 kN = 0.225 kip, 1 MPa = 145 psi**

Test number	Size load (mm × mm)	<i>F</i> (kN)	<i>F/P<sub>max</sub></i>	<i>N</i>	Age (days)	<i>f<sub>cm,cube</sub></i> (MPa)
BB17 <sup>+</sup>	200 × 200	275	0.80	13	147	82.6
BB18 <sup>+</sup>	200 × 200	291	0.85	16	56	82.6
BB23	200 × 200	200	0.60	24,800	301	79.9
BB24	200 × 200	150	0.45	1,500,000	307-326	79.9
BB26**	150 × 115	165	0.48	1,405,337	35-59	70.5-76.7
BB28	150 × 115	165	0.48	1,500,000	68-97	76.8-77.1
		200	0.58	1,000,000	97-113	77.1-77.3
		240	0.70	7,144	113	77.3
BB29	150 × 115	200	0.58	1,500,000	117-136	77.3-77.5
		220	0.64	264,840	136-139	77.5-77.6
BB30*	150 × 115	280	0.58	100,000	143-144	77.6
		240	0.50	1,400,000	144-162	77.6-77.8
		280	0.58	750,000	162-171	77.8-77.9
		320	0.67	500,000	171-177	77.9-78.0
		360	0.75	32,643	177	78.0
BB32	150 × 115	240	0.70	10,000	184	78.1
		200	0.58	272,548	185-187	78.1

<sup>+</sup> Tests with three cycles per load level

\* Experiments with double wheel print

\*\* Ducts of diameter 30 mm (1.2 in) at 300 mm (12 in) on center.

## 1    **List of Figures**

2    Fig. 1–Geometry of specimen: (a) side view showing prestressed girder (longitudinal) and  
3    transverse beams (section) and loading frame; (b) top view showing four prestressed girders, three  
4    deck panels, and loading frame; (c) side view showing a section of the slab-between-girder  
5    structural system and loading frame. Conversion: 1 mm = 0.04 in, 1 m = 3.3 ft.

6    Fig. 2– Photographs of setup. (a) Slab panel B ready for casting for additional fatigue tests. This  
7    photograph shows the formwork, transverse prestressing ducts, mild steel reinforcement, and  
8    remaining parts of the original test setup


9    Fig. 3–Numbering of tests: (a) original setup, including first series of static tests as reported by  
10    Amir (2016); (b) setup with new slab panel B for fatigue tests.

11    Fig. 4–Loading scheme: (a) static test BB25; (b) tests with a low number of cycles BB17; (c)  
12    fatigue tests, sinus load used for BB23.

13    Fig. 5–Specimen after failure: (a) static test BB25, (b) fatigue test BB26 with punching through of  
14    load plate, (c) fatigue test BB30 with double wheel print, (d) saw cut of deck showing the ducts of  
15    prestressing bars 26 – 30 (right to left) and punching cone of

16    Fig. 6–Development of cracks during BB29


17    Fig. 7–Resulting *S-N* curve from experiments.

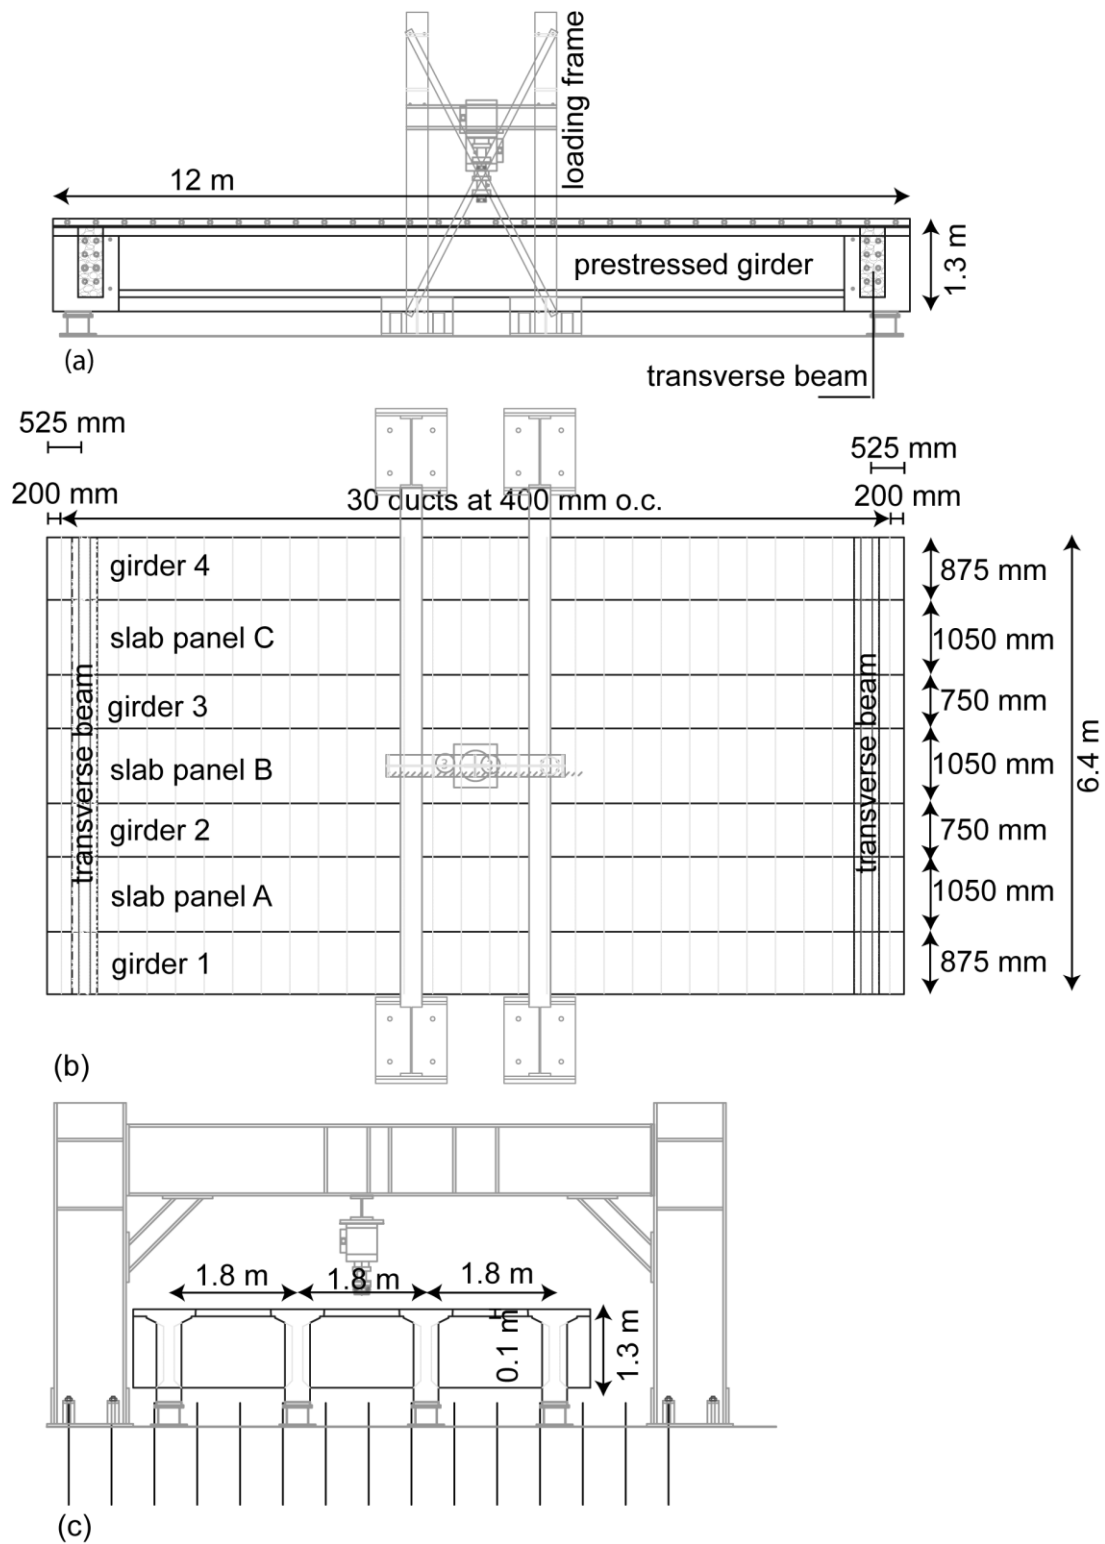




**Fig. 1–Geometry of specimen: (a) side view showing prestressed girder (longitudinal) and transverse beams (section) and loading frame; (b) top view showing four prestressed girders, three deck panels, and loading frame; (c) side view showing a section of the slab-between-girder structural system and loading frame. Conversion: 1 mm = 0.04 in, 1 m = 3.3 ft.**



**Fig. 2– Photographs of setup. (a) Slab panel B ready for casting for additional fatigue tests. This photograph shows the formwork, transverse prestressing ducts, mild steel reinforcement, and remaining parts of the original test setup. (b) Full test setup with new slab panel B.**

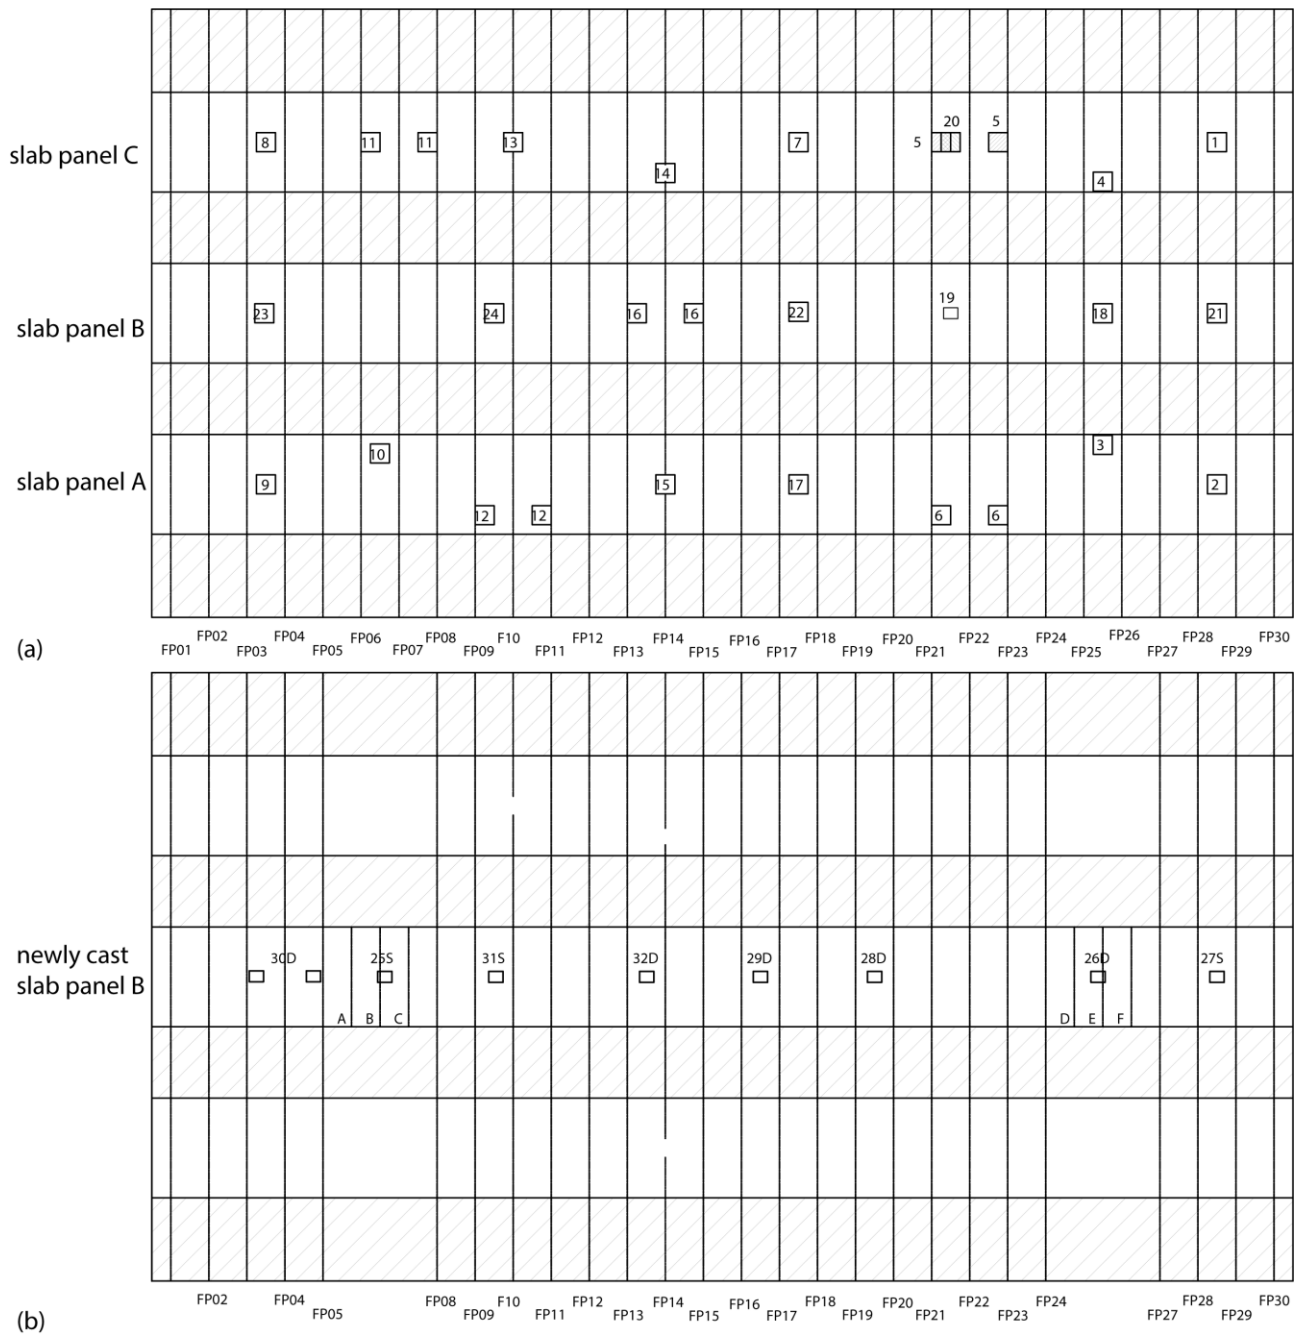

**Fig. 3–Numbering of tests: (a) original setup, including first series of static tests as reported by Amir (2016); (b) setup with new slab panel B for fatigue tests. For tests 25S and 26D, the spacing between the ducts is smaller, as indicated with the centerlines of the prestressing bars.**

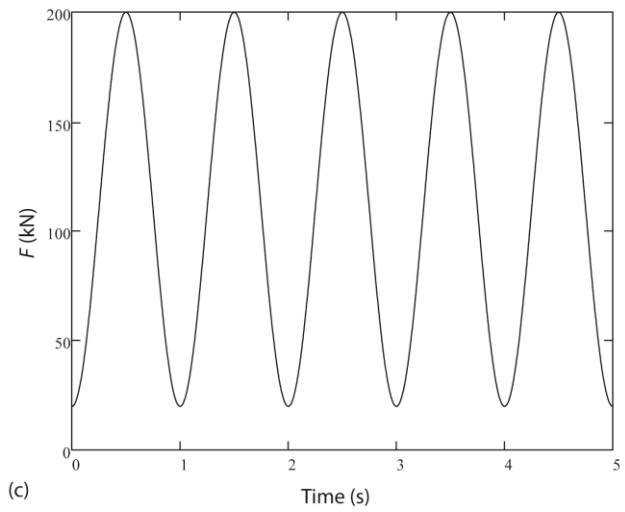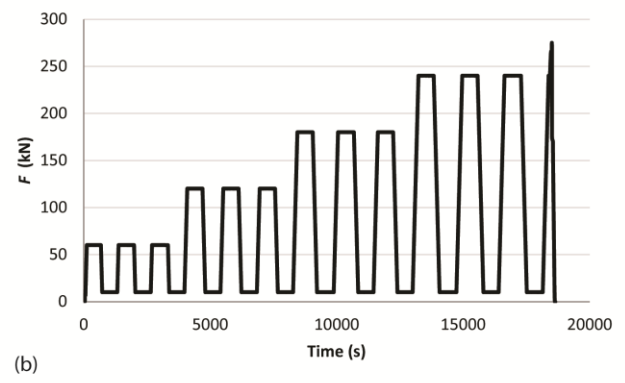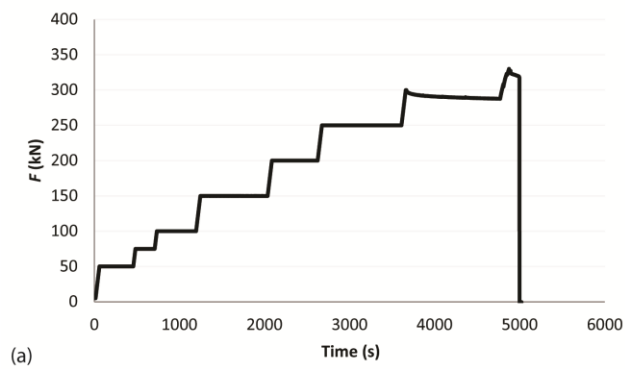


1 (c)


2 **Fig. 4–Loading scheme: (a) static test BB25; (b) tests with a low number of cycles BB17; (c)**

3 **fatigue tests, sinus load used for BB23.**




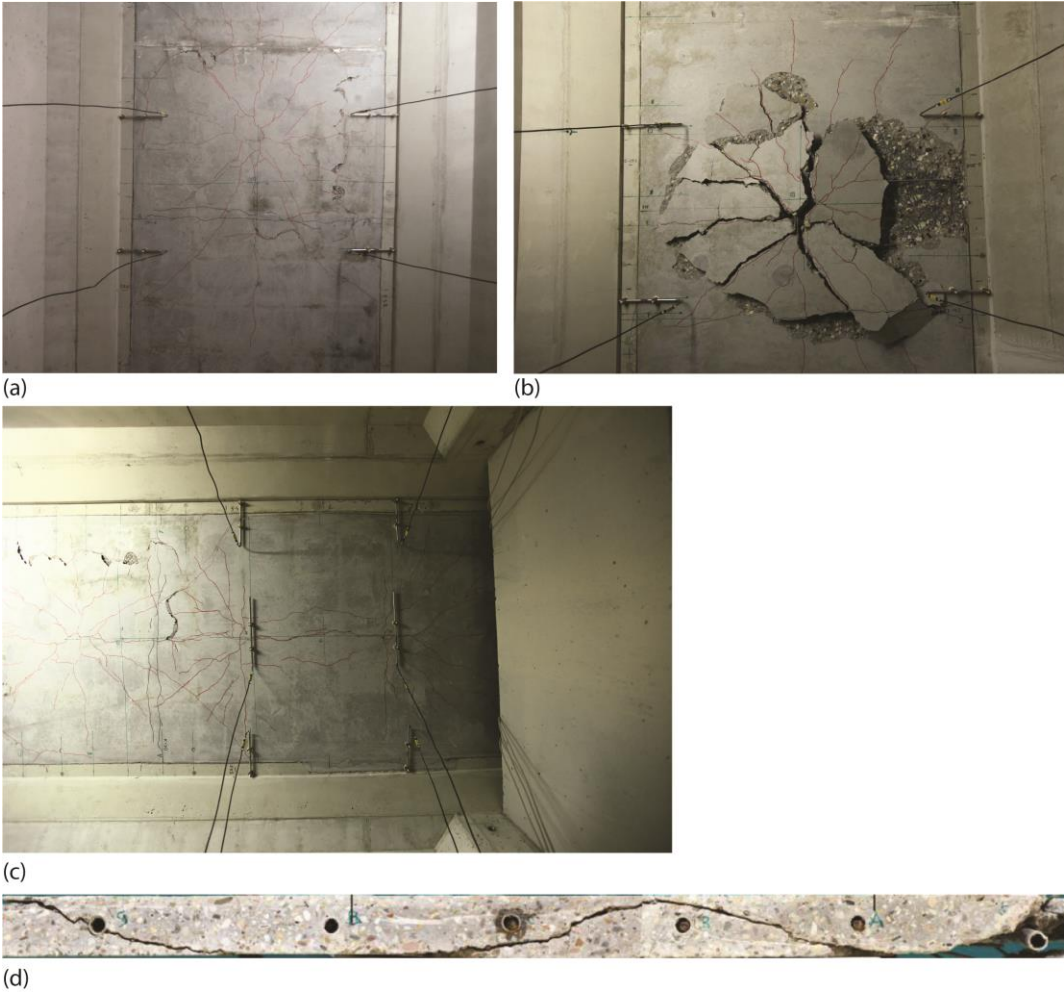

**Fig. 5–Specimen after failure: (a) static test BB25, (b) fatigue test BB26 with punching through of load plate, (c) fatigue test BB30 with double wheel print, (d) saw cut of deck showing the ducts of prestressing bars 26 – 30 (right to left) and punching cone of BB27.**

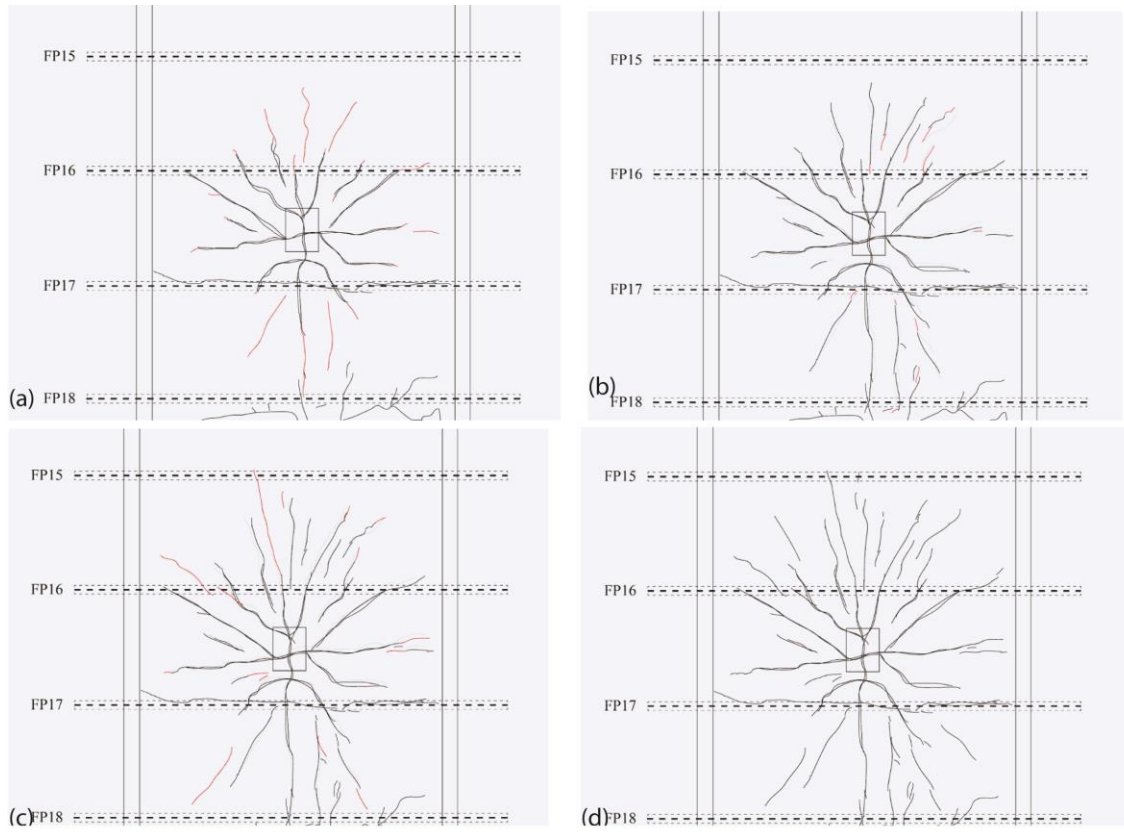

**Fig. 6–Development of cracks during BB29: (a) after 1,000 cycles; (b) after 100,000 cycles; (c) after 500,000 cycles; (d) after 1,500,000 cycles.**

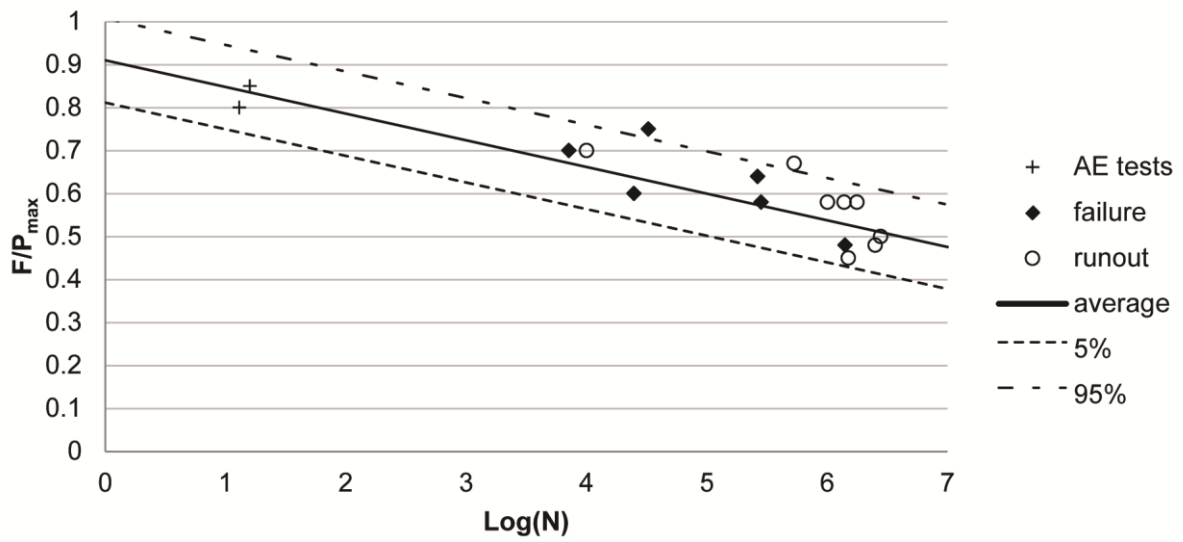

**Fig. 7–Resulting S-N curve from experiments.**