

Partitioning kinetics of alloying elements in a medium Mn steel during Q&P treatments using phase field modelling

Ayenampudi, Sudhindra; Celada-Casero, Carola; Mecozzi, Pina; Sietsma, Jilt; Santofimia, Maria Jesus

Publication date

2018

Document Version

Final published version

Citation (APA)

Ayenampudi, S., Celada-Casero, C., Mecozzi, P., Sietsma, J., & Santofimia, M. J. (2018). *Partitioning kinetics of alloying elements in a medium Mn steel during Q&P treatments using phase field modelling*. THERMEC 2018: International Conference on processing & manufacturing of advanced materials, Paris, France.

Important note

To cite this publication, please use the final published version (if applicable). Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights. We will remove access to the work immediately and investigate your claim.

Study of partitioning kinetics of alloying elements in a medium Mn steel during Q&P treatments using phase field modelling

Sudhindra Ayenampudi, C. Celada-Casero, M.G. Mecozzi, J. Sietsma, M.J. Santofimia


Delft University of Technology, Department of Materials Science and Engineering, Mekelweg 2, 2628 CD, Delft, The Netherlands

Background

Development:

AHSS in automotive parts to accomplish resource efficiency, high strength and less weight.

Q&P steels:

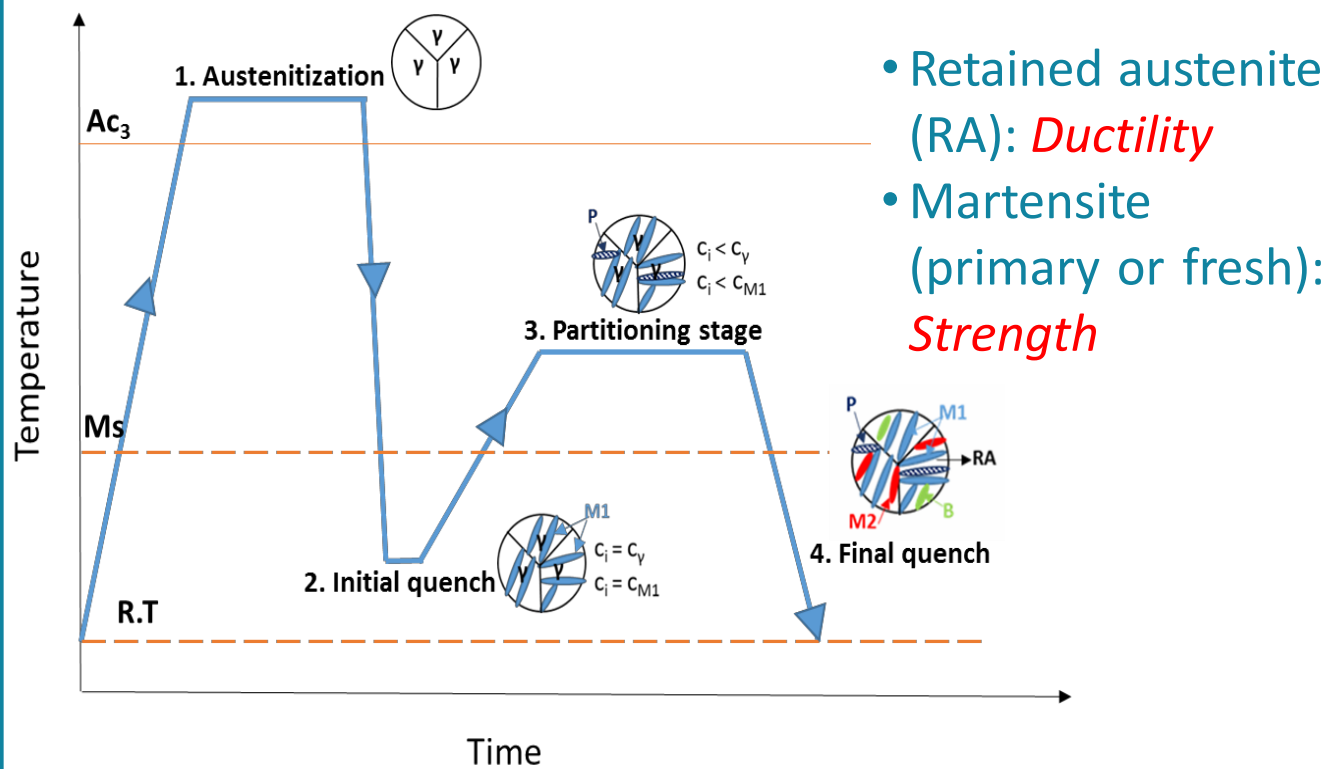

- Partitioning of alloying elements from martensite (α') to austenite (γ) and stabilization of austenite is crucial for Q&P process.
- So far carbon, an interstitial alloying element, is considered as the main austenite stabilizer in the Q&P process.
- Manganese and Nickel are also strong austenite stabilizers.

Objective

- To develop a model using phase field modelling for the study of the partitioning of interstitial and substitutional alloying elements (Mn, Si and Ni) during the quenching and partitioning process.

Approach

- Study different alloying systems: *FeCMn*, *FeCMnSi*, *FeCSiNi*, *FeCMnSiNi*, *FeCMnNi*.


Element	C	Mn	Si	Ni	Fe
Conc., (at. %)	1.38	4.58	2.91	1.86	89.27

- Partitioning conditions : 400, 500 and 600 °C : upto 500 s

Conclusions

Partitioning kinetics of alloying elements (Mn, Si and Ni) during the quenching and partitioning process is studied successfully. It was observed that a mutual impact on the partitioning of alloying elements is observed depending on the alloy systems.

Results

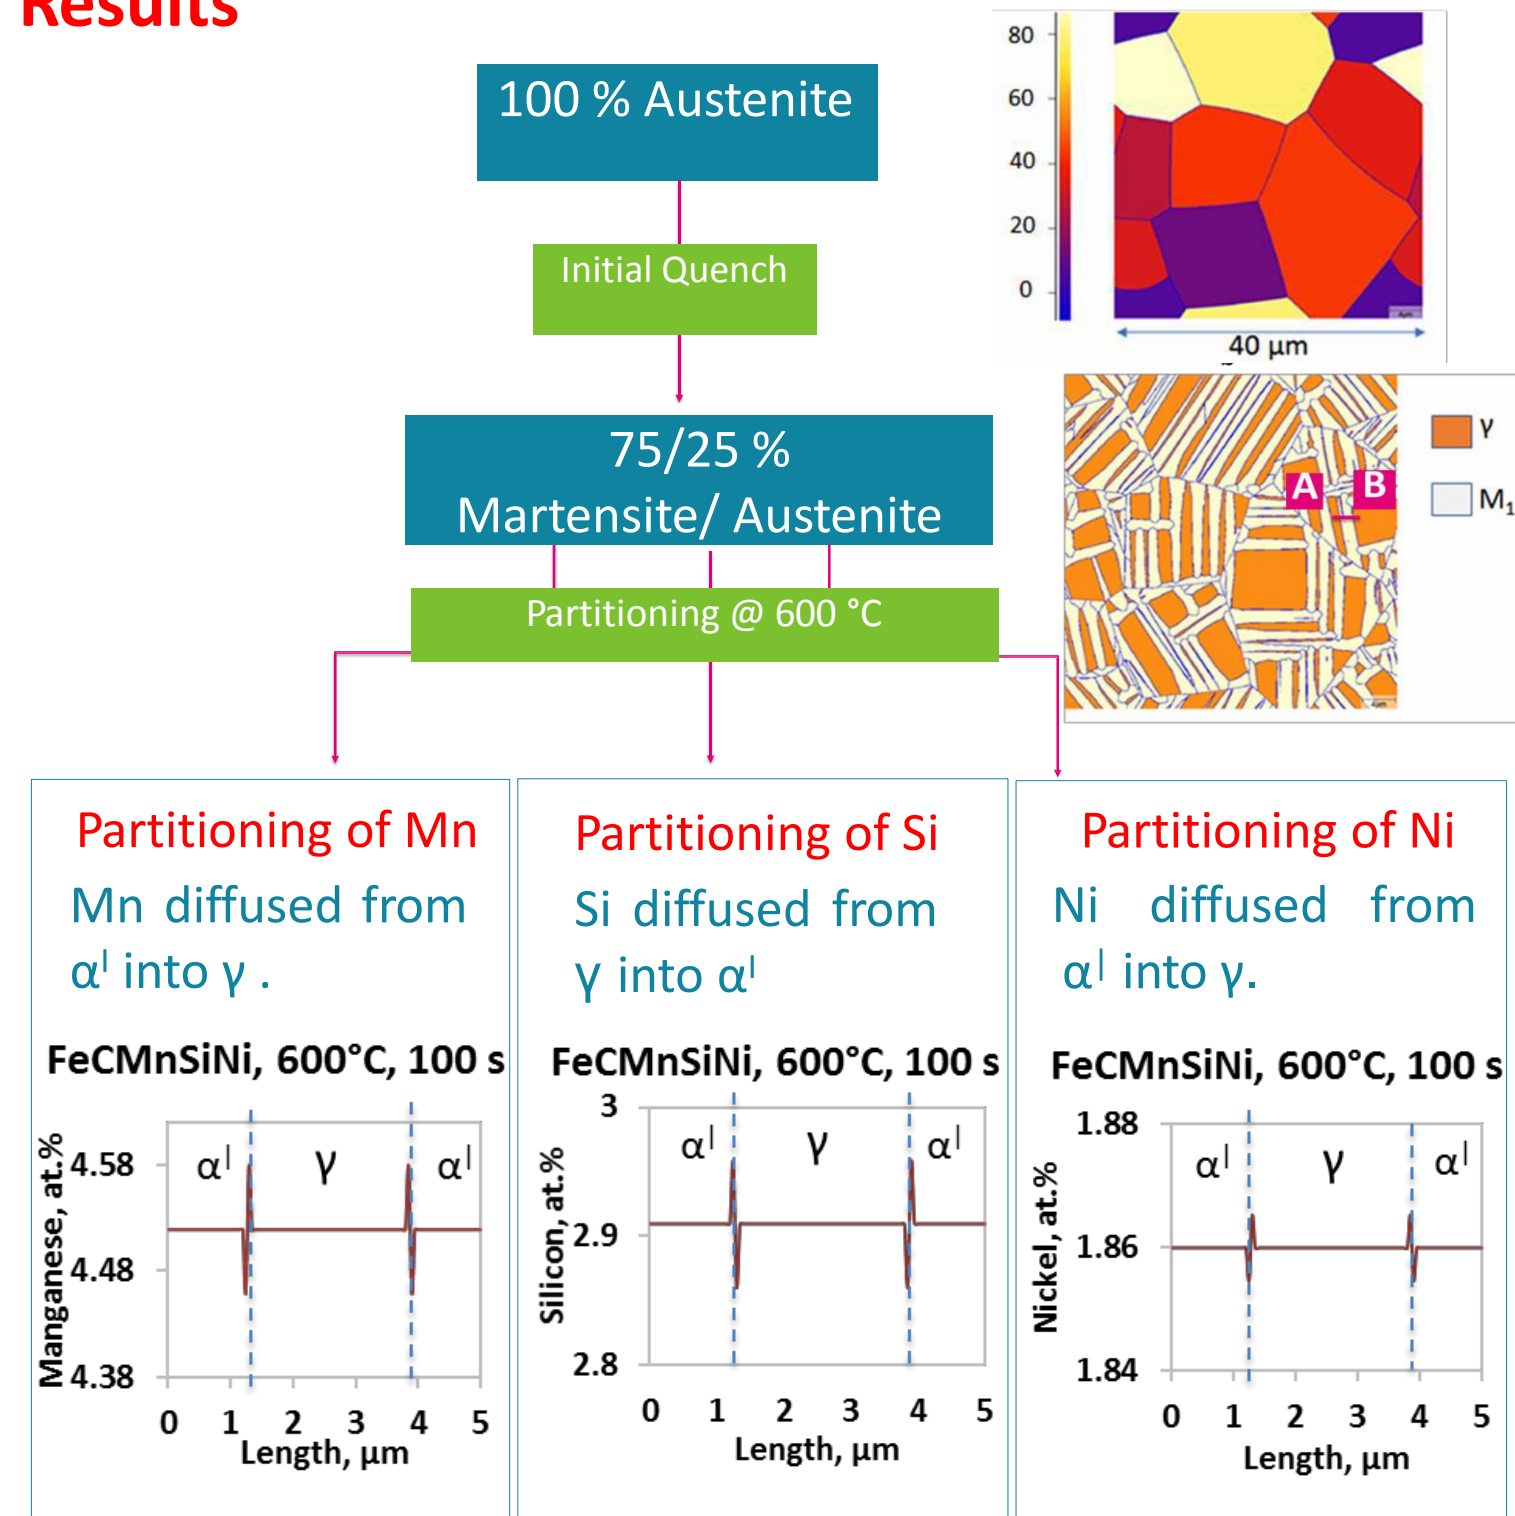

No.	Alloy	Time at which partitioning starts to be detected (s)		
		Mn	Si	Ni
1	FeCMn	40	-	-
2	FeCMnNi	40	-	50
3	FeCMnSiNi	70	40	90
4	FeCMnSi	125	90	-
5	FeCSiNi	-	125	>500

Discussion

- Partitioning of substitutionals is detected only at 600 °C.
- With the addition of Si a delay in Mn diffusion is observed (1-4) / (2-3).
- Addition of Ni promoted Mn diffusion in the presence of Si (3 - 4).
- In the absence of Mn, the diffusion of Si and Ni is delayed by long time (5).

contact: s.ayenampudi@tudelft.nl