

Fluoride removal from water by Ca-Al-CO₃ layered double hydroxides and simultaneous acidification

Wei, Liangfu; Zietzschmann, Frederik; Rietveld, Luuk C.; van Halem, Doris

DOI

[10.1016/j.jwpe.2021.101957](https://doi.org/10.1016/j.jwpe.2021.101957)

Publication date

2021

Document Version

Final published version

Published in

Journal of Water Process Engineering

Citation (APA)

Wei, L., Zietzschmann, F., Rietveld, L. C., & van Halem, D. (2021). Fluoride removal from water by Ca-Al-CO₃ layered double hydroxides and simultaneous acidification. *Journal of Water Process Engineering*, 40, 1-7.³ Article 101957. <https://doi.org/10.1016/j.jwpe.2021.101957>

Important note


To cite this publication, please use the final published version (if applicable).
Please check the document version above.

Copyright

Other than for strictly personal use, it is not permitted to download, forward or distribute the text or part of it, without the consent of the author(s) and/or copyright holder(s), unless the work is under an open content license such as Creative Commons.

Takedown policy

Please contact us and provide details if you believe this document breaches copyrights.
We will remove access to the work immediately and investigate your claim.



Fluoride removal from water by Ca-Al-CO₃ layered double hydroxides and simultaneous acidification

Liangfu Wei ^{*}, Frederik Zietzschmann, Luuk C. Rietveld, Doris van Halem

Faculty of Civil Engineering and Geosciences, Department of Sanitary Engineering, Delft University of Technology, P.O. Box 5048, 2600 GA Delft, The Netherlands

ARTICLE INFO

Keywords:

Ca-Al-CO₃ LDHs
Fluoride removal
Acidification by HCl and CO₂
PHREEQC modelling
Drinking water treatment

ABSTRACT

Millions of people worldwide are exposed to excessive concentrations of fluoride (F⁻) from groundwater sources. Ca-Al-CO₃ layered double hydroxides (LDHs) have shown promising defluoridation efficiency; however, defluoridation by Ca-Al-CO₃ LDHs is highly pH sensitive. This study showed that simultaneous acidification by conventional acids, such as HCl and CO₂ substantially increased the performance of Ca-Al-CO₃ LDHs for F-removal at environmentally relevant concentrations (e.g., 10 mg/L) to below the WHO guideline value (1.5 mg/L), while, in comparison to other acids (HNO₃, H₂SO₄, H₃PO₄), the use of HCl and CO₂ does not lead to the introduction of potentially harmful or undesired anions. The addition of HCl and CO₂ to LDHs suspensions did lead to changes to the LDHs structure. Leaching experiments, supported by PHREEQC modelling and characterization (SEM-EDX, XRD and FTIR), strongly suggest that the main mechanism of F- removal by Ca-Al-CO₃ LDHs was F⁻ adsorption or complexation onto/into various rehydrated mixed metal oxides which re-precipitated upon partial LDHs dissolution when acidifying.

1. Introduction

Fluoride (F⁻) is a trace element that plays a crucial role in the prevention and control of dental caries [1], however, exposure to excessive F⁻ concentrations can lead to dental and skeletal fluorosis [2]. Over 200 million people worldwide are exposed to excessive concentrations of F⁻ from groundwater sources [3]. India and China are the worst affected, around 67 million and 41 million people are affected by fluorosis, respectively [4]. In the past decades, numerous methods (e.g., adsorption, ion exchange, electrochemical, coagulation, and membrane processes,) and materials (e.g., activated alumina, bone char, synthetic hydroxyapatite, biosorbents) have been investigated for F⁻ removal [5, 6]. However, a sustainable solution to this ongoing crisis still appears intangible due to various obstacles, including removal efficiency, material costs, social acceptability, complexity of operation and maintenance [7].

Layered double hydroxides (LDHs) are a family of anionic clays that have attracted considerable attention and are considered applicable in F⁻ removal due to their high defluoridation capacity and cost-effectiveness [8]. The general formula of LDHs can be expressed as [M²⁺_{1-x}M³⁺_x(OH)₂]^{x+} [A^{m-}_{x/m} · nH₂O], where M²⁺ and M³⁺ correspond to a divalent and trivalent metal, respectively, where A^{m-} is an

exchangeable anion [9,10]. Various kinds of LDHs such as Mg-Al, Zn-Al, Ni-Al, Li-Al, Mg-Cr, Mg-Fe, Fe-Mg-Al LDHs, have been studied for F-removal from aqueous solutions [9,11–16]. Among these LDHs types, the most studied are the Mg-Al LDHs and their calcined products, which are of particular value at higher F- concentration ranges. In contrast, F-removal by Ca-Al LDHs is rarely reported, but considering the affinity of Ca²⁺ and Al³⁺ towards F- [17], has recently shown promising defluoridation efficiency at low, environmentally relevant F- concentrations (2–12 mg/L) [18] (Table 1). However, defluoridation by Ca-Al-CO₃ LDHs is highly pH sensitive, with better removals at pH 6–8 compared to ≥ pH 9, with the inherent problem of Ca-Al-CO₃ LDHs to react caustic upon addition to water (i.e., pH of point of zero charge 12–13), resulting in reduced defluoridation (~5%, pH = 11.5, initial F⁻ = 10 mg/L) [18].

As a consequence, acidification is required, e.g. by hydrochloric acid (HCl), nitric acid (HNO₃) [22–25], or CO₂ [7,26]. However, potential effects of such acidification on Ca-Al-CO₃ LDHs-induced F- removal and associated impacts on the water matrix have not been studied previously, despite being mentioned as problematic and potentially hampering successful application. The mechanism of F- removal by LDHs was mainly explained as F- adsorption and anion exchange [13, 14]. Considering the structural properties and the adsorption/ion exchange characteristics of LDHs, more examinations are needed to

^{*} Corresponding author.

E-mail addresses: L.Wei-1@tudelft.nl, weiliangfu12@mails.ucas.ac.cn (L. Wei).

<https://doi.org/10.1016/j.jwpe.2021.101957>

Received 31 October 2020; Received in revised form 27 January 2021; Accepted 29 January 2021

Available online 18 February 2021

2214-7144/© 2021 The Author(s). Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

Table 1

Comparison of F^- removal capacities by different LDHs at environmentally relevant concentrations.

Type of LDHs	Dosage (g/L)	F^- Initial concentration(mg/L)	pH	F^- removal capacity (mg/g)	References
Ca-Al- CO_3	1	10	6	9.1	[18]
Mg-Al- CO_3	1.11	10	6	7.63 ^a	[19]
Ni-Al- NO_3	2	10	6	4.82 ^a	[20]
Zn-Al-Cl	4	10.2	6.2	1.9	[21]
Mg-Al- CO_3	2.5	5	6	1.84	[16]

^a Kinetic model (Pseudo-second-order) value.

understand the possible negative impacts of applying Ca-Al- CO_3 LDHs in combination with acidification such as increased anion concentrations, competitive adsorption, and modifications/changes to the structure of Ca-Al- CO_3 LDHs, to further explore the mechanism of F^- removal. Therefore, the main objectives of this study were to a) elucidate and compare the impact of various pH-adjusting acids on F^- removal by Ca-Al- CO_3 LDHs from water at environmentally relevant F^- concentrations; b) examine the associated effects on the LDHs material and water composition; c) propose the main mechanism of F^- removal by Ca-Al- CO_3 LDHs.

2. Materials and methods

2.1. Chemicals and materials

All reagents including NaF, HCl, HNO_3 , H_2SO_4 , and H_3PO_4 used for the experiments were of analytical grade (Sigma-Aldrich). All the water used throughout the experiments and treatment processes was lab-produced deionized water. An F^- stock solution (1000 mg/L) was prepared with NaF and then diluted to the desired concentrations. The used Ca-Al- CO_3 LDHs (ACTILOX®CAHC) were of a $Ca_4Al_2(OH)_{12}CO_3 \cdot nH_2O$ ($n = 4-5$) type, with a Ca/Al ratio of 1.86, obtained from Nabaltec (Germany). Ca-Al- CO_3 LDHs were dried in an oven at 105 °C for 12 h before use to get rid of water that may be adsorbed.

2.2. Batch experiments and kinetic studies

An overview on the conducted experiments is given in Fig. 1. For

acids comparison, Ca-Al- CO_3 LDHs samples (0.02 or 0.1 g) were firstly dispersed in 100 mL NaF solution (10 mg F^- /L), directly followed by acidification to pH 6 (within ~15 min) using various acids (1 M HCl, 1 M HNO_3 , 0.5 M H_2SO_4 , 0.33 M H_3PO_4) or by injection of CO_2 with a flow of 5 mL/min (10 min), respectively (acid doses recorded), and stirring for 24 h (enough to reach equilibrium based on previous studies [14,18]) with subsequent pH measurement and membrane filtration by 0.45 μm to remove the solids. In a similar manner, different pHs (6, 7, 8, 9, 10) were compared at an initial F^- concentration of 10 mg/L (100 mL), as well as effects of different LDHs' doses (0.1, 0.15, 0.2, 0.5, 1, 2 g/L) at pH 6 (cf. supplementary materials (Figure S1)). Ca^{2+} and Al^{3+} leaching were examined afterwards, and, to minimize potential impacts of Al-species smaller than the membrane pore size (0.1 μm), the samples were centrifuged at 10,000 rpm for 10 min prior to filtration. Effects of variable F^- concentration on the overall removal efficiency were tested at pH 6, 0.2 g Ca-Al- CO_3 LDHs, 100 mL, and initial F^- of 2, 4, 6, 8, 10, 12 mg/L (cf. supplementary materials). In kinetic studies ("acidification sequence", cf. Fig. 1), pH was adjusted to 6 by both HCl and CO_2 after 1 g/L LDHs addition, followed by F^- dosage of 10 mg F^- /L (cf. "B" in Fig. 1), and F^- was dosed to 10 mg F^- /L, followed by acidification (same dosage as in "B") and 1 g/L LDHs addition (cf. "C" in Fig. 1). The solutions were stirred for 3 h under pH 6 with a cap on the jars (1 L) to avoid the influence of air, samples of 3 mL each were collected and filtered (0.45 μm) after 0, 1, 2, 3, 4, 5, 6, 7, 8, 9, 10, 15, 20, 25, 30, 40, 50, 60, 90, 120, 150 and 180 min, respectively. Solid material samples were obtained by 0.1 μm filtration at the end of the kinetic experiments, and dried in an oven at 105 °C for 12 h, then cooled and ground into powder for further use.

2.3. Analytical methods

Scanning electron microscope (SEM) images and X-ray analyses (EDX) of Ca-Al- CO_3 LDHs samples before and after F^- removal were taken on a JEOL scanning electron microscope (JSM-IT100). The functional groups in samples were determined from fourier transform infrared spectroscopy (FTIR) spectra by a fourier transform infrared spectrometer (Spectrum TM 100 Optical ATR-FTIR), following pelletization of the materials. The crystalline structure of the samples was characterized using an X-ray Bruker D8 Advance diffractometer (Bruker).

The concentrations of F^- , Cl^- , NO_3^- , SO_4^{2-} , PO_4^{3-} and HCO_3^- were analyzed by Ion chromatography (IC) (Metrohm 881, Switzerland) with a column of Mestrosep A Supp 5 and ICE-99-9860, respectively. Concentrations of Ca^{2+} and Al^{3+} leaching after experiment were measured by ICP-MS (Analytik Jena AG, Germany).

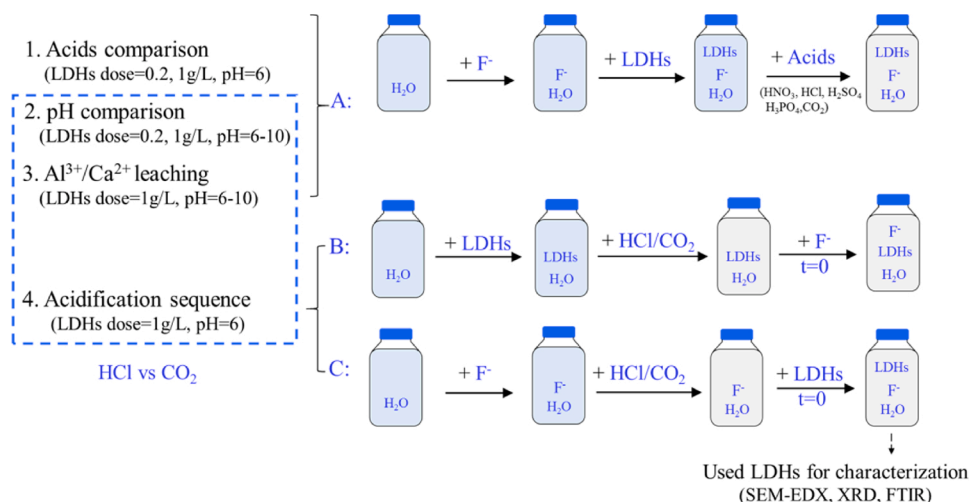


Fig. 1. Overview of experimental conditions and procedures.

2.4. Data evaluation and modelling

The F^- removal efficiency (%) at equilibrium and non-equilibrium contact times was calculated using the following formula:

$$F^- \text{ removal efficiency} = \frac{(C_0 - C)}{C_0} \times 100\% \quad (1)$$

where C_0 and C are initial and F^- concentrations (mg/L) at equilibrium and non-equilibrium contact times, respectively. Data evaluation and model fitting to experimental data were accomplished using OriginPro 9.0. The calculation of saturation index (SI) of CaF_2 and the distribution of Al and Ca species was carried out using PHREEQC [27,28]. Detailed descriptions of simulation and input files can be found in the supplementary information (cf. Section 4).

3. Results and discussion

3.1. Comparison of acidification by various acids

The F^- removal by Ca-Al- CO_3 LDHs at 0.2 and 1 g/L from solutions adjusted to pH 6 by acidification with various acids are shown in Fig. 2A. A dosage of 0.2 g/L was chosen to reach well-discernible results, which is comparatively lower than previous studies on LDHs (0.5–7.5 g/L) [14, 29,30], and much lower than that on Indian Bauxite (12–77 g/L) [7]. A pH of 6 was chosen to reach well-discernible results and because substantial benefits of lower pH were observed previously [14,18,30]. Under acidified conditions the removal reached 37% (CO_2) and 64% (HCl) at a 0.2 g/L LDHs dose, 90% (CO_2) and 94% (HCl) at 1 g/L LDHs. At the lower LDHs dose, acidification by HNO_3 resulted in a similar F^- removal as HCl, whereas for H_3PO_4 , H_2SO_4 , removals were 5 and 8 % lower, respectively, possibly due to increased competition of PO_4^{3-} and SO_4^{2-} with F^- because of their electrostatic interaction, as compared to Cl^- and NO_3^- [24]. At the higher LDHs dose of 1 g/L, F^- removal differences between the tested acidification methods were small and seemed to remain unchanged at different initial concentrations of F^- , due to overall high removal $\geq 90\%$.

The high pH buffering capacity of Ca-Al- CO_3 LDHs caused the solution pH to rise to 10.9–11.5 at LDHs doses of 0.2 and 1 g/L, but better F^- removals were obtained at lower pH. Therefore, to reach the intended pH (6), considerable dosages of acids were required after LDHs addition. At LDHs dose of 1 g/L, the addition of HCl (~478 mg/L) is similar to the report by Cherukumilli et al. (211–401 mg/L) while the addition of CO_2 (~0.99 g/L) is much lower than the reports by Cherukumilli et al. (22.5–34.7 g/L) [7] and Li et al. (80.1 g/L) [26], although the amount of acids is usually not reported [22–25]. The consequent anion concentrations (Cl^- , NO_3^- , PO_4^{3-} , SO_4^{2-} and HCO_3^-) at 1 g/L LDHs are given in Fig. 2B, at the start and end of the experiments, respectively. The consequent concentrations of NO_3^- , SO_4^{2-} and PO_4^{3-} were much higher

than the drinking water threshold (cf. Table S3), whereas the concentrations of Cl^- and HCO_3^- were thought to be acceptable because although excessive Cl^- concentrations (> 250 mg/L) is detectable by taste, a guideline value for Cl^- in drinking water is not established, and HCO_3^- is not proposed as a chemical related to taste or odour in drinking water [31,32]. The NO_3^- concentration, after dosing HNO_3 , was 835 mg/L and decreased only slightly during the experiments (829 mg/L). At lower Ca-Al- CO_3 LDHs dose (0.2 g/L), NO_3^- concentration was still high (~170 mg/L). The PO_4^{3-} concentrations, after dosing H_3PO_4 , decreased from 795 to 238 mg/L during the experiments, and SO_4^{2-} concentrations, after dosing H_2SO_4 , decreased from 671 to 618 mg/L. These results indicate a partial uptake of PO_4^{3-} and SO_4^{2-} by Ca-Al- CO_3 LDHs and could potentially result in competition between F^- and PO_4^{3-} or SO_4^{2-} , as LDHs have been previously documented to have a stronger affinity for multivalent anions [14], then for monovalent ions. The high uptake of PO_4^{3-} could also be due to the formation of Ca- PO_4 precipitate (SI of Hydroxyapatite = 6.31 calculated by PHREEQC at pH6) under such condition [33]. HCl acidification resulted in ~450 mg/L Cl^- and the concentration of introduced HCO_3^- , after dosing CO_2 , was approximately 550 mg/L at 1 g/L LDHs.

3.2. Effect of pH and initial F^- concentration on F^- removal

While considerable differences were not discernible between HCl and CO_2 acidification at the high LDHs dose, F^- removal was slightly higher for HCl than for CO_2 at the lower LDHs doses at pH 6 and 7; at higher pH, no differences appeared (Fig. 3A). Overall, F^- removal increased with decreasing pH, and the effect was more pronounced for HCl than for CO_2 acidification, possibly due to competition by HCO_3^- . Upon application of CO_2 , HCO_3^- concentrations rose to 550 mg/L and 168 mg/L at pH 6 and 7, respectively, which is higher than for HCl (< 90 mg/L, because of the dissolution of LDHs). Earlier research has indicated a slight reduction in F^- removal due to elevated HCO_3^- concentrations (> 250 mg/L); such an adverse effect was not observed for Cl^- as a competitive anion [18].

The F^- removal by 0.2 and 1 g/L Ca-Al- CO_3 LDHs at varying initial F^- concentrations are shown in Fig. 3B. The F^- removal decreased gradually with the increase of initial F^- concentrations at 0.2 g/L LDHs; for 1 g/L LDHs, the initial F^- concentration has little discernible effect. Independent of the initial F^- concentration, higher F^- removal was reached when acidifying with HCl than when using CO_2 , especially at the lower LDHs dose (0.2 g/L), likely confirming potential adverse competitive effects of HCO_3^- (cf. 3.1). At the Ca-Al- CO_3 LDHs dose of 0.2 g/L, concentration of, approximately, 6 mg/L and 3.8 mg/L of F^- could be reduced when pH was adjusted by HCl and CO_2 , respectively, whereas all the initial concentrations, 2–12 mg F^- /L, were reduced to below WHO guideline (1.5 mg/L) at the Ca-Al- CO_3 LDHs dose of 1 g/L (Figure S4).

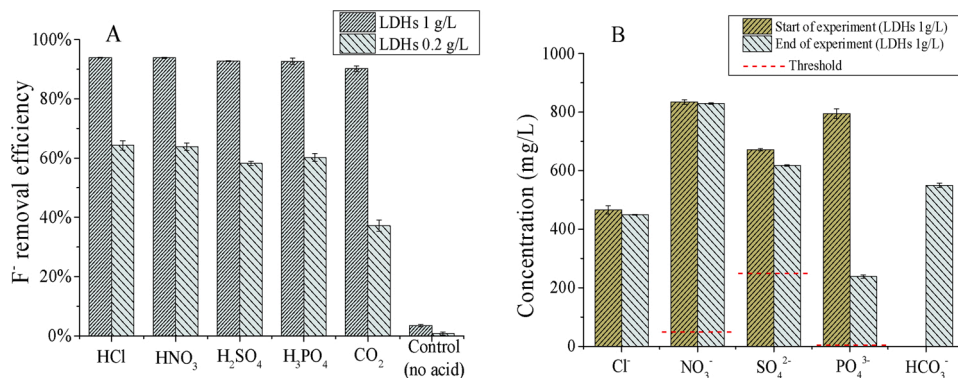


Fig. 2. (A) F^- removal efficiency at 0.2 and 1 mg/L LDHs dose, and (B) anion concentration of different pH-adjusting acids at start and end of the experiment. Initial F^- = 10 mg/L, initial pH = 6, $T = 22 \pm 1^\circ C$, LDHs dose = 0.2 or 1 g/L.

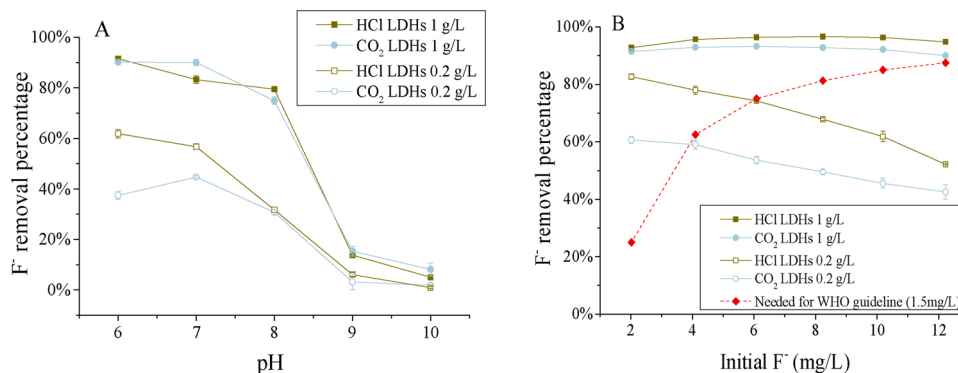


Fig. 3. The effect of pH (A) (Initial F^- = 10 mg/L; pH = 6, 7, 8, 9, 10; LDHs dose = 0.2 g/L; $T = 22 \pm 1^\circ C$) and initial F^- (B) (LDHs Initial F^- = 24,681,012 mg/L; pH = 6; LDHs dose = 0.2 or 1 g/L; $T = 22 \pm 1^\circ C$) on F^- removal by Ca-Al- CO_3 .

3.3. Effect of acidification sequence on F^- removal

In order to better understand the F^- removal process, two groups of experiments were carried out to investigate the effect of time and acidification order. F^- was dosed either after or before acidification of the Ca-Al- CO_3 LDHs-containing suspension (cf. Fig. 1). The absolute and relative F^- removal is depicted over time for the two tested acidification orders with HCl and CO_2 , respectively, in Fig. 4. Several models fit to the kinetic experimental data and are presented in the supplementary information. HCl acidification resulted in faster removal kinetics than CO_2 acidification. Specifically, equilibria were reached after 20 min, 60 min, 90 min, >180 min for HCl + F^- before/after and CO_2 + F^- before/after, respectively. Thus, the F^- removal performance was overall faster when LDHs were added to solutions already containing F^- and acid, as compared to when F^- was dosed to suspensions previously containing acidified LDHs.

Potentially, the Ca-Al- CO_3 LDHs surfaces were firstly activated by acids when acidified (prior to F^- addition) and simultaneously occupied by respective anions (Cl^- and HCO_3^-), which subsequently had to be replaced when F^- was added. The effect was particularly pronounced for CO_2 , where the F^- removal during F^- dosage after acidification only approached the removal during F^- dosage before acidification after several hours. Possibly, the competition for adsorption sites between F^- and HCO_3^- were more pronounced than with the other ions. When CO_2 is diffusing into the solution, the hydration of CO_2 can occur in two paths. At pH > 10, the predominant mechanism is via direct reaction with OH^- forming HCO_3^- and CO_3^{2-} (instantaneous); at pH < 8, the direct hydration is the predominant mechanism forming H_2CO_3 and HCO_3^-

(instantaneous) [34,35] and resulting in a high concentration of HCO_3^- which has an adverse effect on F^- removal [18]. During HCl acidification there was little difference between dosage of F^- before or after acidification (similar equilibrium removal). Apparently Cl^- had little competition with F^- . Although < 90 mg/L of HCO_3^- can be formed because of the dissolution of LDHs after HCl acidification, no adverse effect was observed at this concentration [18].

3.4. Al^{3+} and Ca^{2+} leaching

Fig. 5 shows the Al^{3+} and Ca^{2+} concentrations after addition of 1 g/L Ca-Al- CO_3 LDHs. The concentration reached ~70 mg/L for both Al^{3+} and Ca^{2+} without pH control (pH = 11.5). After HCl acidification, Al^{3+} concentrations ranged between 0.05 mg/L (pH 6) and 75 mg/L (pH 10) and Ca^{2+} concentrations ranged between 184 mg/L (pH 9) and 273 mg/L (pH 6). During CO_2 acidification, Al^{3+} concentrations were in the range of 0.12 mg/L (pH 6) to 54 mg/L (pH 10), and Ca^{2+} ranged from 35 mg/L (pH 9) to 241 mg/L (pH 6). CO_2 acidification thus caused slightly higher Al^{3+} leaching at pH below 9 but less Ca^{2+} leaching compared to HCl. Ca^{2+} concentrations were within the ranges of the WHO (100–300 mg/L), however, occasionally additional Ca^{2+} removal could be needed if this water is distributed for drinking water supply (World Health Organization, 2011). The observed Al^{3+} and Ca^{2+} leaching indicates the dissolution of Ca-Al- CO_3 LDHs. Based on its formula $Ca_4Al_2(OH)_{12}CO_3 \cdot nH_2O$ ($n = 4-5$) and the measured concentrations of Ca^{2+} , approximately 24% of Ca-Al- CO_3 LDHs was dissolved with no pH control and over 94% (273 mg/L) and 83% (241 mg/L) dissolved at pH 6 for HCl and CO_2 acidification, respectively.

3.5. Proposed removal mechanism

Given the reduced Al^{3+} concentrations at decreased pH, it is likely that Al-containing precipitates were formed from the previously dissolved LDHs. Composition, structure and morphology of precipitated Al species are affected by pH value, from a pure bayerite phase through bayerite ($\alpha-Al(OH)_3$) and boehmite ($\gamma-AlOOH$) to amorphous Al species with decreasing pH from 11 to 6 [36]. F^- removal from solution onto such precipitates was previously observed [37,38].

The distribution of Al and F species under varying pH conditions was simulated by PHREEQC based on the found leaching concentrations, as shown in Fig. 6. For the Al species distribution, $Al(OH)_4^-$ accounted for ~8% at pH 6, ~70% at pH 7, and >99% for pH > 8. The predominant species at pH 6 was $Al(OH)_2^+$ (~32%), followed by AlF_2^+ (~23%) and AlF_2^+ (~22%). For the F species distribution, free F^- was ~0.3% at pH 6, ~10% at pH 7, and >94% at pH > 8. AlF_2^+ (~55%) and AlF_2^+ (~44%) were two predominant species at pH 6.

PHREEQC modelling (cf. Figures S5, S6) underlined that CaF_2 precipitation was strongly hampered by Al^{3+} presence, indicating that the here observed F^- removal resulted rather from F/Al interactions than

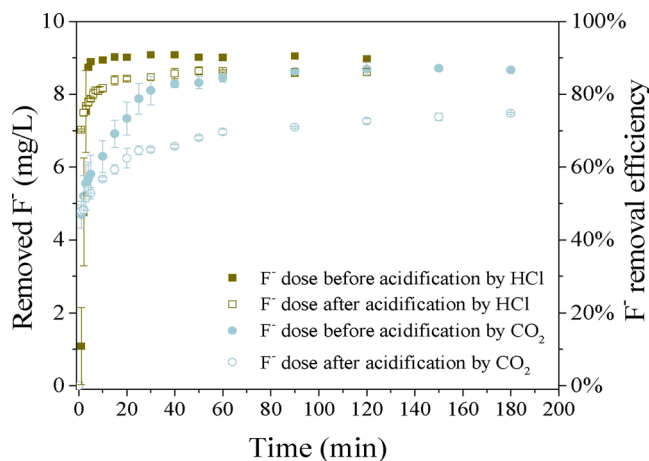


Fig. 4. F^- removal capacity and removal percentage, as a function of time. Initial F^- = 10 mg/L; pH = 6; LDHs dose = 1 g/L; $T = 22 \pm 1^\circ C$.

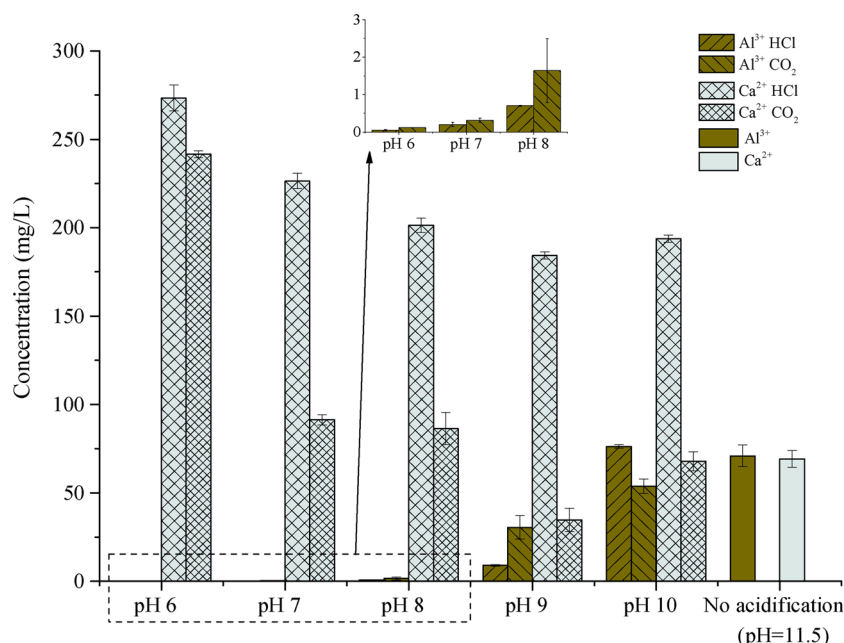


Fig. 5. Al^{3+} and Ca^{2+} leaching from Ca-Al- CO_3 LDHs under different pH conditions; inset: Al^{3+} concentrations for pH 6, 7, 8. Initial $\text{F}^- = 10 \text{ mg/L}$, $T = 22 \pm 1^\circ\text{C}$, LDHs dose = 1 g/L.

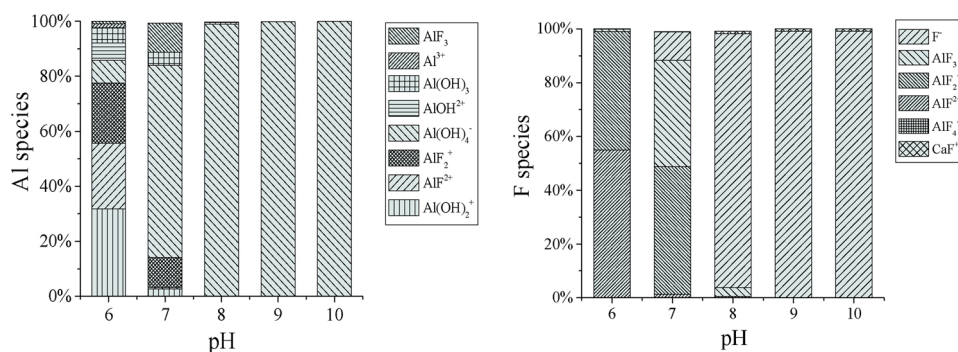


Fig. 6. Distribution of Al and F species under different pH conditions simulated by PHREEQC. $T = 25^\circ\text{C}$, $\text{pH} = 6-10$, $\text{F}^- = 10 \text{ mg/L}$, the molar ratio of $\text{F}^-/\text{Al}^{3+} = 0.2$.

from F/Ca. According to PHREEQC modelling and literature data, the various Al-containing species such as $\text{Al}(\text{OH})_2^+$, AlF_2^+ , AlF_3 , $\text{Al}(\text{OH})_4^-$, etc. were present under the tested conditions, particularly when lowering the $\text{pH} < 8$, likely serving as adsorption/complexation/interaction partners for F^- , depending on the respective pH and $\text{F}^-/\text{Al}^{3+}$ ratio [39–41] (Fig. 7). But specifically for CO_2 acidification, F^- can also be removed by CaCO_3 adsorption [42]. The pH buffering capacity of Ca-Al- CO_3 LDHs played a positive impact on F- removal by fully hydrolyzing Al^{3+} before Al-F complexation.

3.6. Characterization of Ca-Al- CO_3 LDHs before and after use

Given the observed dissolution and re-precipitation of the tested Ca-Al- CO_3 LDHs, morphology and structure, before and after experiments (cf. “C” in Fig. 1), were further characterized. The SEM-EDX results in Figure S7 show a reduction of Ca, particularly for acidification by HCl, confirming the observed leaching of this cation. The formed HCO_3^- after CO_2 acidification ($\sim 550 \text{ mg/L}$) is much more than that after HCl acidification ($< 90 \text{ mg/L}$), which likely inhibited the dissolution of CaCO_3 (cf. Figure S6). EDX further shows presence of F- after the experiments, thus verifying F^- uptake into solids for both acidification methods. XRD patterns of Ca-Al- CO_3 LDHs before and after the experiments are given in Fig. 8A. The virgin LDHs show sharp and symmetric characteristic

peaks (003 and 006) of hydrotalcite-like compounds at lower 2Theta values [43], which almost disappeared by both tested acidification methods, indicating the damage of the layered hydrotalcite-like structure, different from previously examined with Mg-Al type LDHs [13,29,44]. The phase identification shows that the Ca-Al- CO_3 LDHs after HCl acidification were amorphous, whereas after CO_2 acidification the main compounds were CaCO_3 and $\text{Al}(\text{OH})_3$. The aqueous stability of LDHs is driven by the solubility of the corresponding divalent metal salt [45,46]. The damage of the layered hydrotalcite-like structure after acidification indicated a low stability of Ca-Al- CO_3 LDHs.

The FTIR spectra of Ca-Al- CO_3 LDHs before and after the experiments are shown in Fig. 8B. Acidification by HCl led to profound structural changes, as indicated by the disappearance of nearly all bands (OH groups in brucite-like layers, interlayer and/or adsorbed water at $3600-3300 \text{ cm}^{-1}$ [47], sorbed CO_2 and interlamellar CO_3^{2-} at 1419 and 1363 cm^{-1} [29,48], as well as calcium and aluminum oxides at 1000 and 600 cm^{-1} [30,48]). Structural changes by CO_2 acidification were less severe, mainly impacting the layered hydrotalcite-like structure (disappearance of bands between 3600 and 3300 cm^{-1}). The high concentration of HCO_3^- resulting from the CO_2 injection likely inhibited the dissolution of CaCO_3 (cf. Figure S6) and probably led to the formation of $\text{Al}(\text{OH})_3$ due to the weak acid property of H_2CO_3 [49]. Adsorbents with a high defluorination capacity are often double or triple metal oxides,

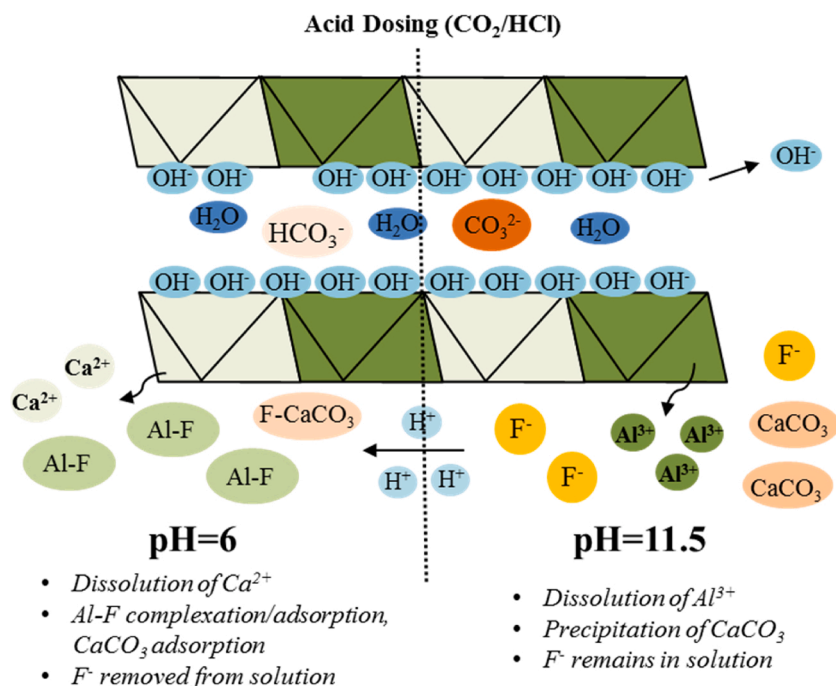


Fig. 7. Schematic drawing of proposed dissolution-complexation/adsorption mechanism.

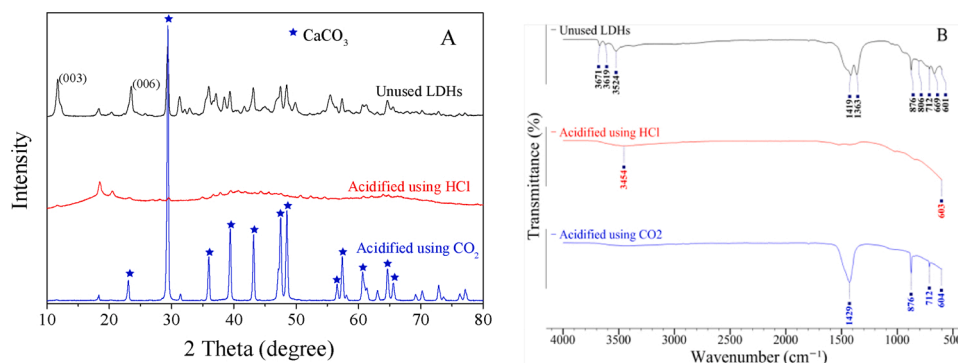


Fig. 8. XRD patterns (A) and FTIR spectra (B) of the Ca-Al- CO_3 LDHs before and after experiments.

while they are generally amorphous and show increased performance at lower pH (<7) [50–53]. The main mechanism of F^- uptake by Mg-Al LDHs (Mg-Al- NO_3 and Mg-Al- Cl LDHs) has been previously proposed as the result of exchange between aqueous F^- and NO_3^- or Cl^- anions positioned in the Mg-Al LDHs interlayer [13]. However, our proposed removal mechanism is F^- adsorption or complexation onto/into Al-containing species and CaCO_3 (in the case of CO_2 acidification), which can be supported by the characterization results. These results suggest that the layered hydroxide-like structure was damaged, F^- was present and $\text{Al}(\text{OH})_3$ and CaCO_3 (in the case of CO_2 acidification) were formed after the experiments. Apart from the SEM-EDX, XRD and FTIR characterization, additional research is recommended, such as transmission electron microscopy (TEM) and X-ray photoelectron spectroscopy (XPS), to further examine the F^- removal mechanism.

4. Conclusions

In the present work the effects of pH-adjusting acids on F^- removal from water by Ca-Al- CO_3 LDHs were reported. Acidification by conventional acids like HCl or CO_2 led to a substantially increased performance of Ca-Al- CO_3 LDHs for F^- removal at environmentally relevant concentrations (e.g., 10 mg/L) with a relatively lower LDHs dose than

that found in most of the literature. The observed F^- removal under LDHs acidification to pH 6 with HCl and CO_2 were 62 and 92% (HCl), and 38 and 90% (CO_2) at LDHs doses of 0.2 and 1 g/L, respectively. Addition of HCl and CO_2 to LDHs suspensions led to changes to the LDHs structure, demonstrated by SEM, EDX, XRD, and FTIR. Leaching experiments, supported by PHREEQC modelling, strongly suggest that the main mechanism of F^- removal by Ca-Al- CO_3 LDHs was F^- adsorption or complexation onto/into various rehydrated mixed metal oxides which re-precipitate upon partial LDHs dissolution when acidifying. The benefits of the lower costs (cf. cost estimate calculation in SI) and lower residual anion concentrations lead to the recommendation to apply CO_2 as the acidification method in combination with Ca-Al- CO_3 LDHs. The reusability and feasibility of Ca-Al- CO_3 LDHs in column and real groundwater should be examined in future studies.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

The authors are grateful for the financial support from the China Scholarship Council (No. 201504910742). We express our sincere appreciation to Waterlab of Delft University of Technology. Ruud Hendrikx and Yageng Li at the Department of Materials Science and Engineering of the Delft University of Technology is acknowledged for the XRD and SEM analysis. We also thank Zhenming Li from Microlab of the Delft University of Technology for his assistance on the FTIR analysis.

Appendix A. Supplementary data

Supplementary material related to this article can be found, in the online version, at doi:<https://doi.org/10.1016/j.jwpe.2021.101957>.

References

- [1] P.E. Petersen, M.A. Lennon, Effective use of fluorides for the prevention of dental caries in the 21st century: the WHO approach, *Community Dent. Oral Epidemiol.* 32 (2010) 319–321.
- [2] D. Kanduti, P. Sterbenk, B. Artnik, Fluoride: a review of use and effects on health, *Mater. Sociomed.* 28 (2016) 133–137.
- [3] S. Ayoob, A.K. Gupta, Fluoride in drinking water: a review on the status and stress effects, *Crit. Rev. Environ. Sci. Technol.* 36 (2006) 433–487.
- [4] A.K. Gupta, S. Ayoob, Fluoride in Drinking Water: Status, Issues, and Solutions, CRC Press, 2016.
- [5] S. Ayoob, A.K. Gupta, V.T. Bhat, A conceptual overview on sustainable technologies for the defluoridation of drinking water, *Crit. Rev. Environ. Sci. Technol.* 38 (2008) 401–470.
- [6] L. Osterwalder, C.A. Johnson, H. Yang, R.B. Johnston, Multi-criteria assessment of community-based fluoride-removal technologies for rural Ethiopia, *Sci. Total Environ.* 488–489 (2014) 532–538.
- [7] K. Cherukumilli, T. Maurer, J.N. Hohman, Y. Mehta, A.J. Gadgil, Effective remediation of groundwater fluoride with inexpensively processed indian bauxite, *Environ. Sci. Technol.* (2018) 52.
- [8] Z. Sun, J.-S. Park, D. Kim, C.-H. Shin, W. Zhang, R. Wang, P. Rao, Synthesis and adsorption properties of Ca-Al layered double hydroxides for the removal of aqueous fluoride, *Water Air Soil Pollut.* 228 (2017) 23.
- [9] L. Batistella, L.D. Venquiaruto, M.D. Luccio, J.V. Oliveira, S.B.C. Pergher, M. A. Mazutti, D.D. Oliveira, A.J. Mossi, H. Treichel, R. Dallago, Evaluation of acid activation under the adsorption capacity of double layered hydroxides of Mg–Al–CO₃ type for fluoride removal from aqueous medium, *Behav. Brain Res.* 224 (2011) 180–188.
- [10] W.T. Reichle, Synthesis of anionic clay minerals (mixed metal hydroxides, hydrotalcite), *Solid State Ion.* 22 (1986) 135–141.
- [11] Q. Chang, L. Zhu, Z. Luo, M. Lei, S. Zhang, H. Tang, Sono-assisted preparation of magnetic magnesium–aluminum layered double hydroxides and their application for removing fluoride, *Ultrason. Sonochem.* 18 (2011) 553–561.
- [12] J. Du, D.A. Sabatini, E.C. Butler, Synthesis, characterization, and evaluation of simple aluminum-based adsorbents for fluoride removal from drinking water, *Chemosphere* 101 (2014) 21–27.
- [13] T. Kameda, J. Oba, T. Yoshioka, Kinetics and equilibrium studies on Mg–Al oxide for removal of fluoride in aqueous solution and its use in recycling, *J. Environ. Manage.* 156 (2015) 252–256.
- [14] L. Lv, J. He, M. Wei, D. Evans, Z. Zhou, Treatment of high fluoride concentration water by MgAl–CO₃ layered double hydroxides: kinetic and equilibrium studies, *Water Res.* 41 (2007) 1534–1542.
- [15] S. Mandal, S. Mayadevi, Cellulose supported layered double hydroxides for the adsorption of fluoride from aqueous solution, *Chemosphere* 72 (2008) 995–998.
- [16] H. Wang, J. Chen, Y. Cai, J. Ji, L. Liu, H.H. Teng, Defluoridation of drinking water by Mg/Al hydrotalcite-like compounds and their calcined products, *Appl. Clay Sci.* 35 (2007) 59–66.
- [17] P.S. Ghosal, A.K. Gupta, An insight into thermodynamics of adsorptive removal of fluoride by calcined Ca–Al–(NO₃) layered double hydroxide, *RSC Adv.* 5 (2015) 105889–105900.
- [18] L. Wei, F. Zietzschmann, L.C. Rietveld, D. van Halem, Fluoride removal by Ca–Al–CO₃ layered double hydroxides at environmentally-relevant concentrations, *Chemosphere* (2019), 125307.
- [19] L. Lv, J. He, M. Wei, X. Duan, Kinetic studies on fluoride removal by calcined layered double hydroxides, *Ind. Eng. Chem. Res.* 45 (2006) 8623–8628.
- [20] L. Wang, D. He, Removal of fluoride from water by NiAl layered double hydroxide prepared by solvothermal method, *J. Chem. Pharm. Res.* 6 (2014) 413–417.
- [21] S. Mandal, S. Mayadevi, Adsorption of fluoride ions by Zn–Al layered double hydroxides, *Appl. Clay Sci.* 40 (2008) 54–62.
- [22] Y. Chi, Y. Chen, C. Hu, Y. Wang, L. Chen, Preparation of Mg–Al–Ce triple-metal composites for fluoride removal from aqueous solutions, *J. Mol. Liq.* 242 (2017) 416–422.
- [23] P.P. Huang, C.Y. Cao, F. Wei, Y.B. Sun, W.G. Song, MgAl layered double hydroxides with chloride and carbonate ions as interlayer anions for removal of arsenic and fluoride ions in water, *RSC Adv.* 5 (2015) 10412–10417.
- [24] D. Kang, X. Yu, M. Ge, M. Lin, X. Yang, Y. Jing, Insights into adsorption mechanism for fluoride on cactus-like amorphous alumina oxide microspheres, *Chem. Eng. J.* 345 (2018) 252–259.
- [25] J.H. Kim, C.G. Lee, J.A. Park, J.K. Kang, S.Y. Yoon, S.B. Kim, Fluoride removal using calcined Mg/Al layered double hydroxides at high fluoride concentrations, *Water Sci. Technol. Water Supply* 13 (2013) 249–256.
- [26] Y. Li, J. Wang, X. Peng, N. Fan, Z. Luan, Evaluation of arsenic immobilization in red mud by CO₂ or waste acid acidification combined ferrous (Fe²⁺) treatment, *J. Hazard. Mater.* 199 (2012) 43–50.
- [27] S. Dhiman, A.K. Keshari, Hydrogeochemical evaluation of high-fluoride groundwaters: a case study from Mehsana District, Gujarat, India, *Hydrol. Sci. J. Des Sci. Hydrol.* 51 (2006) 1149–1162.
- [28] D.L. Parkhurst, C. Appelo, Description of input and examples for PHREEQC version 3: a computer program for speciation, batch-reaction, one-dimensional transport, and inverse geochemical calculations, *US Geological Survey*. (2013).
- [29] P. Cai, H. Zheng, C. Wang, H. Ma, J. Hu, Y. Pu, P. Liang, Competitive adsorption characteristics of fluoride and phosphate on calcined Mg–Al–CO₃ layered double hydroxides, *J. Hazard. Mater.* 213 (2012) 100–108.
- [30] S. Dhiman, A.K. Keshari, Physicochemical characterization and adsorption behavior of calcined Zn/Al hydrotalcite-like compound (HTLc) towards removal of fluoride from aqueous solution, *J. Colloid Interface Sci.* 261 (2003) 213–220.
- [31] D.K. Mueller, D.R. Helsel, Nutrients in the Nation's Waters: Too Much of a Good Thing? US Government Printing Office, 1996.
- [32] World Health Organization, Guidelines for Drinking-water Quality, 4th ed, 2011.
- [33] C.M. Kanno, R.L. Sanders, S.M. Flynn, G. Lessard, S.C. Myneni, Novel apatite-based sorbent for defluoridation: synthesis and sorption characteristics of nano-micro-crystalline hydroxyapatite-coated-limestone, *Environ. Sci. Technol.* 48 (2014) 5798–5807.
- [34] P. Danckwerts, A. Kennedy, The kinetics of absorption of carbon dioxide into neutral and alkaline solutions, *Chem. Eng. Sci.* 8 (1958) 201–215.
- [35] D.M. Kern, The hydration of carbon dioxide, *J. Chem. Educ.* 37 (1960) 14.
- [36] X. Du, Y. Wang, X. Su, J. Li, Influences of pH value on the microstructure and phase transformation of aluminum hydroxide, *Powder Technol.* 192 (2009) 40–46.
- [37] Z. He, R. Liu, J. Xu, H. Liu, J. Qu, Defluoridation by Al-based coagulation and adsorption: species transformation of aluminum and fluoride, *Sep. Purif. Technol.* 148 (2015) 68–75.
- [38] J. Lu, W. Liu, W. Zheng, The removal mechanisms of fluoride ion by aluminum salt coagulant, *Acta Scientiae Circumstantiae* (2000) 6.
- [39] S. Bi, C. Wang, Q. Cao, C. Zhang, Studies on the mechanism of hydrolysis and polymerization of aluminum salts in aqueous solution: correlations between the “Core-links” model and “Cage-like” Keggin–Al₁₃ model, *Coord. Chem. Rev.* 248 (2004) 441–455.
- [40] Y. Deng, D.K. Nordstrom, R.B. McCleskey, Fluoride geochemistry of thermal waters in Yellowstone National Park: I. Aqueous fluoride speciation, *Geochim. Cosmochim. Acta* 75 (2011) 4476–4489.
- [41] R. Liu, L. Zhu, W. Gong, H. Lan, H. Liu, J. Qu, Effects of fluoride on coagulation performance of aluminum chloride towards Kaolin suspension, *Colloids Surf. A Physicochem. Eng. Asp.* 421 (2013) 84–90.
- [42] S. Budyanto, Y.-L. Kuo, J. Liu, Adsorption and precipitation of fluoride on calcite nanoparticles: a spectroscopic study, *Sep. Purif. Technol.* 150 (2015) 325–331.
- [43] F. Cavani, F. Trifiro, A. Vaccari, Hydrotalcite-type anionic clays: preparation, properties and applications, *Catal. Today* 11 (1991) 173–301.
- [44] L. Lv, Defluoridation of drinking water by calcined MgAl–CO₃ layered double hydroxides, *Desalination* 208 (2007) 125–133.
- [45] Rk. Allada, A. Navrotsky, H.T. Berbeco, W.H. Casey, Thermochemistry and aqueous solubilities of hydrotalcite-like solids, *Science* 296 (2002) 721–723.
- [46] J.J. Bravo-Suárez, E.A. Pérez-Mozo, S.T. Oyama, Review of the synthesis of layered double hydroxides: a thermodynamic approach, *Quim. Nova* 27 (2004) 601–614.
- [47] M. Noorjahan, M. Khayyum, K.G. Mangatayaru, A novel cobalt modified layered double hydroxide for the efficient removal of fluoride, *Mater. Focus.* 4 (2015) 283–289.
- [48] L. Lv, J. He, M. Wei, D. Evans, X. Duan, Uptake of chloride ion from aqueous solution by calcined layered double hydroxides: equilibrium and kinetic studies, *Water Res.* 40 (2006) 735–743.
- [49] J.D. Hem, C.E. Roberson, Form and stability of aluminum hydroxide complexes in dilute solution, *Geol. Surv. Water-Supply Pap.(US);(United States)* (1967) 1827.
- [50] L. Han, S. Deng, Z. Li, Y. Gang, J. Huang, Preparation of Al–Ce hybrid adsorbent and its application for defluoridation of drinking water, *J. Hazard. Mater.* 179 (2010) 424–430.
- [51] M. Wang, X. Yu, C. Yang, X. Yang, M. Lin, L. Guan, M. Ge, Removal of fluoride from aqueous solution by Mg–Al–Zr triple-metal composite, *Chem. Eng. J.* 322 (2017) 246–253.
- [52] X. Wu, Y. Zhang, X. Dou, M. Yang, Fluoride removal performance of a novel Fe–Al–Ce trimetal oxide adsorbent, *Chemosphere* 69 (2007) 1758–1764.
- [53] Y. Yang, Y. Ling, J.P. Chen, Adsorption of fluoride by Fe–Mg–La triple-metal composite: adsorbent preparation, illustration of performance and study of mechanisms, *Chem. Eng. J.* 262 (2015) 839–846.